

# Analysis of Russian "Vertex" High-Strength Glass Fiber

by William A. Spurgeon, Elias J. Rigas,  
and Matthew S. Burkins

ARL-TR-2045

September 1999

19991006 130

Approved for public release; distribution is unlimited.

DTIC QUALITY INSPECTED 4

**The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.**

**Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.**

**Destroy this report when it is no longer needed. Do not return it to the originator.**

# Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5069

---

---

ARL-TR-2045

September 1999

## Analysis of Russian "Vertex" High-Strength Glass Fiber

William A. Spurgeon, Elias J. Rigas, and Matthew S. Burkins  
Weapons and Materials Research Directorate, ARL

---

---

## Abstract

---

This report presents the results of mechanical and ballistic tests required in MIL-PRF-46197A (U.S. Department of the Army, "A Laminate, High Strength Glass Fiber Reinforced Polyester Resin," U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, 16 April 1997) on Russian Vertex high-strength glass that is supposed to be equivalent to domestic S-2 glass. The results of tensile tests of 250-yield yarns of both types of fibers were very similar, with the Vertex glass possibly as much as 2% stronger. For fabricating composites, however, a pseudo-250-yield yarn made by combining three 750-yield yarns was woven to make the fabrics used in the polyester resin composites for the mechanical and ballistic tests. This pseudo-250-yield yarn was about 7% weaker than the true 250-yield yarns. The tensile strength of the composites and the ballistic performance vs. a 20-mm fragment-simulating projectile (FSP) were both below the requirements of the specification, probably as a consequence of the use of this weaker yarn. The flexure and shear properties of the composites just met the specification, while the compressive strength was about 12% low. These results suggest that the sizing needs some fine-tuning to improve the performance of the Vertex glass fibers.

## Acknowledgments

A number of people contributed to this effort. Mr. Richard O'Meara of ROM Development Corporation was instrumental in setting up the acquisition of the Vertex glass used in this project. Mr. Timothy Collins of Advanced Glass Fiber Yarns provided S-2 glass yarns for test. Mr. David Chandlee and Mr. Timothy O'Shea of the University of Delaware helped with the sample fabrication and testing the yarns. Mr. Jeffrey Swab of the Metals and Ceramics Branch of the U.S. Army Research Laboratory (ARL) performed the Weibull analyses on the tensile test results on the yarns. Mr. Donovan Harris and Mr. Phillip Patterson of the Polymers Research Branch of ARL performed the energy-dispersive x-ray analysis (EDAX) and infrared (IR) measurements, respectively. Ms. Linda Ghiorse, Mr. Paul Moy, Mr. Steven Ngyuen, and Mr. Alan Teets of the Polymers Research Branch helped set up the mechanical test equipment. Ms. Eleanor Deal, Mr. William Edmanson, and Mr. Bernard McKay of the Lethal Mechanisms Branch conducted the 20-mm fragment-simulating projectile (FSP) ballistic testing at Experimental Facility 110G. Mr. Donald Little and Mr. Vaughn Torbert of the Armor Mechanics Branch conducted the 0.22- and 0.30-cal. FSP testing at Experimental Facility 108. Ms. Mary Adamson of the ARL Foreign Intelligence Office helped obtain valuable funding for this project. These contributions are deeply appreciated.

INTENTIONALLY LEFT BLANK.

# Table of Contents

	<u>Page</u>
<b>Acknowledgments</b> .....	iii
<b>List of Figures</b> .....	vii
<b>List of Tables</b> .....	ix
<b>1. Introduction</b> .....	1
<b>2. Material Acquisition</b> .....	2
<b>3. Chemical Composition and Sizing Chemistry</b> .....	4
<b>4. Tensile Tests on Glass Yarns</b> .....	6
<b>5. Composite Mechanical Properties</b> .....	12
<b>6. Ballistic Testing</b> .....	14
<b>7. Conclusions</b> .....	18
<b>8. References</b> .....	19
<b>Distribution List</b> .....	21
<b>Report Documentation Page</b> .....	37

INTENTIONALLY LEFT BLANK.

## List of Figures

<u>Figure</u>		<u>Page</u>
1.	A Photograph of the Vertex Glass Fabric Used in This Project.....	3
2.	A Photograph of Samples of Cured, Prepregged, Vertex Glass (Right) and S-2 Glass (Left) .....	5
3.	Weibull Plot of the Tensile Test Data for 250-Yield Owens-Corning S-2 Glass Yarn .....	7
4.	Weibull Plot of the Tensile Test Data for 250-Yield Vertex Glass Yarn.....	8
5.	Weibull Plot of the Tensile Test Data for the Pseudo-250-Yield Vertex Glass Yarn (Three Combined 750-Yield Yarns).....	10
6.	Weibull Plot of the Tensile Test Data for 750-Yield S-2 Glass Yarn.....	11
7.	Test Specimens for Tensile, Flexure, Compression, and Short-Beam-Shear Tests Before Testing.....	13
8.	A Photograph of a 69-Ply Vertex Glass Laminate After Ballistic Testing With a 20-mm FSP.....	16

INTENTIONALLY LEFT BLANK.

# List of Tables

<u>Table</u>	<u>Page</u>
1. Tensile Test Results on S-2 and Vertex Glass Yarns.....	6
2. Required Composite Mechanical Tests.....	12
3. Results of Tensile, Flexure, Compression, and Short-Beam-Shear Tests on Vertex Glass Composites .....	13
4. Ballistic Test Results for 20-mm FSP vs. 69-Ply Vertex Glass Composite Panels .....	15
5. Ballistic Test Results of Vertex and RH Glass Composites.....	17

INTENTIONALLY LEFT BLANK.

# 1. Introduction

High-strength S-2 glass has become a very important material for structural and armor applications on military ground vehicles. This glass is significantly stronger and about seven times as expensive as the cheaper and more common fiberglass known as "E" glass. The S-2 glass has been used in the structural armor employed on the composite infantry fighting vehicle (CIFV) and more recently in the composite armored vehicle (CAV) advanced technology demonstrators. Future armored vehicles, such as Crusader, will also use substantial quantities of the S-2 glass. Its importance should increase significantly as the Army develops lighter armored vehicles that are more mobile and have better survivability features.

The only U.S. manufacturer of S-2 glass, Owens-Corning, has recently sold its S-2 glass business unit to a joint venture with a French company, Porcher.\* Owens-Corning has also sold their recently developed new glass fiber known as "Zentron," which is nominally stronger and cheaper than S-2 glass, to the same joint venture. Another French Company, Vetrotex-St. Gobain, makes a product known as RH glass that has been shown to have properties equal to those of S-2 glass [1]. However, Vetrotex-St. Gobain has been unwilling to market their RH glass in the United States. With the end of the Cold War, a Russian company, AO-Steklonit,† began to market an S-2 glass equivalent known as "Vertex HSG" outside of Russia. It has a chemical composition nominally identical to that of S-2 glass and, if properly made, should have strength and dielectric properties similar to those of S-2 or RH glass. The Vertex glass will nominally meet military requirements for type IV, class 1 S-2 glass fibers as specified in MIL-R-60346 (MR) [2]. This specification has recently been canceled, however. In any case, a more relevant question is how the glass fiber will perform in composite laminates, for which MIL-PRF-46197A [3] applies. Tests on composite panels made from the Vertex glass have not previously been conducted by an Army laboratory.

---

\* Advanced Glass Fiber Yarns, 2556 Wagener Road, Aken, SC 29801.

† AO-Steklonit, Baschkortostan, UL Tranvainaja, 15, Ufa 450040, Russia. A U.S. representative is Mr. Richard O'Meara, ROM Development Corporation, 136 Swineburne Row, Brick Market Place, Newport, RI 02840. Mr. O'Meara was instrumental in setting up the acquisition of the Vertex glass used in this project.


This report presents results of an evaluation of the mechanical and ballistic properties of the Russian Vertex glass that was conducted to determine how well it compares to the S-2 and RH glasses in polyester resin matrix composites. The results are important; if the Vertex glass tests out well and political conditions are favorable, it could easily become an economic competitor for S-2 glass, which would lead to lower prices. An additional source of material would be desirable in view of the reluctance of Vetrotex-St. Gobain to compete in the U.S. market. History has shown that economic competition is the most reliable means of driving prices down. If the glass were to test out poorly, this will also be useful intelligence information since the glass will probably be marketed worldwide. Many potential programs depend on the quality and availability of high-strength glass fibers.

The strength properties of glass fibers and composites made from them depend, in part, on the type and manner of application of protective coatings, known as sizings, that are applied to the fibers. The sizing also controls the binding of the matrix polymer to the glass in composites. AO-Steklonit claims that their C-96 sizing performs as well as the standard Owens-Corning type-463 sizing, and that they were actually developed by the same person. The sizing should enable enough matrix resin to glass fiber bonding for good mechanical strength and still allow the composite to perform well in ballistic tests, dissipating energy from the projectile by delaminating. A simple test of the sizing was also conducted to see how well the two sizings compared.

The quality of Russian material in general is widely regarded as highly uneven. The glass purchased is supposedly the best the Russians have ever marketed.

## **2. Material Acquisition**

A total of 300 yd of 24-oz/yd<sup>2</sup> glass fabric in a 5 × 5 plain weave pattern was ordered for this project. Figure 1 shows a photograph of a piece of the fabric. This fabric style is usually made using a yarn that is sufficiently thick so that 1 lb of the yarn is 250 yd long (hence a 250-yield

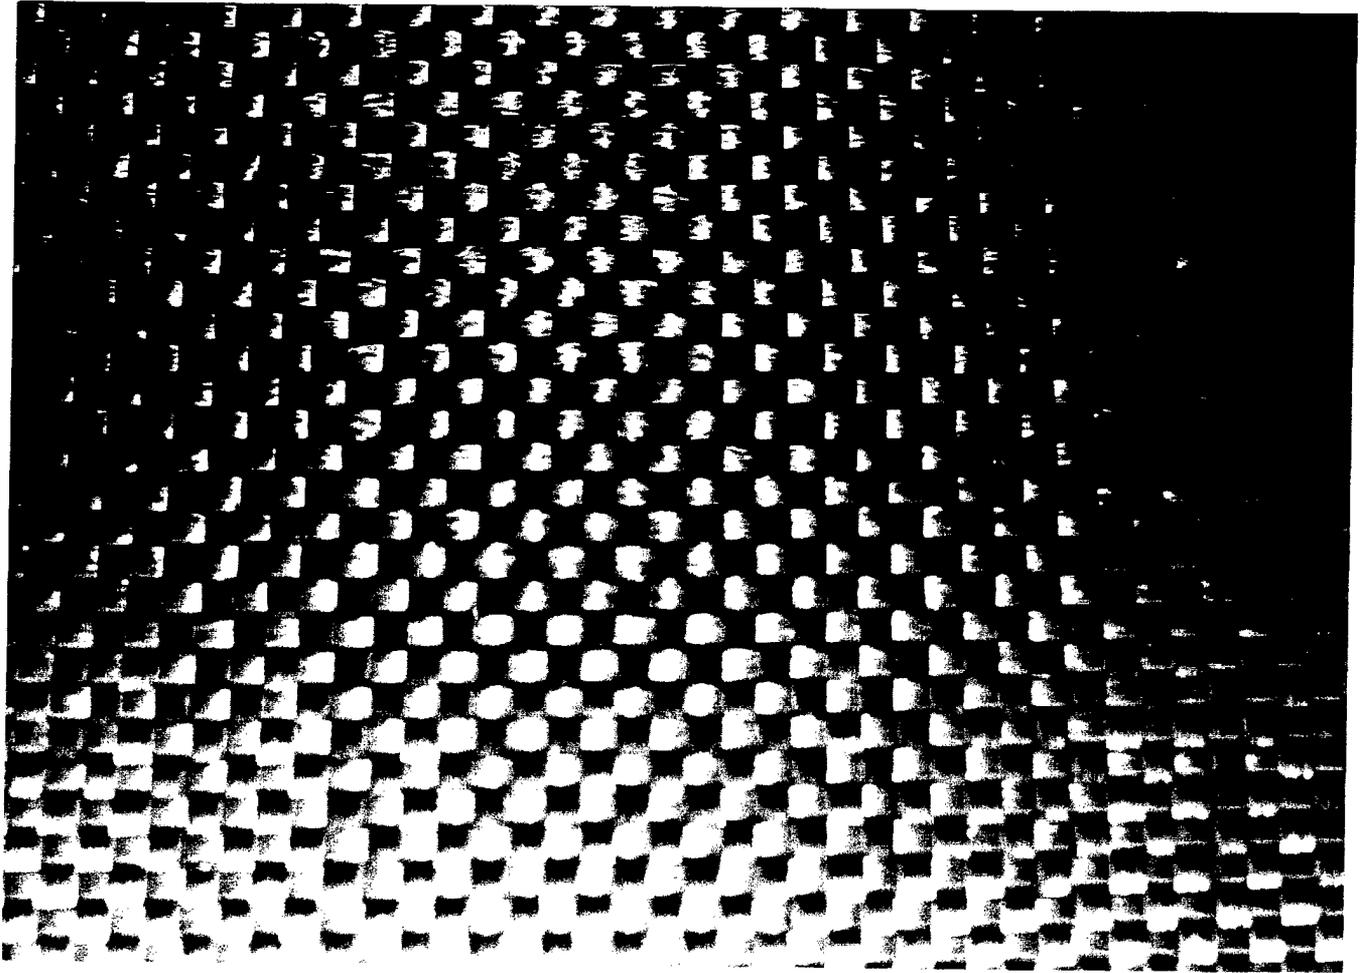

**Figure 1. A Photograph of the Vertex Glass Fabric Used in This Project.**

yarn). Sufficient 250-yield yarn was fabricated by AO-Steklonit for this project. However, the amount of sizing on the fiber was deemed too great for good mechanical and ballistic results to be obtained and the 250-yield yarn was not released to the weaver. After several months, it became clear that production of additional 250-yield yarn with the desired sizing by AO-Steklonit was not likely to happen in a time frame commensurate with the requirements for this project. Accordingly, a decision was made to use an alternate approach to making the fabric with three 750-yield yarns combined into a pseudo-250-yield yarn. This process involves more handling of the glass fibers, so there is the possibility of more handling damage to the fibers. Fabrics made from these fibers could have inferior strength properties. MIL-PRF-46197A [3]

allows for the use of these fabrics with the consent of the acquiring activity. Composite Materials, Inc.,\* did the weaving. A sample of the fabric weighed  $23.8 \pm 0.1$  oz/yd<sup>2</sup>, well within the 24 oz  $\pm 3\%$  allowed by the specification.

Approximately 300 yd of the Vertex glass fabric was prepregged by Cytec-Fiberite<sup>†</sup> using CYCOM 4102 polyester resin. This resin has been used extensively by the U.S. Army Research Laboratory (ARL) for the past 15 year. MIL-PRF-46197A [3] requires a number of tests on the prepreg. The volatile content, determined by weighing small pieces of prepreg before and after a 10-minute heating to 250° F in air, was found to be  $2.10 \pm 0.3$  weight-percent, within the 0–3% allowed by the specification. Similarly, the resin content of the prepreg was determined by weighing small pieces of prepreg before and after a 2-hour heating to 1,000° F in air and subtracting the volatile content. The resin content was found to be  $34.0 \pm 0.4$  weight-percent, in excellent agreement with the 34  $\pm 3\%$  allowed by the specification. The prepregger's certificate of compliance was accepted for the other tests of the resin required in the specification. Cured composites of the prepregged Vertex glass were a little darker than similar cured composites of prepregged S-2 glass, as the photograph of the samples in Figure 2 shows.


### 3. Chemical Composition and Sizing Chemistry

The Vertex and S-2 glasses have the same chemical compositions according to vendor's literature. An energy-dispersive x-ray analysis (EDAX) was performed on the two glasses to see if there were any significant differences between them. None was found for the major metallic elements magnesium, aluminum, and silicon at about 2, 8, and 25 weight-percent, respectively. The Vertex glass did show traces (1 weight-percent or less) of potassium, calcium, titanium, and iron that did not show up in the S-2 glass. These elements, particularly potassium and calcium,

---

\* Composite Materials, Inc., 19105 63rd Ave. NE, PO Box 25, Arlington, WA 98223.

† Cytec-Fiberite, 1440 N Kraemer Blvd., Anaheim, CA 92806.

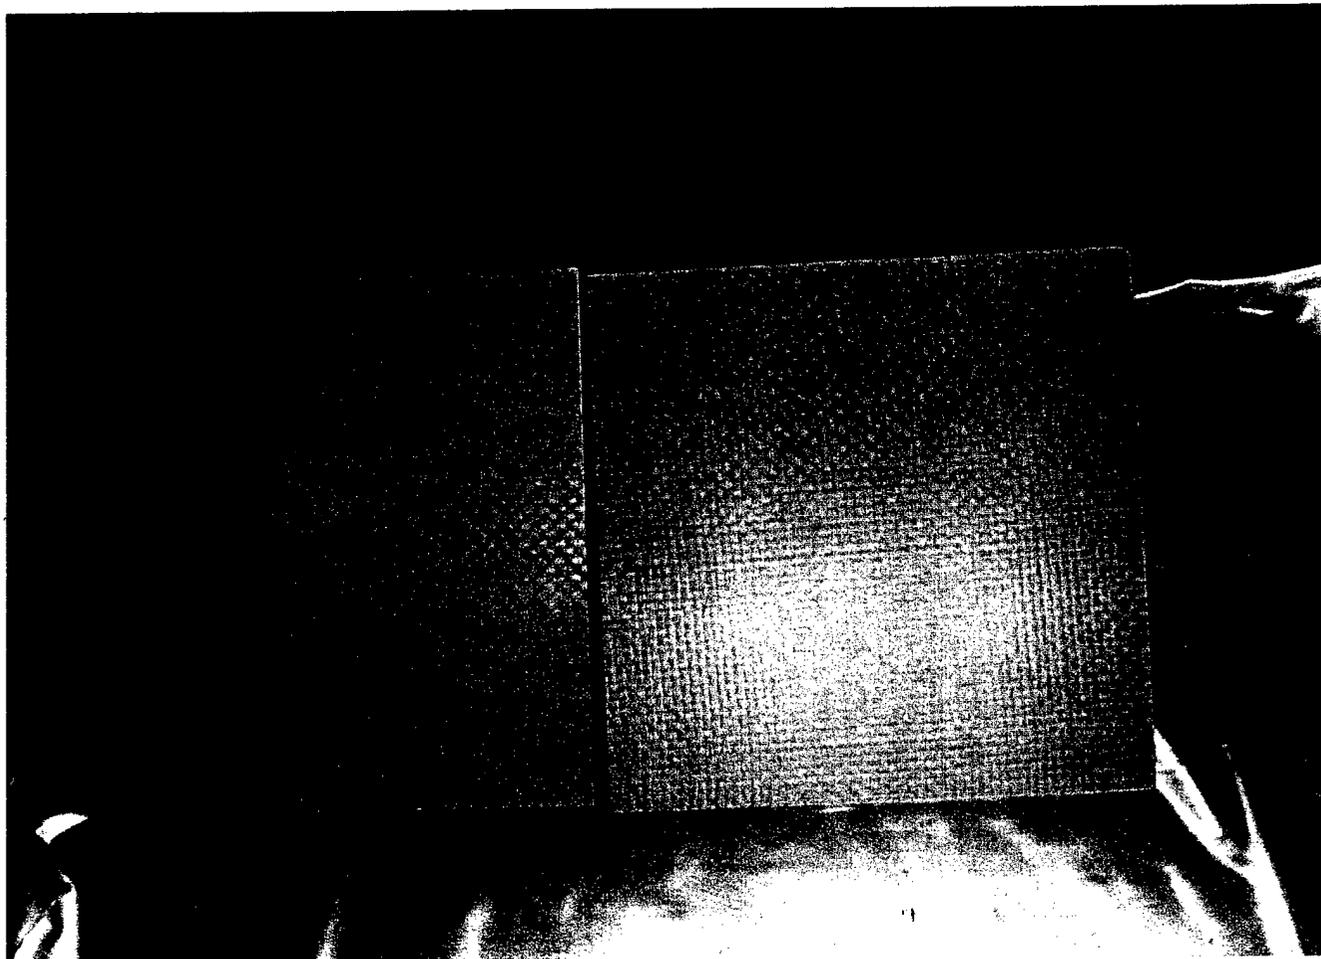

**Figure 2. A Photograph of Samples of Cured, Prepregged, Vertex Glass (Right) and S-2 Glass (Left).**

could lower the strength of the glass, although the tensile tests on the yarns would suggest that this was not a problem and the glass is just as strong as S-2 glass. The iron could account for the slight color difference noted in the composites.

Samples of both the Russian and domestic glass fibers were refluxed in methyl ethyl ketone to try to remove some of the sizing for infrared (IR) analysis. IR spectra of the extracts from the two fibers were similar but not identical. The spectra suggest that a bis-phenol-A epoxy is the major constituent of the sizings.

## 4. Tensile Tests on Glass Yarns

In order to obtain as direct a comparison between the S-2 and Vertex glass fibers as possible, tensile strength tests were run on several fiber yarns. Spools of 250-yield yarns of S-2 and Vertex glasses were obtained from Owens-Corning and Graphite Masters\* (through ROM Development Corporation), respectively. A spool of the pseudo-250-yield yarn (three 750-yield yarns combined) was also obtained from the fabric weaver, Composite Materials, Inc. Owens-Corning also provided a spool of 750-yield S-2 glass yarn that was tested to see how it compared to the 250-yield yarn.

The tensile tests were run on a standard Instron<sup>†</sup> testing machine. The gauge length of fiber was 10 in. The yarns were held in place with a special fixture. Fifty samples of each yarn were tested so that the spread in tensile strengths could be adequately explored. The results are presented in Table 1.

**Table 1. Tensile Test Results on S-2 and Vertex Glass Yarns**

Yarn	Maximum Load (lb)	Weibull Load (lb)	Weibull Slope (m)
250-Yield S-2	289 ±43	304	7.77
250-Yield Vertex	295 ±39	312	8.35
Pseudo-250-Yield Vertex	274 ±34	289	8.46
750-Yield S-2	102 ±9.3	106	13.03

In view of the spread in the data, it is clearly preferable to analyze the glass fiber tensile strength data using the methodology now generally applied to ceramic materials. This methodology is described in ASTM-C-1239-95 [4]. Weibull plots of the data for the 250-yield S-2 and Vertex glasses are shown in Figures 3 and 4. The test results for these two yarns are very

\* Graphite Masters, Inc., 3815 Medford St., Los Angeles, CA 90063-1900.

† Instron Corporation, 100 Royall Street, Canton, MA 02021.

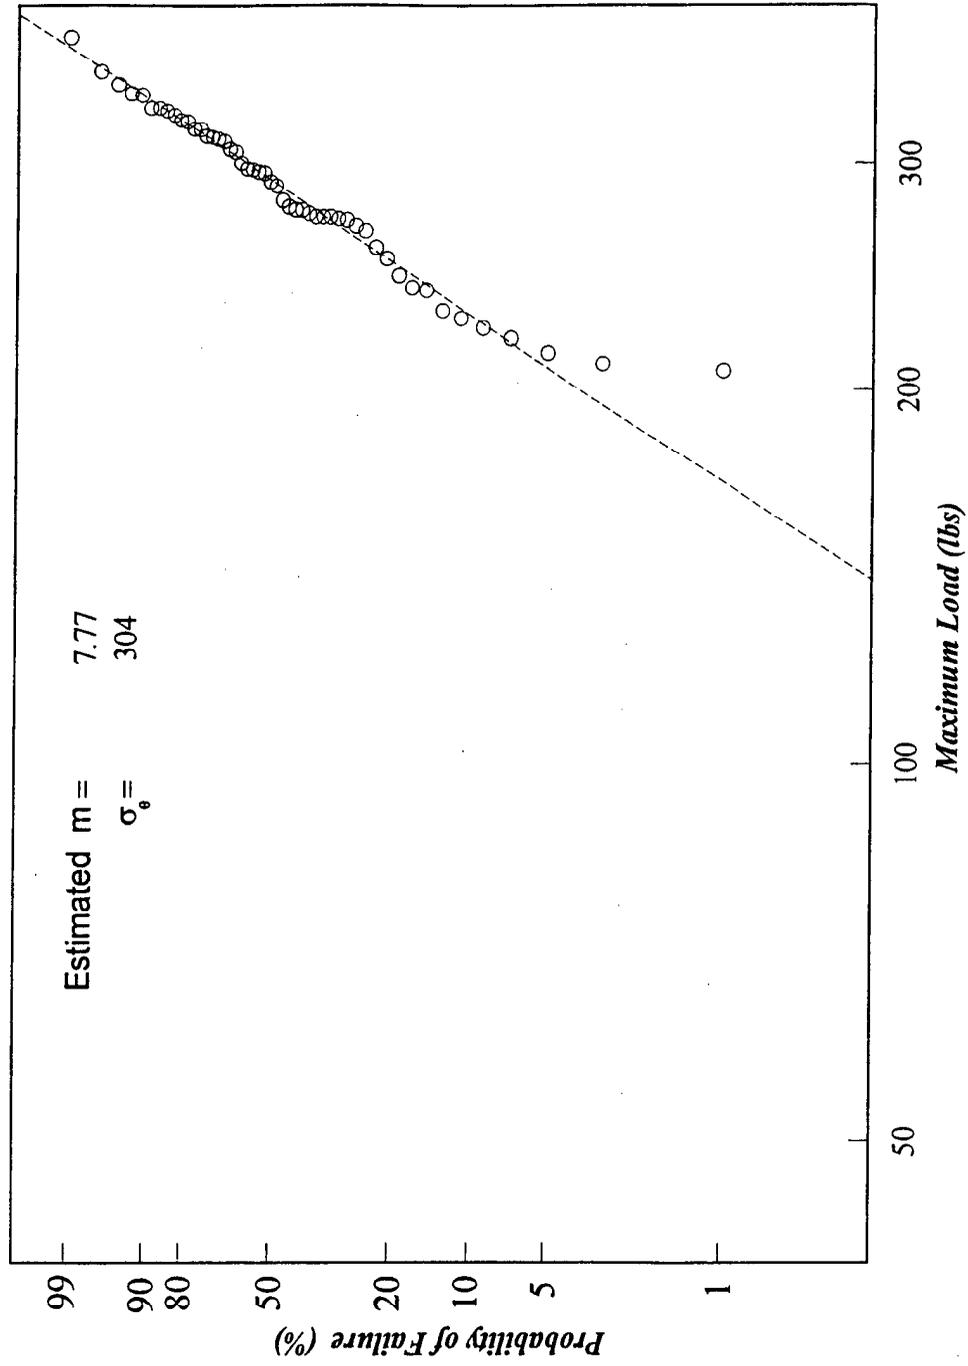


Figure 3. Weibull Plot of the Tensile Test Data for 250-Yield Owens-Corning S-2 Glass Yarn.

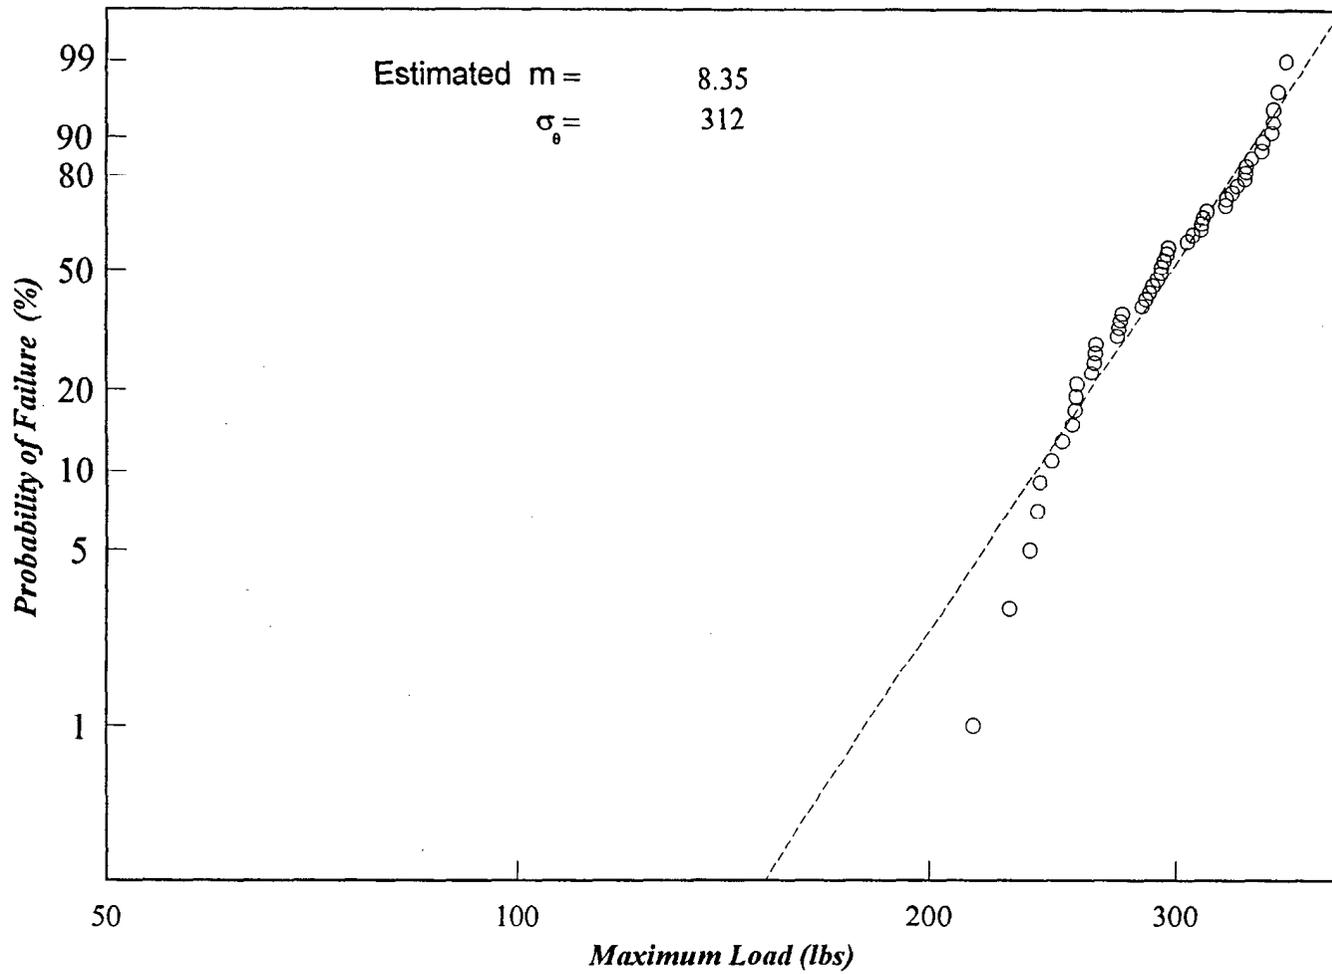


Figure 4. Weibull Plot of the Tensile Test Data for 250-Yield Vertex Glass Yarn.

similar, with the Vertex glass marginally stronger. The results are consistent with the proposition that a single flaw population with a distribution of defect sizes determines the strength of the material.

The lines in the Weibull plots represent a fit of the data to the formula


$$P_f = 1 - \exp - (\sigma/\sigma_\theta)^m,$$

where  $P_f$  is the probability of failure,  $\sigma$  is the strength (load in this case),  $\sigma_\theta$  is the characteristic strength, and  $m$  is an experimentally determined constant. In general, the higher the "m" value, the narrower the distribution of strength-limiting flaws. The characteristic strength (load),  $\sigma_\theta$ , is the load at which 63.2% of the samples have failed. The  $m$  values for the 250-yield S-2 and Vertex glasses are quite similar, as are the characteristic strengths, 304 lb and 312 lb, respectively.

The characteristic strength of the pseudo-250-yield Vertex glass is a little lower, at 289 lb, but the  $m$  value is similar to that for the 250-yield yarn (see Figure 5). This is consistent with the possibility that the additional handling required to combine the three 750-yield yarns introduces a few extra defects in the yarn. Also, having three 750-yield yarns wound together could result in a few stress concentration points that are not present in the larger 250-yield yarn.

The 7% lower tensile strength of the pseudo-250-yield fibers indicates that this method of making a 250-yield roving should be avoided if possible.

The  $m$  value for the 750-yield S-2 glass is considerably higher than that for the heavier yarns (see Figure 6). Note too that a 250-yield yarn is not exactly three times stronger than a 750-yield yarn.

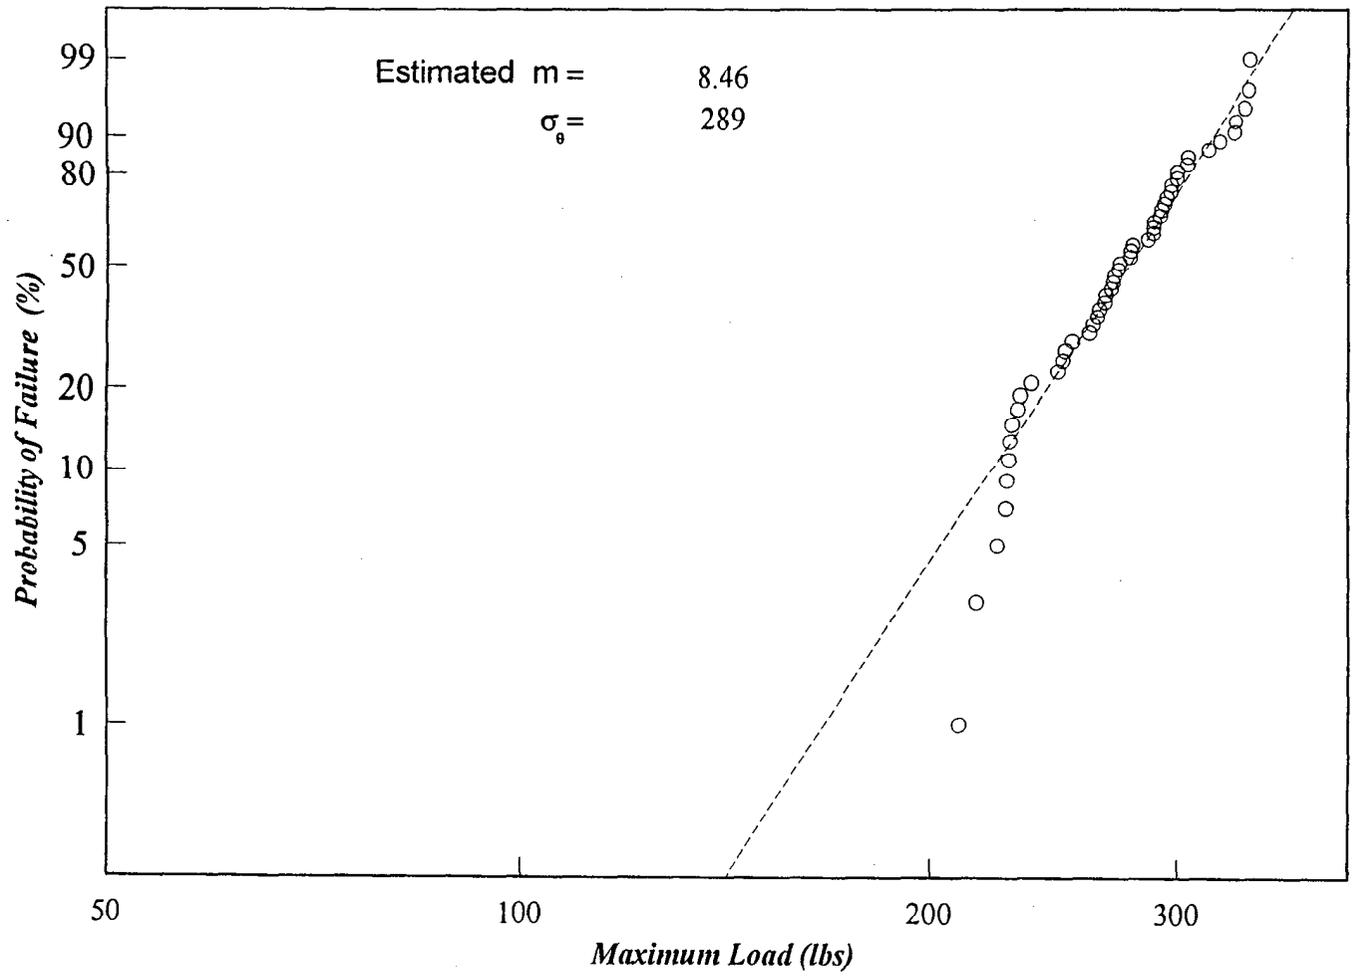

**Figure 5. Weibull Plot of the Tensile Test Data for the Pseudo-250-Yield Vertex Glass Yarn (Three Combined 750-Yield Yarns).**

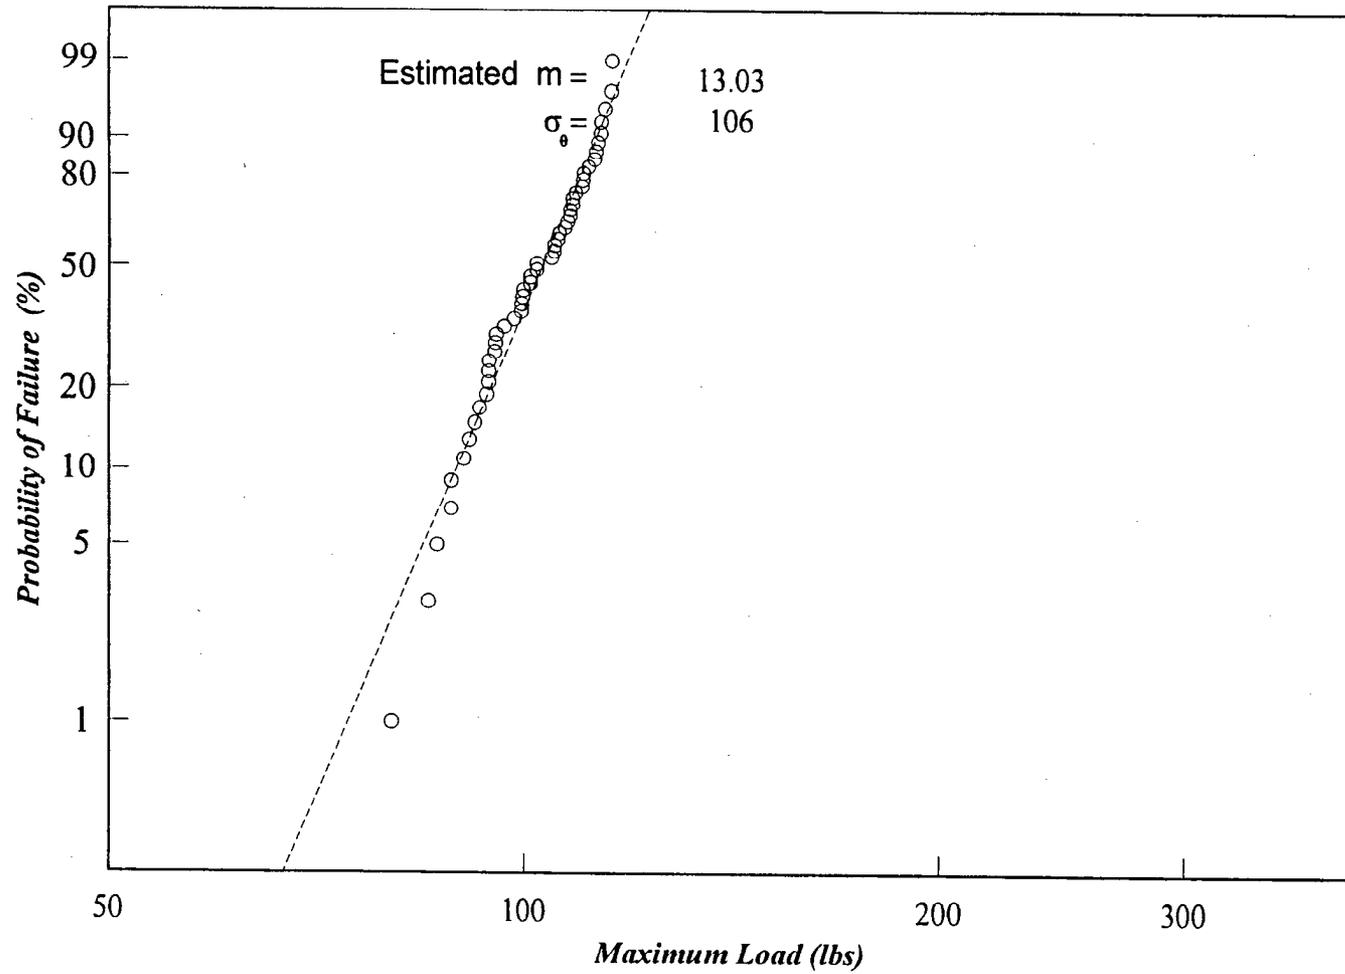


Figure 6. Weibull Plot of the Tensile Test Data for 750-Yield S-2 Glass Yarn.

## 5. Composite Mechanical Properties

MIL-PRF-46197A [3] and its predecessor MIL-L-46197 [5] specify a number of standard mechanical tests listed in Table 2 for glass-polyester laminates.


**Table 2. Required Composite Mechanical Tests**

Test	Standard
Tensile Properties	ASTM-D638 [6]
Flexural Properties	ASTM-D790 [7]
Compression Strength	ASTM-D695 [8]
Short-Beam-Shear Strength	ASTM-D2344 [9]

These tests are to be made on specimens cut from a quasi-isotropic panel fabricated with the ply sequence  $0^\circ$ ,  $-45^\circ$ ,  $+45^\circ$ ,  $90^\circ$ ,  $0^\circ$ ,  $90^\circ$ ,  $+45^\circ$ ,  $-45^\circ$ , and  $0^\circ$ , where the angle is measured with respect to the warp direction of the fabric (the long direction of the fabric roll). This arrangement minimizes effects arising from the test specimens being cut a little off the nominal  $0^\circ$  direction of the panel. A 2-ft<sup>2</sup> panel was fabricated using plies from different rolls of the prepregged Vertex glass fabric. The individual plies were cut from regions of the prepregged fabric with minimal weft distortion (regions in which the  $0^\circ$  and  $90^\circ$  rovings were as close to perpendicular as possible). Care was taken not to introduce additional distortion into the prepregged fabric. The test specimens were cut to the required shapes by Dess Machine and Manufacturing.\* The long axis of the test specimens was the  $0^\circ$  direction of the panel. Examples of the test specimens prior to testing are shown in Figure 7. A few compression test samples were also cut in-house as 0.5-in-wide  $\times$  0.215-in-thick  $\times$  3-in-long rectangular samples. The test results on the samples and the test requirements are shown in Table 3.

---

\* Dess Machine and Manufacturing, 5049 N DuPont Hwy., Dover, DE 19901.

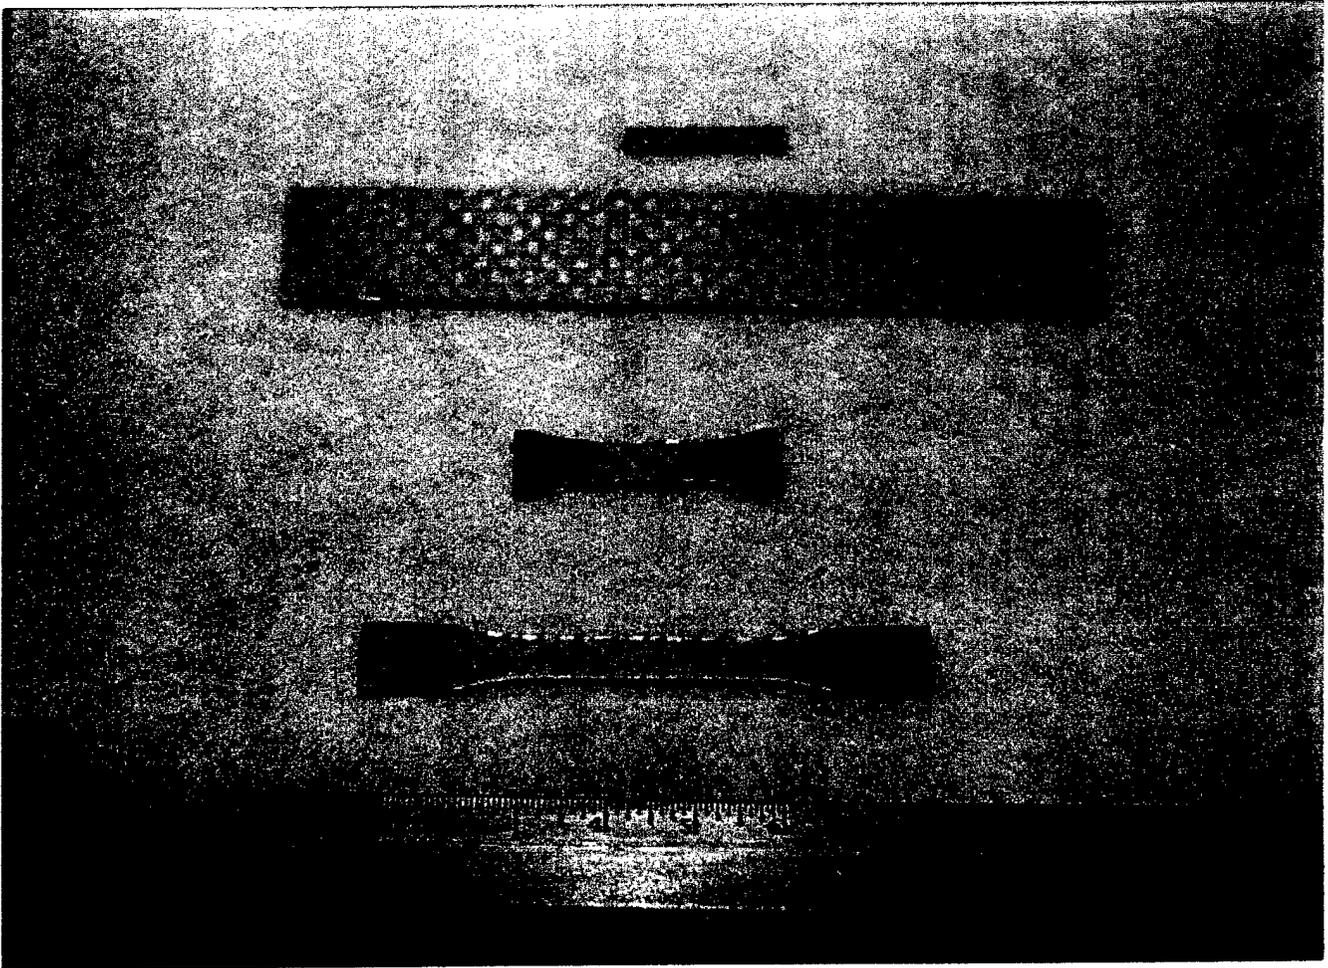

**Figure 7. Test Specimens for Tensile, Flexure, Compression, and Short-Beam-Shear Tests Before Testing.**

**Table 3. Results of Tensile, Flexure, Compression, and Short-Beam-Shear Tests on Vertex Glass Composites**

Test	Requirement	Vertex Glass
Tensile Strength (ksi [MPa])	43 [296]	40.4 ±2.8 [278 ±19]
Tensile Modulus (msi [GPa])	2.3 [15.8]	2.59 ±0.15 [17.8 ±1]
Compressive Strength (ksi [MPa])	20 [138]	17.6 ±0.9 [121 ±6.2]
Flexure Strength (ksi [MPa])	32 [221]	33.3 ±2.2 [230 ±15]
Flexure Modulus (msi [GPa])	2.5 [17.2]	2.55 ±0.13 [17.6 ±0.9]
Short-Beam-Shear Strength (ksi [MPa])	2.5 [17.2]	2.55 ±0.1 [17.6 ±0.7]

The tensile strength of the composite samples is 6% lower than the requirements of the specification. This is almost exactly the difference between the strength of the 250-yield and pseudo-250-yield rovings. It thus seems likely that a fabric made with the 250-yield roving would have passed this test. The tensile modulus just meets the requirements of the specification.

The flexure strength and modulus and the short-beam-shear strength just barely meet the requirements of the specification. Although these three properties depend strongly on the mechanical properties of the matrix resin and of the fiber-matrix interface, the test results would be higher if the fibers were stronger and a true 250-yield yarn had been used.

The compressive strength is well below the requirements, however. Several batches of samples were run to verify this result. A stronger and stiffer fiber would improve the compressive strength, but the difference between the 250-yield and pseudo-250-yield yarns is probably not large enough to bring the compressive strength up to the requirement of the specification. The results suggest that a modification in the sizing chemistry could improve all of the mechanical properties tested.

## 6. Ballistic Testing

For ballistic testing, MIL-PRF-46197A [3] only requires testing of a 69-ply laminate with an areal density of  $17 \text{ lb/ft}^2$  against a 20-mm fragment-simulating projectile (FSP). The velocity at which half of the shots completely penetrate the laminate ( $V_{50}$ ) should be above 2,370 ft/s to meet the specification. It is difficult to make 69-ply laminates, and the first two large panels ( $2 \text{ ft}^2$ ) made using the prepregged Vertex glass were failures since they exhibited serious internal delaminations. At the time, it was not clear if the failure was a consequence of poor fabrication technique (as now seems probable) or if it was due to an excessive incompatibility between the resin and the sizing. In view of this, a few additional ballistic tests seemed desirable, so tests

were also run on 10-ply panels (2.3 lb/ft<sup>2</sup>) with a 0.22-cal. FSP and against a 22-ply panel (5 lb/ft<sup>2</sup>) with a 0.30-cal. FSP.

All of the ballistic laminates tested were 1 ft × 1 ft and were shot once in the center. Laminates were clamped to a metal fixture during testing using a C-clamp at each corner. A 2024 aluminum witness plate 0.020 in thick was placed behind each laminate during ballistic tests to confirm partial and complete penetrations.


Ballistic testing of the 69-ply laminate vs. a 20-mm FSP must meet or exceed 725 m/s (2,380 ft/s). The 69-ply targets had an average areal density of 17.2 lb/ft<sup>2</sup>. The results of the tests are listed in Table 4. The material came within 2% of the minimum V<sub>50</sub> of 725 m/s at the required areal density. It is probable that the glass would have passed this test if the 7% stronger 250-yield roving had been used instead of the pseudo-250-yield roving. A photograph of a panel that has been ballistically tested with the 20-mm FSP is shown in Figure 8.

**Table 4. Ballistic Test Results for 20-mm FSP vs. 69-Ply Vertex Glass Composite Panels**

Shot No.	Velocity <sup>a</sup>	Penetration	Used for V <sub>50</sub> <sup>b</sup> Calculation
1	742	Complete	N
2	765	Complete	N
3	622	Complete	Y
4	724	Complete	N
5	675	Partial	N
6	695	Partial	Y
7	708	Partial	Y
8	733	Complete	N
9	719	Complete	Y
10	713	Complete	Y
11	695	Partial	Y

<sup>a</sup> Velocity Spread: 27 m/s (88 ft/s).

<sup>b</sup> V<sub>50</sub>: 709 m/s (2,326 ft/s) ± 11 m/s (36 ft/s).

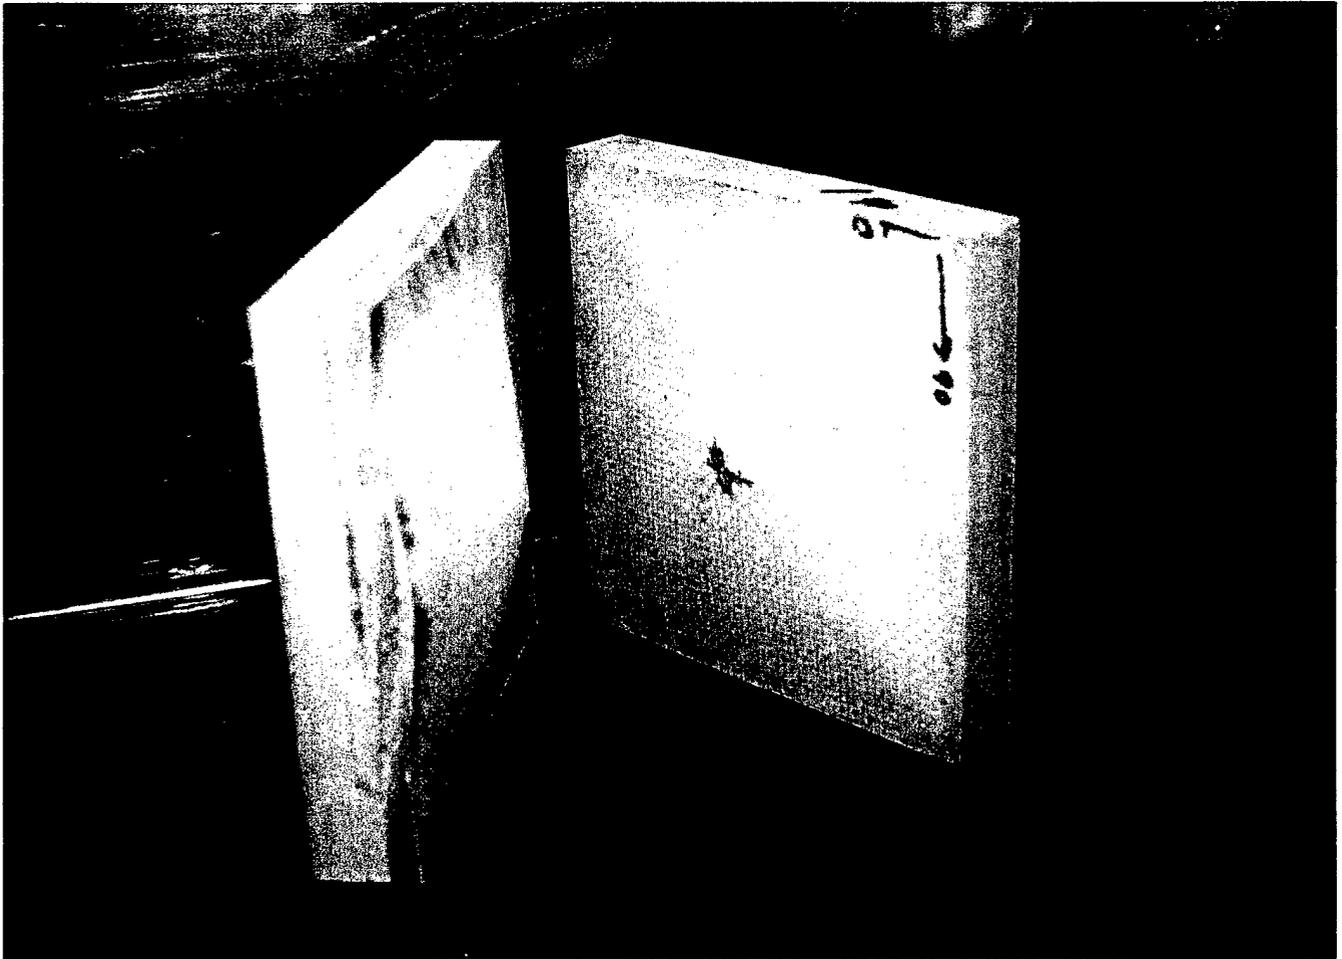

**Figure 8. A Photograph of a 69-Ply Vertex Glass Laminate After Ballistic Testing With a 20-mm FSP.**

In all cases, the ballistic test results for the Russian Vertex glass are not as good as those for the French RH glass reported in Haskell [1]. The  $V_{50}$  values are linear functions of the areal density of the armor and of the strength of the fibers. If the values are corrected to the areal densities of the RH glass and the 7% strength factor for 250-yield glass is taken into account, the Russian ballistic data come much closer to the RH data, as shown in the last column in Table 5.

The test results on all the thinner plates are presented in Table 5. The results of these tests are compared to results of previous ballistic tests on RH glass from Vetrotex-St. Gobain

**Table 5. Test Results of Vertex and RH Glass Composites**

Material	Areal Density (lb/ft <sup>2</sup> )	Projectile Caliber and Weight (Grains)	V <sub>50</sub> (m/s [ft/s])	Shots - Velocity Spread (m/s)	Normalized V <sub>50</sub> (m/s [ft/s])
Russian Vertex	2.31	0.22 (17)	472 [1,548]	4-15	494 [1,620]
RH	2.26	0.22 (17)	530 [1,740]	4-16	530 [1,740]
Russian	5.22	0.30 (44)	689 [2,260]	4-34	798 [2,617]
RH	5.65	0.30 (44)	792 [2,597]	2-38	792 [2,597]
Russian	17.19	20 mm	709 [2,326]	6-27	775 [2,541]
RH	17.55	20 mm	840 [2,755]	2-13	840 [2,755]

presented in Haskell [1]. The RH glass passed all of the tests (mechanical and ballistic) required by the specification.

## 7. Conclusions

The Russians have developed a glass fiber that comes close to meeting the requirements in MIL-PRF-96197A [3] for S-2 glass composites. The pseudo-250-yield roving used in the composites was about 7% weaker than a true 250-yield roving in direct tensile tests on the rovings. If a true 250-yield roving had been used, it is likely that the composites would have passed all of the mechanical and ballistic tests, except for compressive strength. Some modifications to the sizing are probably needed for composites of these fibers to pass this test.

Questions must also be raised about the value of MIL-PRF-96197A [3] as a specification for qualifying high-strength fibers. The specification was written for S-2 glass fibers with a special (epoxy) sizing and resin (polyester) that could be made into composites with particular mechanical and ballistic properties that were relevant to the CIFV. The same S-2 glass fiber with a different sizing (an amino silane) was used in the structural composites on the CAV in composites based on phenolic and epoxy resins. These composites have better mechanical properties than the polyester composites and are processed by cheaper vacuum-assisted resin-transfer molding techniques. New specifications for these for composites based on these resins and fibers with an amino silane sizing are needed. The new Zentron fiber also needs to be thoroughly evaluated, since it has the potential to replace S-2 glass as the high-strength glass of choice.

The future of the Russian Vertex high-strength glass is not clear. The plant where it is made has recently been temporarily closed for lack of demand. Programs in other countries could rapidly change this situation, however. The Vertex glass fiber is reasonably good and could be made even better.

## 8. References

1. Haskell, W. E. III. "High Strength Glass Second Source Qualification to Composite Armor Specification MIL-L-46197 (MR)." MTL-TR-92-30, April 1992.
2. U.S. Department of the Army. "Roving, Glass, Fibrous for Prepreg Tape and Roving, Filament Winding and Pultrusion Applications." MIL-R-60346 (MR), U.S. Army Materials Technology Laboratory, Watertown, MA, 1 June 1981 (cancelled 7 June 1997).
3. U.S. Department of the Army. "A Laminate, High Strength Glass Fiber Reinforced Polyester Resin." MIL-PRF-46197A, U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, 16 April 1997.
4. American Society for Testing and Materials. "Standard Practice for Reporting Uniaxial Strength Data and Estimating Weibull Distribution Parameters for Advanced Ceramics." ASTM-C-1239-95, Philadelphia, PA, 10 September 1997.
5. U.S. Department of the Army. "A Laminate, S-2 Glass Fiber Reinforced Polyester Resin." MIL-L-46197 (MR), U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, 16 April 1997.
6. American Society for Testing and Materials. "Standard Test Method for Tensile Properties of Plastics." ASTM-D638, West Conshohocken, PA, 10 October 1997.
7. American Society for Testing and Materials. "Standard Test Methods for Flexural Properties of Unreinforced and Reinforced Plastics and Insulating Materials." ASTM-D790, West Conshohocken, PA, 10 October 1997.
8. American Society for Testing and Materials. "Standard Test Method for Compressive Properties of Rigid Plastics." ASTM-D695, West Conshohocken, PA, 10 April 1996.
9. American Society for Testing and Materials. "Standard Test for Apparent Interlaminar Shear Strength of Parallel Fiber Composites by Short Beam Shear Method." ASTM-2344, 1 January 1984.

INTENTIONALLY LEFT BLANK.

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC DDA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218
1	HQDA DAMO FDQ D SCHMIDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460
1	OSD OUSD(A&T)/ODDDR&E(R) R J TREW THE PENTAGON WASHINGTON DC 20301-7100
1	DPTY CG FOR RDE HQ US ARMY MATERIEL CMD AMCRD MG CALDWELL 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001
1	INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN PO BOX 202797 AUSTIN TX 78720-2797
1	DARPA B KASPAR 3701 N FAIRFAX DR ARLINGTON VA 22203-1714
1	NAVAL SURFACE WARFARE CTR CODE B07 J PENNELLA 17320 DAHLGREN RD BLDG 1470 RM 1101 DAHLGREN VA 22448-5100
1	US MILITARY ACADEMY MATH SCI CTR OF EXCELLENCE DEPT OF MATHEMATICAL SCI MAJ M D PHILLIPS THAYER HALL WEST POINT NY 10996-1786

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	DIRECTOR US ARMY RESEARCH LAB AMSRL DD J J ROCCHIO 2800 POWDER MILL RD ADELPHI MD 20783-1145
1	DIRECTOR US ARMY RESEARCH LAB AMSRL CS AS (RECORDS MGMT) 2800 POWDER MILL RD ADELPHI MD 20783-1145
3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1145
	<u>ABERDEEN PROVING GROUND</u>
4	DIR USARL AMSRL CI LP (305)

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
1	DIR US ARMY RSRCH LAB AMSRL CP CA D SNIDER 2800 POWDER MILL RD ADELPHI MD 20783
1	CDR US ARMY ARDEC AMSTA AR FSE T GORA PICATINNY ARSENAL NJ 07806-5000
3	CDR US ARMY ARDEC AMSTA AR TD R PRICE V LINDNER C SPINELLI PICATINNY ARSENAL NJ 07806-5000
5	PM SADARM SFAE GCSS SD COL B ELLIS M DEVINE W DEMASSI J PRITCHARD S HROWNAK PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC SFAE FAS PM F MCLAUGHLIN PICATINNY ARSENAL NJ 07806-5000
6	CDR US ARMY ARDEC AMSTA AR CCH S MUSALLI P CHRISTIAN R CARR M LUCIANO T LOUCEIRO PICATINNY ARSENAL NJ 07806-5000
3	CDR US ARMY ARDEC AMSTA AR (2 CPS) E FENNELL PICATINNY ARSENAL NJ 07806-5000

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
1	CDR US ARMY ARDEC AMSTA AR CCH P J LUTZ PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC AMSTA AR FSF T C LIVECCHIA PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC AMSTA AR QAC T C C PATEL PICATINNY ARSENAL NJ 07806-5000
2	CDR US ARMY ARDEC AMSTA AR M D DEMELLA F DIORIO PICATINNY ARSENAL NJ 07806-5000
3	CDR US ARMY ARDEC AMSTA AR FSA A WARNASH B MACHAK C CHIEFA PICATINNY ARSENAL NJ 07806-5000
1	CDR WATERVLIET ARSENAL SMCWV QAE Q B VANINA BLDG 44 WATERVLIET NY 12189-4050
1	CDR WATERVLIET ARSENAL SMCWV SPM T MCCLOSKEY BLDG 253 WATERVLIET NY 12189-4050

NO. OF  
COPIES ORGANIZATION

8 DIR BENET LABORATORIES  
AMSTA AR CCB  
J KEANE  
J BATTAGLIA  
J VASILAKIS  
G FFIAR  
V MONTVORI  
J WRZOCHALSKI  
R HASENBEIN  
SMCAR CCB R S SOPOK  
WATERVLIET NY 12189

1 CDR WATERVLIET ARSENAL  
SMCWV QA QS  
K INSCO  
WATERVLIET NY 12189-4050

1 CDR US ARMY ARDEC  
PROD BASE MODERN ACTY  
AMSMC PBM K  
PICATINNY ARSENAL NJ  
07806-5000

1 CDR US ARMY BELVOIR RD&E CTR  
STRBE JBC  
FT BELVOIR VA 22060-5606

2 CDR US ARMY ARDEC  
AMSTA AR FSP G  
M SCHIKSNIS  
D CARLUCCI  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY COLD REGIONS RSRCH &  
ENGR LAB  
P DUTTA  
72 LYME RD  
HANOVER NH 03755

NO. OF  
COPIES ORGANIZATION

6 US ARMY RSRCH OFC  
A CROWSON  
J CHANDRA  
J PRATER  
R SINGLETON  
G ANDERSON  
K IYER  
PO BOX 12211  
RESEARCH TRIANGLE PARK NC  
27709-2211

5 PM US TMA  
SFAE GSSC TMA  
COL PAWLICKI  
K KIMKER  
E KOPACZ  
R ROESER  
B DORCY  
PICATINNY ARSENAL NJ  
07806-5000

1 PM TMA  
SFAE GSSC TMA SMD  
R KOWALSKI  
PICATINNY ARSENAL NJ  
07806-5000

2 PEO FIELD ARTILLERY SYSTEMS  
SFAE FAS PM  
H GOLDMAN  
T MCWILLIAMS  
PICATINNY ARSENAL NJ  
07806-5000

2 PM CRUSADER  
G DELCOCO  
J SHIELDS  
PICATINNY ARSENAL NJ  
07806-5000

2 NASA LANGLEY RSRCH CTR  
MS 266  
AMSRL VS  
W ELBER  
F BARTLETT JR  
HAMPTON VA 23681-0001

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
2	CDR DARPA J KELLY B WILCOX 3701 N FAIRFAX DR ARLINGTON VA 22203-1714
3	CDR DEPT OF THE AIR FORCE AIR FORCE RSRCH LAB S DONALDSON T BENSON TOLLE BLDG 654 WRIGHT PATTERSON AFB OH 45433-7750
1	NAVAL SURFC WARFARE CTR DAHLGREN DIV CODE G06 DAHLGREN VA 22448
1	NAVAL RSRCH LAB I WOLOCK CODE 6383 WASHINGTON DC 20375-5000
1	OFC OF NAVAL RSRCH MECH DIV CODE 1132SM Y RAJAPAKSE ARLINGTON VA 22217
1	NAVAL SURFC WARFARE CTR CRANE DIVISION M JOHNSON CODE 20H4 LOUISVILLE KY 40214-5245
1	DAVID TAYLOR RSRCH CTR SHIP STRUCTURES & PROT DEPT J CORRADO CODE 1702 BETHESDA MD 20084
2	DAVID TAYLOR RSRCH CTR R ROCKWELL W PHYLLAIER BETHESDA MD 20054-5000
1	DEFENSE NUCLEAR AGCY INNOVATIVE CONCEPTS DIV R ROHR 6801 TELEGRAPH RD ALEXANDRIA VA 22310-3398

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
1	EXPEDITIONARY WARFARE DIV N85 F SHOUP 2000 NAVY PENTAGON WASHINGTON DC 20350-2000
1	OFC OF NAVAL RSRCH D SIEGEL 351 800 N QUINCY ST ARLINGTON VA 22217-5660
1	NAVAL SURFC WARFARE CTR R HUBBARD G33 C DAHLGREN DIVISION DAHLGREN VA 2248-5000
1	NAVAL SURFC WARFARE CTR J H FRANCIS CODE G30 DAHLGREN VA 22448
2	NAVAL SURFC WARFARE CTR CODE G32 D WILSON R D COOPER DAHLGREN VA 22448
4	NAVAL SURFC WARFARE CTR CODE G33 J FRAYSSE E ROWE T DURAN L DE SIMONE DAHLGREN VA 22448
1	CDR NAVAL SEA SYST CMD D LIESE 2531 JEFFERSON DAVIS HIGHWAY ARLINGTON VA 22242-5160
1	NAVAL SURFC WARFARE CTR M E LACY CODE B02 17320 DAHLGREN RD DAHLGREN VA 22448
1	NAVAL SURFC WARFARE CTR TECH LIBRARY CODE 323 17320 DAHLGREN RD DAHLGREN VA 22448

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
4	DIR LAWRENCE LIVERMORE NATL LAB R CHRISTENSEN S DETERESA F MAGNESS M FINGER PO BOX 808 LIVERMORE CA 94550
1	LOS ALAMOS NATL LAB F ADDESSIO MS B216 PO BOX 1633 LOS ALAMOS NM 87545
1	LOS ALAMOS NATL LAB J REPPA MS F668 PO BOX 1663 LOS ALAMOS NM 87545
1	OAK RIDGE NATL LAB R M DAVIS PO BOX 2008 OAK RIDGE TN 37831-6195
3	UDLP 4800 EAST RIVER RD P JANKE MS170 T GIOVANETTI MS236 B VAN WYK MS389 MINNEAPOLIS MN 55421-1498
4	DIR SANDIA NATL LABORATORIES APPLIED MECHANICS DEPT DIV 8241 W KAWAHARA K PERANO D DAWSON P NIELAN PO BOX 969 LIVERMORE CA 94550-0096
1	BATTELLE C R HARGREAVES 505 KING AVE COLUMBUS OH 43201-2681

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	PACIFIC NORTHWEST LAB M SMITH PO BOX 999 RICHLAND WA 99352
1	LAWRENCE LIVERMORE NATL LAB M MURPHY PO BOX 808 L 282 LIVERMORE CA 94550
2	U OF DAYTON RSRCH INST R Y KIM A K ROY 300 COLLEGE PARK AVE DAYTON OH 45469-0168
1	AAI CORPORATION T G STASTNY PO BOX 126 HUNT VALLEY MD 21030-0126
1	J HEBERT PO BOX 1072 HUNT VALLEY MD 21030-0126
1	ARMTEC DEFENSE PRODUCTS S DYER 85 901 AVE 53 PO BOX 848 COACHELLA CA 92236
2	ADVNC D COMPST MATERIALS CORP P HOOD J RHODES 1525 S BUNCOMBE RD GREER SC 29651-9208
1	SAIC D DAKIN 2200 POWELL ST STE 1090 EMERYVILLE CA 94608
1	SAIC M PALMER SAIC 2109 AIR PARK RD S E ALBUQUERQUE NM 87106

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	SAIC R ACEBAL SAIC 1225 JOHNSON FERRY RD STE 100 MARIETTA GA 30068
1	SAIC G CHRYSSOMALLIS SAIC 3800 W 80TH STREET STE 1090 BLOOMINGTON MN 55431
4	ALLIANT TECHSYSTEMS INC C CANDLAND R BECKER L LEE R LONG D KAMDAR G KASSUELKE 600 2ND ST NE HOPKINS MN 55343-8367
1	AMOCO PERFORM PRODUCTS INC M MICHNO JR 4500 MCGINNIS FERRY RD ALPHARETTA GA 30202-3944
1	APPLIED COMPOSITES W GRISCH 333 NORTH SIXTH ST ST CHARLES IL 60174
1	BRUNSWICK DEFENSE T HARRIS STE 410 1745 JEFFERSON DAVIS HWY ARLINGTON VA 22202
1	PROJECTILE TECHNOLOGY INC 515 GILES ST HAVRE DE GRACE MD 21078
1	CSTM ANALYTICAL ENGR SYS INC A ALEXANDER 13000 TENSOR LANE NE FLINTSTONE MD 21530

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	NOESIS INC A BOUTZ 1110 N GLEBE RD STE 250 ARLINGTON VA 22201-4795
1	ARROW TECH ASSO 1233 SHELBURNE RD STE D 8 SOUTH BURLINGTON VT 05403-7700
5	AEROJET GEN CORP D PILLASCH T COULTER C FLYNN D RUBAREZUL M GREINER 1100 WEST HOLLYVALE ST AZUSA CA 91702-0296
7	CIVIL ENGR RSRCH FNDTN H BERNSTEIN C MAGNELL K ALMOND R BELLE M WILLETT E DELO B MATTES 1015 15TH ST NW STE 600 WASHINGTON DC 20005
1	NATL INST OF STAND & TECHLGY STRUCTURE & MECHANICS GRP POLYMER DIV POLYMERS RM A209 G MCKENNA GAITHERSBURG MD 20899
1	DUPONT COMPANY COMPOSITES ARAMID FIBERS S BORLESKE CHESNUT RUN PLAZA PO BOX 80702 WILMINGTON DE 19880-0702
1	GENERAL DYNAMICS LAND SYSTEMS DIV D BARTLE PO BOX 1901 WARREN MI 48090

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
3	HERCULES INC R BOE F POLICELLI J POESCH PO BOX 98 MAGNA UT 84044
3	HERCULES INC G KUEBELER J VERMEYCHUK B MANDERVILLE JR HERCULES PLAZA WILMINGTON DE 19894
1	HEXCEL M SHELENDICH 11555 DUBLIN BLVD PO BOX 2312 DUBLIN CA 94568-0705
5	INST FOR ADVANCED TECH T KIEHNE H FAIR P SULLIVAN W REINECKE I MCNAB 4030 2 W BRAKER LN AUSTIN TX 78759
1	INTEGRATED COMPOSITE TECH H PERKINSON JR PO BOX 397 YORK NEW SALEM PA 17371-0397
1	INTERFEROMETRICS INC R LARRIVA 8150 LEESBURG PIKE VIENNA VA 22100
1	AEROSPACE RES & DEV (ASRDD) CORP D ELDER PO BOX 49472 COLORADO SPRINGS CO 80949-9472

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	PM ADVANCED CONCEPTS LORAL VOUGHT SYSTEMS J TAYLOR PO BOX 650003 MS WT 21 DALLAS TX 76265-0003
2	LORAL VOUGHT SYSTEMS G JACKSON K COOK 1701 W MARSHALL DR GRAND PRAIRIE TX 75051
1	BRIGS CO J BACKOFEN 2668 PETERBOROUGH ST HERDON VA 22071-2443
1	SOUTHWEST RSRCH INST ENGR & MTRL SCIENCES DIV J RIEGEL 6220 CULEBRA RD PO DRAWER 28510 SAN ANTONIO TX 78228-0510
1	ZERNOW TECHNICAL SERVICES L ZERNOW 425 W BONITA AVE SUITE 208 SAN DIMAS CA 91773
1	R EICHELBERGER 409 W CATHERINE ST BEL AIR MD 21014-3613
1	DYNA EAST CORPORATION P C CHOU 3201 ARCH ST PHILADELPHIA PA 19104-2711
2	MARTIN MARIETTA CORP P DEWAR L SPONAR 230 EAST GODDARD BLVD KING OF PRUSSIA PA 19406

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	OLIN CORPORATION FLINCHBAUGH DIV E STEINER B STEWART PO BOX 127 RED LION PA 17356
1	OLIN CORPORATION L WHITMORE 10101 9TH ST NORTH ST PETERSBURG FL 33702
1	SPARTA INC J GLATZ 9455 TOWNE CTR DRIVE SAN DIEGO CA 92121-1964
2	UNITED DEFENSE LP P PARA G THOMAS 1107 COLEMAN AVE BOX 367 SAN JOSE CA 95103
1	MARINE CORPS SYST CMD PM GROUND WPNS COL R OWEN 2083 BARNETT AVE SUITE 315 QUANTICO VA 22134-5000
1	OFC OF NAVAL RES J KELLY 800 NORTH QUINCEY ST ARLINGTON VA 22217-5000
2	NAVAL SURFC WARFARE CTR CARDEROCK DIV R CRANE CODE 2802 C WILLIAMS CODE 6553 3A LEGGETT CIR ANNAPOLIS MD 21402

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
5	SIKORSKY H BUTTS T CARSTENSAN B KAY S GARBO J ADELMANN 6900 MAIN ST PO BOX 9729 STRATFORD CT 06601-1381
1	AMOCO POLYMERS J BANISAUKAS 4500 MCGINNIS FERRY RD ALPHARETTA GA 30005
1	HEXCEL T BITZER 11711 DUBLIN BLVD DUBLIN CA 94568
1	BOEING R BOHLMANN BOEING PO BOX 516 ,MC 5021322 ST LOUIS MO 63166-0516
1	NAVSEA OJRI G CAMPONESCHI 2351 JEFFERSON DAVIS HWY ARLINGTON VA 22242-5160
1	LOCKHEED MARTIN R FIELDS 1195 IRWIN CT WINTER SPRINGS FL 32708
1	USAF WL MLS OL A HAKIM 5225 BAILEY LOOP 243E MCCLELLAN AFB CA 55552
1	D HAMBRICK PRATT & WHITNEY 400 MAIN ST MS 114 37 EAST HARTFORD CT 06108

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	DOUGLAS PRODUCTS DIV BOEING L J HART SMITH 3855 LAKEWOOD BLVD D800-0019 LONG BEACH CA 90846-0001
1	MIT P LAGACE 77 MASS AVE CAMBRIDGE MA 01887
1	NASA LANGLEY J MASTERS MS 389 HAMPTON VA 23662-5225
2	CYTEC FIBERITE M LIN W WEB 1440 N KRAEMER BLVD ANAHEIM CA 92806
2	BOEING ROTORCRAFT P MINGURT P HANDEL 800 B PUTNAM BLVD WALLINGFORD PA 19086
2	FAA TECH CENTER D OPLINGER AAR 431 P SHYPRYKEVICH AAR 431 ATLANTIC CITY NJ 08405
1	NASA LANGLEY RC CC POE MS 188E NEWPORT NEWS VA 23608
1	LOCKHEED MARTIN S REEVE 8650 COBB DR D73 62 MZ 0648 MARIETTA GA 30063-0648
1	WL MLBC E SHINN 2941 PST STE 1 WRIGHT PAT AFB OH 45433-7750

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	D ROSE IIT RSRCH CTR 201 MILL ST ROME NY 13440-6916
1	MATERIALS SCIENCES CORP B W ROSEN 500 OFC CENTER DR STE 250 FORT WASHINGTON PA 19034
1	DOW UT S TIDRICK 15 STERLING DR WALLINGFORD CT 06492
4	NIST R PARNAS J DUNKERS M VANLANDINGHAM D HUNSTON POLYMERS DIVISION GAITHERSBURG MD 20899
2	NORTHROP GRUMMAN ENVIRONMENTAL PROGRAMS R OSTERMAN 8900 E WASHINGTON BLVD PICO RIVERA CA 90660
1	OAK RIDGE NATL LAB A WERESZCZAK BLDG 4515 MS 6069 PO BOX 2008 OAKRIDGE TN 37831-6064
1	CDR US ARMYARDEC T SACHAR INDUSTRIAL ECOLOGY CTR BLDG 172 PICATINNY ARSENAL NJ 07806-5000
1	CDR USA ATCOM AVIATION APPLIED TECH DIR J SCHUCK M DINNING K UNSWORTH FT EUSTIS VA

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	CDR US ARMY ARDEC AMSTA AR SRE D YEE PICATINNY ARSENAL NJ 07806-5000
7	CDR US ARMY ARDEC AMSTA AR CCH B B KONRAD E RIVERA G EUSTICE S PATEL G WAGNECZ R SAYER F CHANG BLDG 65 PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC AMSTA AR QAC T D RIGOGLIOSO BLDG 354 M829E3 IPT PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARMOR CTR ATZK MW S BLASKE FT KNOX KY 40121
1	CDR US ARMY ARDEC AMSTA AR CCH C S CHICO BLDG 65 PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY AVCOM AMC SMART WEAPONS MGMT OFC AMSMI SW D SAINSBURY REDSTONE ARSENAL AL 35898-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	COMMANDANT US ARMY FIELD ARTILLERY CTR ATFS CD LTC BUMGARNER FT SILL OK 73503-5600
1	DIR US ARMY AVCOM COMANCHE PRGM MGR OFC SFAE AV RAM TV D CALDWELL BLDG 5300 REDSTONE ARSENAL AL 35898
3	CDR US ARMY TACOM PM TACTICAL VEHICLES SFAE TVL SFAE TVM SFAE TVH WARREN MI 48397-5000
1	CDR US ARMY TACOM PM ABRAMS SFAE ASM AB WARREN MI 48397-5000
1	CDR US ARMY TACOM PM BFVS SFAE ASM BV WARREN MI 48397-5000
1	CDR US ARMY TACOM PM AFAS SFAE ASM AF WARREN MI 48397-500
1	CDR US ARMY TACOM PM SURV SYS FAE ASM SS T DEAN WARREN MI 48397-5000
3	CDR US ARMY SOLDIER SYST CMD NATICK RD&E CENTER SSCNC WST W NYKVIST T MERRILL S BEAUDOIN NATICK MA 01760-5018

NO. OF  
COPIES ORGANIZATION

1 GEORGIA TECH RSRCH INST  
GEORGIA INST OF TECHLGY  
P FRIEDERICH  
ATLANTA GA 30392

1 LOCKHEED MARTIN SKUNK WORKS  
D FORTNEY  
1011 LOCKHEED WAY  
PALMDALE CA 93599-2502

2 CDR NAVAL SURFC WARFARE CTR  
CADEROCK DIV  
R PETERSON CODE 2020  
M CRITCHFIELD CODE 1730 2  
BETHESDA MD 20084

2 UNITED DEFNS LTD PARTNERS  
PO BOX 359  
R BRYNSVOLD  
D MARTIN  
SANTA CLARA CA 95052-0359

2 UNITED DEFNS LTD PARTNERS  
328 W BROKAW RD  
MAIL DROP M53  
R BARRETT  
V HORVATICH  
SANTA CLARA CA 95052-0359

1 OFC OF THE SECRETARY OF DEFENSE  
JOINT CCD TEST FORCE  
OSD JCCD  
R WILLIAMS  
3909 HALLS FERRY RD  
VICKSBURG MS 29180-6199

2 GEN DYNAMICS LAND SYST  
D REES  
M PASIK  
PO BOX 2074  
WARREN MI 48090-2074

1 BATTELLE NW DOE PNNL  
T HALL  
BATTELLE BLVD  
MS K231  
RICHLAND WA 99352

NO. OF  
COPIES ORGANIZATION

2 BOEING DEFNS & SPACE GRP  
W HAMMOND  
J RUSSELL  
MS 4X55  
PO BOX 3707  
SEATTLE WA 98124-2207

1 GEN DYNAMICS LAND SYST  
MUSKEGON OPERATIONS  
W SOMMERS JR  
76 GETTY ST  
MUSKEGON MI 49442

1 CDR US ARMY ARDEC  
AMSTA AR FSP  
A P KISATSKY  
PICATINNY ARSENAL NJ  
07806-5000

1 DEPT OF THE ARMY OASARDA  
SARD SO  
DIRECTOR  
103 ARMY PENTAGON  
WASHINGTON DC 20310-0103

9 DIR  
US ARMY NATL GRND  
INTLLGNC CTR  
D LEITER  
S EITELMAN  
M HOLTUS  
M WOLFE  
S MINGLEDORF  
H C ARDLEIGH  
J A GASTON  
W P GSTATTENBAUER  
R WARNER  
220 SEVENTH ST NE  
CHARLOTTESVILLE VA 22091

1 DPTY ASSIST SECY FOR R&T  
SARD TT RM3EA79  
THE PENTAGON  
WASHINGTON DC 20301-7100

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
8	CDR US ARMY TACOM AMSTA TR R D THOMAS J BENNETT D HANSEN AMSTA JSK S GOODMAN J FLORENCE AMSTA TR D D OSTBERG L HINOJOSA B RAJU WARREN MI 48397-5000
3	DIR US ARMY CECOM NIGHT VSN & ELECT SENSORS DIRCTRT AMSEL RD NV CM CCD R MCLEAN A YINGST AMSEL RD NV VISP E JACOBS 10221 BURBECK RD FT BELVOIR VA 22060-5806
2	NORTHROP GRUMMAN CORP ELECT SENSORS & SYST DIV K RADFORD K F SCHOCH 1350 BEULAH RD PITTSBURGH PA 15235-5080
1	GRAPHITE MASTERS INC J WILLIS 3815 MEDFORD ST LOS ANGELES CA 90063-1900
1	ROM DEV CORP R OMEARA 136 SWINEBURNE ROW BRICK MARKET PLACE NEWPORT RI 02840
1	ADVANCED GLASS FIBER YARNS T COLLINS 281 SPRING RUN LN SUITE A DOWNINGTON PA 19335

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
1	COMPOSITE MATERIALS INC D SHORTT 19105 63 AVE NE PO BOX 25 ARLINGTON WA 98223
1	COMPOSITE MATERIALS INC R HOLLAND 11 JEWEL COURT ORINDA CA 94563
1	COMPOSITE MATERIALS INC C RILEY 14530 S ANSON AVE SANTA FE SPRINGS CA 90670
2	HEXCEL W SWANSON D HARTMAN 5794 W LAS POSITAS BLVD PLEASANTON CA 94588
2	COMPOSIX D BLAKE L DIXON 120 ONEILL DR HEBRUN OH 43025
2	SIMULA J COLTMAN R HUYETT 10016 S 51ST STREET PHOENIX AZ 85044
1	SIOUX MFG B KRIEL PO BOX 400 FT TOTTEN ND 58335
2	PROTECTION MATERIALS INC M MILLER F CRILLEY 14000 NW 58 CT MIAMI LAKES FL 33014
1	B&R SPECIALTIES INC J R KLINGER 9G CENTER STAATSBURG NY 12580

NO. OF COPIES   ORGANIZATION  
 2   FOSTER MILLER  
      J J GASSNER  
      M ROYLANCE  
      195 BEAR HILL RD  
      WALTHAM MA 02354-1196  
  
 2   TEXTRON SYSTEMS  
      R E SINGLER  
      M FAVALORO  
      201 LOWELL ST  
      WILMINGTON MA 08870-2941  
  
 1   CYTEC FIBERITE  
      R DUNNE  
      1300 REVOLUTION ST  
      HAVRE DE GRACE MD 21078  
  
 1   JPS GLASS  
      L CARTER  
      PO BOX 260  
      SLATER RD  
      SLATER SC 29683  
  
 1   PEO GCSS  
      SFAE GCSS W GSI M  
      D COCHRAN  
      WARREN MI 48397-5001  
  
 1   LTTC T J CUMMINGS  
      CHIEF USAIC  
      ATZB COM  
      FT BENNING GA 31905-5800  
  
 1   PM BFV  
      SFAE GCSS W BV  
      S DAVIS  
      11 MILE RD  
      WARREN MI 48307-5000  
  
 1   APM M1AZ  
      PM ABRAMS  
      MAJ K S FLYNN  
      6501 11 MILE RD  
      WARREN MI 48397-5000  
  
 1   M A GILLESPIE  
      OGARA HESS & EISENHARDT  
      9113 LESAINTE DR  
      FAIRFIELD OH 45014

NO. OF COPIES   ORGANIZATION  
 1   APM RDT&E  
      ABRAMS TANK SYSTEM  
      J A GODELL  
      SFAE GCSS W AB  
      WARREN MI 48307-5000  
  
 1   US ARMY ARDEC  
      AMSTA AR WEL F  
      C T GUERRIERE  
      INTELLIGENCE SPECIALIST  
      PICATINNY ARSENAL NJ 07806-5000  
  
 2   CDR US ARMY TACOM  
      AMSTA CS SF  
      H HUTCHINSON  
      F SCHWARZ  
      WARREN MI 48397-5000  
  
 1   CENTRAL INTELLIGENCE AGCY  
      OTI WDAG GT  
      PO BOX 1925  
      W L WALTMAN  
      WASHINGTON DC 20505  
  
 1   SURVIVABILITY LEAD  
      GENERAL DYNAMICS AMPHIBIOUS  
      SYSTEMS  
      G WALKER  
      991 ANNAPOLIS WAY  
      WOODBRIDGE VA 22191  
  
 1   PMGSI  
      HTI DIV  
      PM SURVIVABLE SYSTEMS  
      SFAE GCSS W GSI H  
      M G RYZYI  
      WARREN MI 48397-5000  
  
 1   UNITED DEFENSE LP  
      GROUND SYST DIV  
      M PEDRAZZI  
      1205 COLEMAN AVE  
      MAIL DROP N09  
      SANTA CLARA CA 95052

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
1	SYST MGER ABRAMS ATZK TS LTC J H NUNN BLDG 1002 RM 110 FT KNOX KY 40121
1	PM LIGHT TACTICAL VEHICLES AMSTA TR S MS 209 MAJ J B MILLS WARREN MI 48397-5000
1	UNITED DEFENSE LP GROUND SYST DIV A P LEE 1205 COLEMAN AVE MAIL DROP N11 SANTA CLARA CA 95052
1	GROUND SYST DIV M MACLEAN 1205 COLEMAN AVE MAIL DROP N06 SANTA CLARA CA 95052
1	PEO GCSS GROUND SYST INTEGRATION SFAE GCSS W GSI R J LABATILLE B229 WARREN MI 48397-5000
1	DIRCTRT OF COMBAT DEV C A KJORO 320 ENGINEER LOOP SUITE 141 FT LEONARD WOOD MO 65473-8929
1	CHIEF ABRAMS TESTING SFAE GCSS W AB QT T J KRASKIEWICZ WARREN MI 48397-5000
1	MARINE CORPS INTELLIGENCE ACTVTY D C KOSITZKE SUITE 250 3300 RUSSELL RD QUANTICO VA 22134-5011

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
2	MILLIKEN RSRCH CORP H KUHN M MACLEOD PO BOX 1926 SPARTANBURG SC 29303
1	CDR US ARMY MATERIEL COMMAND AMXMI INT 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001
1	CDR NATL GRD INTELLIGENCE CTR IANG TMT 220 SEVENTH ST NE CHARLOTTESVILLE VA 22902-5396
1	DIR DEFENSE INTELLIGENCE AGCY TA 5 K CRELLING WASHINGTON DC 20310
1	CDR US ARMY ARDEC AMSTA AR ASF PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY TACOM AMSTA SF WARREN MI 48397-5000
1	HQDA DAMI FIT NOLAN BLDG WASHINGTON DC 20310-1025
1	CONNEAUGHT INDUSTRIES INC J P SANTOS PO BOX 1425 COVENTRY RI 02816
2	BATTELLE NATICK OPERATIONS J P CONNORS B HALPIN 209 W CENTRAL ST SUITE 302 NATICK MA 01760

NO. OF COPIES ORGANIZATION

3 US ARMY SBCCOM  
SOLDIER SYST CTR  
J WARD  
J MACKIEWICZ  
W E HASKELL  
KANSAS ST  
NATICK MA 01760-5019

6 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL WM MB  
A ABRAHAMIAN  
M BERMAN  
A FRYDMAN  
T LI  
W MCINTOSH  
E SZYMANSKI  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145

3 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL SE L  
R WEINRAUB  
J DESMOND  
D WOODBURY  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145

2 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL SE R  
R CHASE  
H B WALLACE

2 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL SE DS  
R REYZER  
R ATKINSON  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145

NO. OF COPIES ORGANIZATION

ABERDEEN PROVING GROUND

1 DIR USAMSAA  
AMXSY TD  
P DIETZ

89 DIR USARL  
AMSRL CI  
W STUREK (1121)  
AMSRL CI S  
A MARK (309)  
AMSRL CS IO FI  
M ADAMSON  
AMSRL SL B  
J SMITH  
AMSRL SL BA  
AMSRL SL BE  
D BELY (328)  
R HENRY  
AMSRL SL BG  
A YOUNG  
AMSRL WM B  
A HORST (390A)  
E SCHMIDT (390A)  
AMSRL WM BE  
G WREN (390)  
C LEVERITT (390)  
D KOOKER (390A)  
AMSRL WM BC  
P PLOSTINS (390)  
D LYON (390)  
J NEWILL (390)  
S WILKERSON (390)  
AMSRL WM BD  
R FIFER  
B FORCH  
R PIESCE-RODRIGUEZ  
B RICE  
AMSRL WM  
D VIECHNICKI (4600)  
G HAGNAUER (4600)  
J MCCAULEY (4600)  
LTC TANNER

NO. OF  
COPIES ORGANIZATION

AMSRL WM MA  
R SHUFORD (4600)  
S MCKNIGHT (4600)  
L GHIORSE  
P MOY  
S NGYUEN  
G RODRIGUEZ  
P PATTERSON  
A TEETS  
D FLANAGAN  
P TOUCHET  
D HARRIS  
AMSRL WM MB  
W DRYSDALE (390)  
J BENDER (390)  
T BLANAS (4600)  
T BOGETTI (4600)  
R BOSSOLI (120)  
L BURTON (390)  
S CORNELISON (120)  
P DEHMER (4600)  
R DOOLEY (4600)  
B FINK (4600)  
G GAZONAS (390)  
S GHIORSE (4600)  
D GRANVILLE (4600)  
D HOPKINS (390)  
C HOPPEL (390)  
D HENRY (390)  
R KASTE (390)  
M LEADORE (390)  
R LIEB (390)  
E RIGAS (4600)  
J SANDS  
D SPAGNUOLO (4600)  
W SPURGEON (4600)  
J TZENG (390)  
AMRSL WM MC  
J BEATTY  
J SWAB  
AMSRL WM MD  
W ROY (4600)  
S WALSH  
AMSRL WM T  
B BURNS  
D DIETRICH (309)

NO. OF  
COPIES ORGANIZATION

AMSRL WM TA  
W GILlich (393)  
T HAVEL (393)  
J RUNYEON  
M BURKINS  
E HORWATH  
AMSRL WM TC  
R COATES (309)  
W DE ROSSET (309)  
AMSRL WM TD  
A GUPTA (309)  
T HADUCH  
T MOYNIHAN  
F SEITSINGER  
W BRUCHEY  
F GREGORY  
A RAJENDRAN  
D DANDEKAR  
AMSRL WM T  
A HORST  
AMSRL WM BA  
F BRANDON  
W D AMICO  
AMSRL WM BB  
J BORNSTEIN (120)  
AMSRL WM TE  
A ZIELINSKI (390)  
J POWELL (120)  
AMSRL WM BF  
J LACETERA (120)  
AMSRL SL BA  
R HENRY

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE September 1999	3. REPORT TYPE AND DATES COVERED Final, Oct 98 - Feb 99		
4. TITLE AND SUBTITLE Analysis of Russian "Vertex" High-Strength Glass Fiber			5. FUNDING NUMBERS 665709D650	
6. AUTHOR(S) William A. Spurgeon, Elias J. Rigas, and Matthew S. Burkins				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WM-MB Aberdeen Proving Ground, MD 21005-5069			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-2045	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES)			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) This report presents the results of mechanical and ballistic tests required in MIL-PRF-46197A (U.S. Department of the Army, "A Laminate, High Strength Glass Fiber Reinforced Polyester Resin," U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, 16 April 1997) on Russian Vertex high-strength glass that is supposed to be equivalent to domestic S-2 glass. The results of tensile tests of 250-yield yarns of both types of fibers were very similar, with the Vertex glass possibly as much as 2% stronger. For fabricating composites, however, a pseudo-250-yield yarn made by combining three 750-yield yarns was woven to make the fabrics used in the polyester resin composites for the mechanical and ballistic tests. This pseudo-250-yield yarn was about 7% weaker than the true 250-yield yarns. The tensile strength of the composites and the ballistic performance vs. a 20-mm fragment-simulating projectile (FSP) were both below the requirements of the specification, probably as a consequence of the use of this weaker yarn. The flexure and shear properties of the composites just met the specification, while the compressive strength was about 12% low. These results suggest that the sizing needs some fine-tuning to improve the performance of the Vertex glass fibers.				
14. SUBJECT TERMS high-strength glass fibers, high-strength fiberglass fibers, mechanical properties, ballistic properties, composites			15. NUMBER OF PAGES 42	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

INTENTIONALLY LEFT BLANK.

**USER EVALUATION SHEET/CHANGE OF ADDRESS**

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number/Author ARL-TR-2045 (Spurgeon) Date of Report September 1999

2. Date Report Received \_\_\_\_\_

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

CURRENT  
ADDRESS

\_\_\_\_\_  
Organization

\_\_\_\_\_  
Name

\_\_\_\_\_  
E-mail Name

\_\_\_\_\_  
Street or P.O. Box No.

\_\_\_\_\_  
City, State, Zip Code

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

OLD  
ADDRESS

\_\_\_\_\_  
Organization

\_\_\_\_\_  
Name

\_\_\_\_\_  
Street or P.O. Box No.

\_\_\_\_\_  
City, State, Zip Code

(Remove this sheet, fold as indicated, tape closed, and mail.)  
**(DO NOT STAPLE)**