

*ARMY RESEARCH LABORATORY*



# An Investigation of the Erosion Physics/Mechanisms of Current Army Systems (Point Studies)

by Paul J. Conroy, Paul Weinacht,  
and Michael J. Nusca

---

ARL-TR-2054

September 1999

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5066

---

---

ARL-TR-2054

September 1999

---

---

## An Investigation of the Erosion Physics/Mechanisms of Current Army Systems (Point Studies)

Paul J. Conroy, Paul Weinacht, and Michael J. Nusca  
Weapons and Materials Research Directorate, ARL

---

---

## Abstract

---

Future systems performance requirements have led to a heightened awareness of the erosion issue and to the development of erosion investigations in the U.S. Army and Navy. These investigations involve experimental and modeling efforts to understand the thermal, chemical, and mechanical contributions to erosion/wear. A description of the mechanistic erosion representation follows in this report. The calculation procedure is illustrated, including details of the mass transport scheme, gas surface interface, surface melt wipe model with dynamic gridding, and the equilibrium kinetics model, which utilizes the NASA Lewis thermochemical library.

The following cartridges are investigated: the M829A2 APFSDS in the M256 120-mm tank cannon and the M791-APDS-T and 616W-APFS (the “original” M919), both in the 25-mm Bushmaster cannon. The resulting mass lost per round for these systems compares well qualitatively with the experimental data, providing some support to the assumptions in the code. The primary conclusion is that carburization leading to iron carbide formation is an important contributing factor for much of the material lost from the steel barrel once it is exposed through cracks or chips in the surface coating.

# Table of Contents

	<u>Page</u>
<b>List of Figures</b> .....	v
<b>1. Introduction</b> .....	1
<b>2. Mechanistic Description</b> .....	2
<b>3. Ablation-Conduction Model and Computational Approach</b> .....	4
<b>4. Heat Transport to Surface</b> .....	6
<b>5. Multicomponent Diffusion and Mass Transport Scheme</b> .....	8
<b>6. Equilibrium Kinetics</b> .....	10
<b>7. Surface Description</b> .....	13
<b>8. Application to Point Studies</b> .....	15
<b>9. Concluding Remarks</b> .....	23
<b>10. References</b> .....	25
<b>Appendix A: Blake Thermochemical Input Decks for Propellants Used in This Study</b> .....	29
<b>Appendix B: XKTC Interior Ballistic Input Decks Used in This Study</b> ..	33
<b>Distribution List</b> .....	39
<b>Report Documentation Page</b> .....	47

INTENTIONALLY LEFT BLANK.

## List of Figures

<u>Figure</u>	<u>Page</u>
1. Conceptual Erosion Description .....	4
2. Gun Tube Surface Temperatures at Three Axial Locations for a Single Firing of an M829A2 Cartridge in an M256 Tank Cannon Without Surface Roughness Augmentation to the Heat Transport .....	16
3. Average Erosion Depth per Round at the Bottom of a Chrome Chip in an M256 Tank Cannon Firing an M829A2 Cartridge Without Surface Roughness Augmentation to the Heat Transport .....	16
4. Gun Tube Surface Temperatures at Three Axial Locations and for a Single Firing of an M829A2 Cartridge in an M256 Tank Cannon With Surface Roughness Augmentation to the Heat Transport .....	17
5. Average Erosion Depth per Round at the Bottom of a Chrome Chip for an M256 Cannon Firing an M829A2 Cartridge With Surface Roughness Augmentation to the Heat Transport .....	18
6. Surface Temperature and Carbon Diffusion Depth at the Bottom of a Chrome Chip in an M256 Tank Cannon Firing an M829A2 Cartridge, Presented at 1,778 mm From the Rear Face of the Tube Without Surface Roughness Augmentation to the Heat Transport .....	18
7. Surface Temperature, Carbon Diffusion Depth, and Surface Melting Depth in a Chrome Chip of an M256 Tank Cannon, Presented 1,350 mm From the Rear Face of the Tube for an M829A2 Cartridge With Surface Roughness Augmentation to the Heat Transport .....	19
8. Surface Temperatures for Three Axial Locations of an M791 Cartridge Fired in an M242, 25-mm Bushmaster Cannon .....	20
9. Computed and Experimental Erosion per Round for an M791 Cartridge Fired in a 25-mm Bushmaster Cannon .....	21
10. Surface Temperatures for Three Axial Locations for a 616W (Original M919 APFSDS) Cartridge Fired in an M242 Bushmaster Cannon .....	22

11.	Computed and Experimental Erosion per Round for a 616W (Original M919 APFSDS) Cartridge Fired in an M242, 25-mm Bushmaster Cannon . . . . .	22
-----	---	----

# 1. Introduction

System performance demands are forcing changes in gun tubes in the areas of pressure limits, length, firing rate, and erosion resistance. This has created a resurgence of the interest in gun tube erosion and the associated mechanisms. Historically, the propellant adiabatic flame temperature was used as an indicator of the erosivity of a propellant. Unfortunately, flame temperature is not the only factor [1, 2] influencing the erosion process, which includes mechanical abrasion, pyrolysis, melting, and spalling. Also, once the erosion rate was predicted using the flame temperature correlations, understanding what could be done to mitigate the erosion was left a mystery with the exception of the obvious solution of applying surface coatings or ablatives.

The effectiveness of surface coatings depends upon the ability of the coating to block the thermal and chemical attack of the propellant combustion products with the gun bore surface. Permanent tube coatings, such as chromium, have been successfully implemented in both artillery and direct-fire systems. One concern for the use of chromium as a coating is that the hexavalent state used in electroplating is environmentally undesirable to the level that one day it may be eliminated as a design option. Many other coatings, such as functionally gradient coatings and ceramic coatings, although unsuccessful in the past, are continuously being examined as possible candidates [3]. Also being examined are refractory metals, such as rhenium, molybdenum, niobium, and tantalum, of which tantalum appears to be the optimal choice [4]. Much effort is being placed in coating process technology for these materials by various elements of the Army and Navy. Successful implementation of propelling charge additives, such as talc,  $\text{TiO}_2$ , waxes, greases, and combinations thereof, that deposit on the tube or in the boundary layer and act as coatings are usually Edisonian in nature and without knowledge of the mechanisms of how or why one additive works better than another.

Attempts to model erosion using first principles have been and are currently being made [5–8], although it is believed that significant additional work is still required to understand the fundamental physics involved. In this report the possible mechanisms will be elaborated upon and then applied to specific systems.

## 2. Mechanistic Description

A modular treatment of the contributing factors to erosion consisting of three fully coupled portions, to include thermal ablation with an iterative solution for the surface regression; independent heat and multicomponent species mass transport to the surface; and full equilibrium thermochemistry was utilized. The contributions due to mechanical wear and abrasion, however, are not included. A surface control volume treatment ensures conservation of mass. The gas-phase properties in the core flow of the gun tube from the XKTC [9] or NGEN [10] interior ballistic codes are used in the calculations, as well as species data from IBBLAKE [11–13] or NGEN. The thermochemistry calculation incorporates the NASA Lewis [14] thermochemical database.

Primary features include:

- Variable surface thermo-physical properties: specific heat  $C_p$  and conductivity  $k$ .
- Surface material phase change from base-centered cubic (BCC) to face-centered cubic (FCC). The material replenishment section recognizes the surface temperature and the correct phase. There are no phase change hysteresis nor are there two-phase (BCC+FCC) regions.
- A user-defined “freeze-out” temperature to enable the surface chemistry portion.
- A user selection for two-phase control volume temperature: (1) Surface temperature and (2) a mixture control volume temperature with both gas- and solid-phase contributions.
- User-defined surface materials, both reactant and product species.
- A user-defined surface coating - if any.

- No hardwired inputs. All primary inputs are user defined.

The following assumptions are in the model:

- One-dimensional (1-D) heat conduction.
- Subsurface 1-D diffusion only of carbon.
- All surface liquids and gas products are removed.
- No feedback to the interior ballistics calculation in the core flow.
- Released chemical energy treated as a source term.
- Species are chemically frozen from core flow to the wall.

The description, shown conceptually in Figure 1, enables the surface to heat convectively until the user-defined freeze-out temperature is overcome. At this point, the control volume at the surface is defined and supplied with species from the mass transport routines. Surface reactions are then permitted to occur, which release additional energy into the system as a surface source term and produce various gas, solid, or liquid products. The reaction products can be either unvaried, as some solid materials, or be removed from the area as liquids or gases. The latter case results in pyrolysis or ablation. As the surface regresses, the solids are refreshed accordingly with fresh steel.

Preliminary calculations must be made using interior ballistic codes to provide the core flow state variables of temperature and pressure as well as the velocity and the species concentrations. These outputs are then used as input along with a user-defined input file to the calculation.

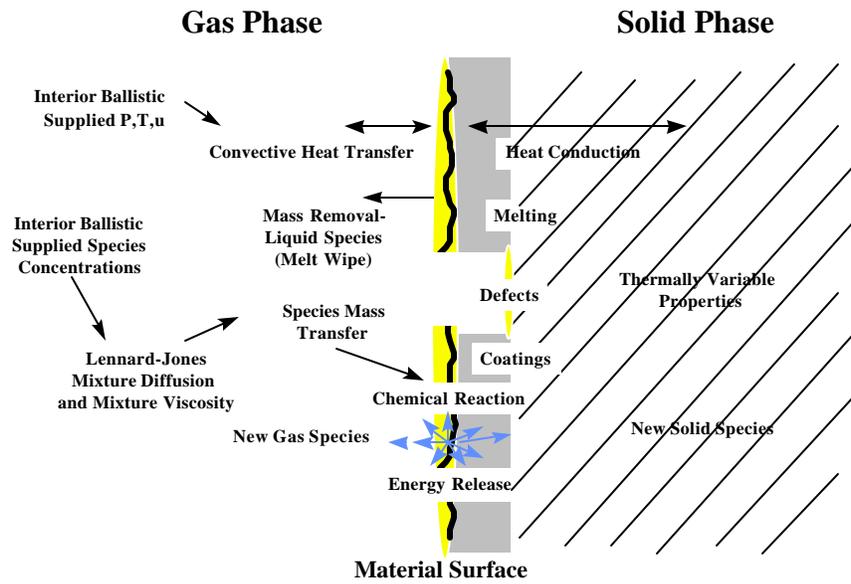


Figure 1. Conceptual Erosion Description.

### 3. Ablation-Conduction Model and Computational Approach

The in-depth temperature response,  $T(r)$ , of the unablated (solid) material is modeled using the 1-D heat conduction equation as follows:

$$DC \frac{MT}{P} \cdot \frac{1}{r} \frac{M}{Mr} \left( r \frac{dT}{Mr} \right). \quad (1)$$

By setting  $\beta = 0$  or  $\beta = 1$ , the planar or axisymmetric form of the governing equation can be obtained. In this form of the equation, the relevant material properties are density,  $D$ , specific heat,  $C_p$ , and conductivity,  $k$ . The conductivity and specific heat may vary but must remain continuous.

The surface (heat) energy balance, while gross melting is not occurring, includes the convective heat input to the surface along with the possible contribution due to the surface reaction, shown in equation 2. This source term is balanced with the energy conducted through the material.

$$h(T_{\text{gas}} - T_{\text{wall}}) + k \frac{dT}{dx} = \text{source} \quad (2)$$

However, when the system is melting, the energy balance also includes the fixed-surface temperature condition and the unknown surface location. The surface temperature cannot rise beyond the specified melting value because any additional energy is applied to the latent heat of formation of the molten material, as shown in equations 3 and 4, where  $S_{\text{surf}}$  is the surface location:

$$T_{\text{wall}} = T_{\text{melt}} \quad (3)$$

$$DL \frac{M_{S_{\text{surf}}}}{M_t} + h(T_{\text{gas}} - T_{\text{wall}}) = k \frac{dT}{dx} + \text{Source} \quad (4)$$

To provide closure for the in-depth temperature response of the gun tube, a convective boundary condition is applied to the outer surface of the gun tube.

$$h_{\text{amb}}(T_{\text{outer\&wall}} - T_4) = k \frac{dT}{dx} \quad (5)$$

The governing equations and boundary conditions are solved using a Crank-Nicholson finite-difference technique. Prior to the onset of melting, the governing equations and boundary conditions are linear and solutions are obtained in a direct (noniterative) fashion. During the melting process, the equations become nonlinear since the dimensions of the computational domain are coupled with the regression rate. An iterative approach is utilized during melting to appropriately address the nonlinearity.

Because the boundary of the computational domain moves during the erosion event, a transformed version of the governing equation is employed. This allows the equations to be solved in a fixed computational space even though the physical boundary is moving. A generalized transformation between

the computational coordinate,  $\xi$ , and the physical coordinate,  $r$ , is utilized. The transformed equations are shown below.

$$\begin{aligned}
 DC_p \left( \frac{MT}{Mt} \right)_{\xi} &= \frac{1}{r} \frac{M}{M_{\xi}} \left( r k \frac{MT}{M_{\xi}} \right)_{\xi} \\
 &= \frac{r_{\xi}}{r_{\xi}} / \frac{Mr}{Mt} \frac{M_{\xi}}{Mr} \\
 &= \frac{1}{r_{\xi}} / \frac{M_{\xi}}{Mr}
 \end{aligned} \tag{6}$$

In this form, the nonlinear nature of the governing equation produced by the moving boundary is evident because the metric terms,  $\xi_r$  and  $\xi_{\xi}$ , are not constant and are dependent on the erosion rate when the grid is moving.

This methodology compares very well to the semianalytical solutions of Landau [15] in test cases [7].

## 4. Heat Transport to Surface

The heat flux to the surface is provided through convective heat transport and energy release as shown [16, 17].

$$Q_w = 0.037 \frac{\mu}{P} \text{Re}^{0.8} \frac{C_f}{C_{f_i}} C_p (T_g - T_w), \tag{7}$$

where  $\frac{C_f}{C_{f_i}}$  is the compressible skin friction ratio,  $\text{Re}^*$  is the compressible Reynolds number,  $\mu^*$  is the viscosity,  $P$  is a pressure normalized length scale from the entrance region,  $C_p$  is the specific heat of the gases, and  $T_g$  and  $T_w$  are the gas temperature and wall temperature, respectively.

This heat flux reduces to the following boundary condition imposed upon the inner wall:

$$k \frac{dT}{dr} = h_{\text{conv}} (T_g - T_w) \quad (8)$$

This boundary condition has been modified for erosion studies with the incorporation of surface defects primarily in coated gun tubes. This has been done by using the ratio of the Stanton numbers (Nusselt/Reynolds/Prandtl) for smooth and rough tubes, defined by the depth of the pit. The frictional factor may be computed by solving Colbrook's function [18], as shown in equation 9.

$$f^{1/2} = -2 \log \left( \frac{e/D}{3.7} + \frac{2.51}{\sqrt{f} Re_D} \right), \quad (9)$$

with  $e$  the depth of the defect,  $D$  the bore diameter, and  $Re_D$  the Reynolds number. The computation of the Stanton number for rough and smooth surfaces can be performed through the following set of equations and instructions in the *Handbook of Single-Phase Heat Transfer* [19].

$$B(e^+) = \sqrt{\frac{2}{f}} + 2.5 \ln \left( \frac{2e^+}{D} + 3.75 \right), \quad (10)$$

where  $f$  is the friction factor and  $e^+$  is defined as

$$e^+ = \frac{e}{D} Re \sqrt{\frac{f}{2}}. \quad (11)$$

The following transcendental correlation provides the Stanton number.

$$g(e)Pr^n \cdot \frac{f/(2St) + 1}{\sqrt{f/2}} B(e), \quad (12)$$

which when reduced results in the following relationship:

$$St = \frac{f/2}{1 + \sqrt{f/2} (g(e)Pr^n + B(e))}. \quad (13)$$

The ratio of the smooth Stanton number to that of the current “rough” Stanton number using the erosion depth as the dimension of the defect “e” provides some measure to the augmentation due to the flow disturbances of a sand grain type roughness.

## 5. Multicomponent Diffusion and Mass Transport Scheme

Mass transport to the surface is provided through a concentration potential  $N_{i \text{ core flow}} - N_{i \text{ wall}}$  for each species  $i$  and a mass transport coefficient,  $h_m$ , derived from Sherwood number correlations integrated over space and time [8], as shown in equation 14:

$$\text{Mass}_i = \int h_m (N_{i \text{ core flow}} - N_{i \text{ wall}}) dA dt. \quad (14)$$

Currently, species are assumed not to penetrate the surface, with the exception of carbon; however, the diffusion module is general enough to readily incorporate this possibility in the future.

In order to derive the mass transport coefficient,  $h_m$ , for a specific species from the Sherwood number,  $Sh = h_m L / D_{AB}$ , where  $L$  is a length parameter, the diffusion coefficient,  $D_{12}$ , of species 1 into species 2 must be determined. The Lennard-Jones 6–12 model is used to model the binary diffusion [20].

$$D_{12} = \frac{0.0026280 \sqrt{T^3 (M_1 + M_2) / 2 M_1 M_2}}{P F_{12}^2 S_{12}^{(1,1)}(T_{12})}, \quad (15)$$

where  $M_1, M_2$  are the molecular weights of the binary species,  $T$  is the temperature,  $P$  is the pressure,  $F_{12}$  is the collision diameter, and  $S_{12}^{(1,1)}$  is the collisional cross section integral obtained through table interpolation.

The binary diffusion provides the basis for the multicomponent diffusion coefficient. Each binary diffusion possibility for species  $i, j$ , is used and weighted vs. all other possibilities in the following mixture coefficient combinatory methodology of Wilke in Anderson [21].

$$D_{im} = \frac{1 + X_i}{\sum_{j \neq i} \frac{X_j}{D_{ij}}}, \quad (16)$$

thus enabling the calculation of the diffusion coefficient for a particular specie into a mixture of many species.

Utilizing the collisional cross sections and diameters for viscosity as well as the molecular weight, the following relationship derived from kinetic theory [20] is utilized to determine the viscosity and subsequently the mixture viscosity using Wilke's rule in Anderson [21].

$$\mu = 2.6693 \times 10^{-5} \frac{\sqrt{MT}}{F_{12}^2 S_{12,\mu}}, \quad (17)$$

The Schmidt number,  $Sc = \rho D / \mu$ , where  $D$  is the diffusion coefficient and  $\mu$  is the mixture viscosity, is used to determine which regime of mass transport is applicable. At moderate Schmidt numbers ( $10 < Sc < 1000$ ),

the thickness of the boundary layer is much greater than the thickness of the viscous sublayer; utilizing the momentum integral method, Ruckenstein [22] derived the following Sherwood number:

$$\text{Sh} = \frac{0.0097 \text{Re}^{\frac{9}{10}} \text{Sc}^{\frac{1}{2}} \left( 1.10 + 0.44 \text{Sc}^{\frac{1}{3}} + 0.70 \text{Sc}^{\frac{1}{6}} \right)}{1 + 0.064 \text{Sc}^{\frac{1}{2}} \left( 1.10 + 0.44 \text{Sc}^{\frac{1}{3}} + 0.70 \text{Sc}^{\frac{1}{6}} \right)}. \quad (18)$$

For higher Schmidt numbers ( $\text{Sc} > 1000$ ), the thickness of the boundary layer becomes the order of magnitude of the thin wall-layer and the following relationship is applicable [23]:

$$\text{Sh} = 0.0102 \text{Re}^{\frac{9}{10}} \text{Sc}^{\frac{1}{3}}. \quad (19)$$

These expressions for the Sherwood number have been compared [23] with much experimental data and agree well within the Schmidt number regions specified.

## 6. Equilibrium Kinetics

Equilibrium chemical processes are considered to dominate whenever the characteristic time for a fluid element to traverse the flow field of interest is much longer than the characteristic time for chemical reactions to approach equilibrium. As the pressure and temperature increase, the molecular collision frequency and energy per collision increases, which leads to smaller characteristic chemical times, and chemical processes approach equilibrium.

The condition for chemical equilibrium may be stated as the minimization of the Gibbs Free Energy. For a mixture of  $N$  species (e.g., atoms or molecules), where the number of moles of species,  $i$ , is denoted  $n_i$ , the Gibbs Free Energy per mole of mixture is given in terms of the Gibbs Free Energy of the individual

species,  $g_i$ , the internal energy,  $e$ , the temperature,  $T$ , the entropy,  $s$ , the total pressure,  $p$ , and the specific volume,  $v$ .

$$G = \sum_{i=1}^N n_i g_i - e + Ts - pv \quad (20)$$

The equilibrium method employed in the present study is based on the fact that at equilibrium the total Gibbs energy of the system attains a minimum value. The problem is to find the set of  $n_i$ 's that minimizes  $G$  for a specified energy and specific volume ( $e, V$ ), subject to the constraints of material balances. The standard solution to this type of problem is based on the method of Lagrange's undetermined multipliers. First we must recognize that the total number of atoms of each element in the system is constant. A particular atomic species is denoted by the subscript  $k$ , and  $A_k$  is the total number of atomic masses of the  $k$ -th element in the system, as determined by the initial constitution of the system. Denoting the number of atoms of the  $k$ -th element present in each molecule of chemical species  $i$  by  $a_{ik}$ , then the material balance on each element  $k$  may be written ( $M$  used here is the number of elements),

$$\sum_{k=1}^M \delta_k \left( \sum_{i=1}^N n_i a_{ik} - A_k \right) = 0 \quad (k = 1, 2, \dots, M) \quad (21)$$

after introducing Lagrange multipliers,  $\delta_k$ , for each element. Then a new function,  $F$ , is formed by addition of the last equation to  $G$ . The function,  $F$ , is identical to  $G$  since the summation term is zero. However,  $\frac{\partial F}{\partial n_i}$  and  $\frac{\partial G}{\partial n_i}$  are different since  $F$  incorporates the constraints of the material balances. The minimum of both  $F$  and  $G$  occurs when these partial derivatives are zero.

$$F = G + \sum_{k=1}^M \delta_k \left( \sum_{i=1}^N n_i a_{ik} - A_k \right) \quad (22)$$

$$\left( \frac{MF}{Mn_i} \right)_{e, V, n_i} + \left( \frac{MG}{Mn_i} \right)_{e, V, n_i} \sum_{k=1}^M \nu_k a_{ik} = 0 \quad (\text{for } F_{\min}) \quad (i = 1, N) \quad (23)$$

This equation can be rewritten using the definition of chemical potential  $\mu_i$ , for species  $i$ , where  $R_u$  is the universal gas constant.

$$\mu_i^* + \left( \frac{MG}{Mn_i} \right)_{e, V, n_i} = G_i^0 + R_u T \ln(\mu_i) \quad (i = 1, N) \quad (24)$$

Therefore, from equation 23

$$\mu_i^* + \sum_{k=1}^M \nu_k a_{ik} = 0 \quad (i = 1, 2, \dots, N). \quad (25)$$

The standard Gibbs Free Energy change of formation for species  $i$  is denoted  $G_i^0$ , which is equal to zero for elements in their standard states. The activity for species  $i$  in solution is given by  $\mu_i$  defined in terms of the equilibrium constant,  $K$ , as,

$$K = A_i^{\sum \nu_k} \mu_i^{\sum \nu_k}, \quad (26)$$

where the activities of the components are raised to the corresponding stoichiometric coefficients,  $\sum \nu_k$ . For an ideal gas mixture ( $\sum N_i = 1$ ), where  $N_i$  is the void fraction,

$$\mu_i = f_i = X_i N_i p = p, \quad (27)$$

where  $f_i$  is the fugacity and  $X_i$  is the mole fraction for the  $i$ -th species. For liquid and solid phases [24],

$$\ln(n_i) = \ln(1 - 1/p), \quad (28)$$

which is approximately zero for large pressure, therefore,  $n_i = G_i^0$  from equation 24.

There are N equilibrium equations (equation 25), one for each species, and there are M material-balance equations (equation 21), one for each element, a total of N + M equations. The unknowns in these equations are the  $n_i$ 's, of which there are N, and the  $\delta_k$ 's, of which there are M, a total of N + M. Thus, the number of equations is sufficient for the determination of all unknowns. Numerical experiments were performed with well-known gas-phase systems of which the results matched those of the NASA Lewis equilibrium code [14].

## 7. Surface Description

The full equilibrium control volume approach results in many product mass fractions, which are physically impossible due to the constraints of diffusion into the solid phase. Mainly, the carbon in the control volume, which results from CO and/or CO<sub>2</sub> breakdown, will react with as much iron as possible to form Fe<sub>3</sub>C if permitted. To treat this deficiency, the carbon content in the steel resulting from the diffusion over the current time step has been integrated. This represents the total amount of carbon that may possibly react with the steel while the extra carbon released into the control volume is left as carbon graphite C(GR).

A surface exposed to a carbon concentration G per unit surface area for a specified length of time t has a carbon concentration C(x) at a specified depth of x given by the following relationship [25]:

$$C(x) = \frac{G}{\sqrt{BDt}} e^{-\frac{x^2}{4Dt}}, \quad (29)$$

where D is the diffusion coefficient provided over the  $\delta$  and  $\gamma$  phases (BCC and FCC lattice structure, respectively). The diffusion of carbon into  $\delta$  iron ( $T < 1118^\circ \text{C}$ ) is given by the following function in *Smithells Metals Reference Handbook* [25], where  $R_u$  is the universal gas constant.

$$D = 0.008 e^{-\frac{19.8 \text{ (cal/mol)}}{R_u T}} + 2.2 e^{-\frac{29.3 \text{ (cal/mol)}}{R_u T}} \left( \frac{\text{cm}^2}{\text{s}} \right), \quad (30)$$

while the diffusion of carbon into  $\delta$  iron ( $T < 1300^\circ \text{C}$ ) is provided by

$$D = 0.36 e^{-\frac{36 \text{ (cal/mol)}}{R_u T}} \left( \frac{\text{cm}^2}{\text{s}} \right). \quad (31)$$

To find the total amount of carbon that has diffused in time  $t$ , the concentration function can be integrated, having an error function solution as

$$\int_0^x C(x) dx = \frac{G}{\sqrt{BDt}} \int_0^x e^{-\frac{x^2}{4Dt}} dx = G(\text{erf}(x)). \quad (32)$$

Integrating the concentration profile to the maximum depth to which material can diffuse in time step  $t$ ,  $\sqrt{BDt}$ , provides the carbon diffused into the material over the time period. Usually this depth ranges from 20 to 80 lattice parameters. To treat the reactant product from the full equilibrium calculation, a subset reaction is created consisting of the carbon, iron ( $\delta$ ) and iron ( $\gamma$ ), and iron carbide. The total carbon available for reaction is equal to the diffused carbon plus the original carbon in the steel as well as the possible carbon on surface, also in the form of iron carbide as shown on the left-hand side of the following equation:



where  $\text{Fe}(\delta)$  or  $\text{Fe}(\gamma)$  are supplied as fresh material, as needed, depending upon the control volume temperature. There is assumed no carbon dissolved in  $\text{Fe}(\delta)$  or  $\text{Fe}(\gamma)$ . The product carbon  $C(\text{GR})$ , in the lattice, and  $\text{Fe}_3\text{C}$  from the previous time step are retained as residuals and reintroduced as reactants in the next time step. Carbon graphite is permitted to form or be simply transferred from a reactant to a

product unchanged on the right-hand side if there is excess carbon from the equilibrium calculation in comparison to what is possibly available to react with the existing iron. The amount of  $\text{Fe}_3\text{C}$  that is possible, due to diffusion limitations, is formed and carried over to the next time step if the control volume is below the melting temperature of the iron carbide. On the other hand, if there is no excess carbon, then  $\text{Fe}(\text{C})$  or  $\text{Fe}(\text{Fe})$ , depending on the temperature, is formed or carried over to the next time step. Once this post equilibrium calculation is made, the final energy change in the control volume is recomputed and the amount attributable to the residual solids is accounted for as the surface source term.

## 8. Application to Point Studies

Three systems are presented in this report including the M829A2 cartridge in an M256 tank cannon and both the 616W-APFSDS original cartridge, which had a propellant adiabatic flame temperature near 3,650 K, and the M791-APDS-T training round in the 25-mm Bushmaster cannon.

The calculations for the M829A2 cartridge assume an initial chrome defect or chip. Two calculations were then performed for this region using exposed steel. The first involved normal or standard heat transfer, and the second applied the previously described surface irregularity augmentation to the heat transport due to the actual depth of the defect. The calculations were performed over a region from the forcing cone to about 800 mm down-bore.

Surface temperatures of the first calculation, without the surface roughness factor, are presented in Figure 2. As shown, all three locations reach the user-prescribed melting temperature of 1,723 K.

Figure 3 shows the amount of material lost over the investigated region in comparison to experimental data [26, 27] for three gun tubes. The experimental defect data show widely varying erosion once a defect is formed, with the average presented as a straight line. The tube history is provided as the number of rounds fired to the commencement of the series of M829A2 cartridges, the number of M829A2 cartridges fired, and the serial number of the tube.

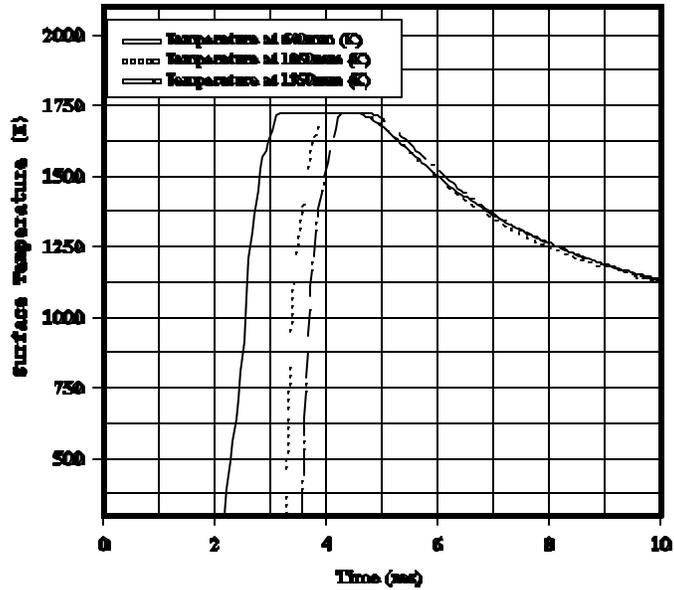


Figure 2. Gun Tube Surface Temperatures at Three Axial Locations for a Single Firing of an M829A2 Cartridge in an M256 Tank Cannon Without Surface Roughness Augmentation to the Heat Transport.


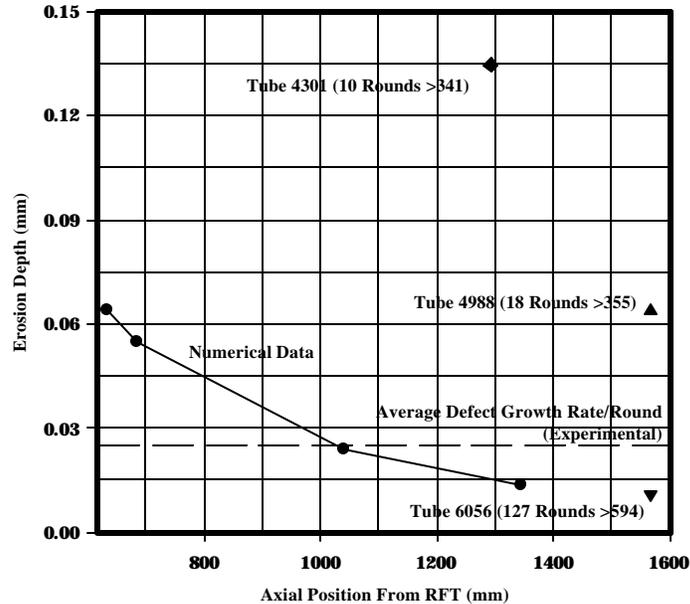



Figure 3. Average Erosion Depth per Round at the Bottom of a Chrome Chip in an M256 Tank Cannon Firing an M829A2 Cartridge Without Surface Roughness Augmentation to the Heat Transport.

Figure 4 shows the effect of added surface roughness to the calculation in lengthening the duration of the melting of the surface. Correspondingly, in Figure 5, the amount of erosion is shown to also increase. The resultant amount of erosion appears to be much closer to the average amount from the experimental “pit-tracking” data in Figure 5 with the augmentation than without it in Figure 3.

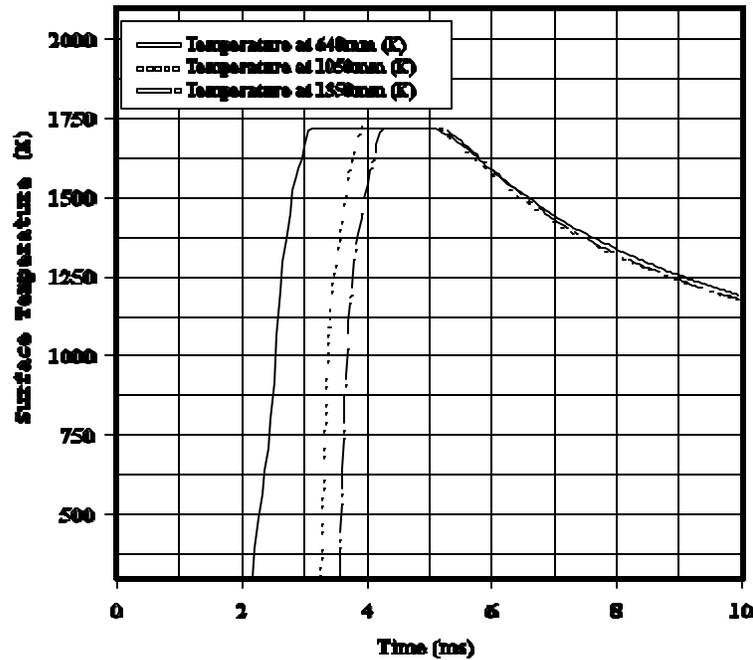


**Figure 4. Gun Tube Surface Temperatures at Three Axial Locations and for a Single Firing of an M829A2 Cartridge in an M256 Tank Cannon With Surface Roughness Augmentation to the Heat Transport.**


The total erosion in these calculations is due to the sum of the gross melting and the melting of iron carbide created near the surface due to the carbon diffusion. This effect can be seen in Figure 6 without, and in Figure 7 with, the surface roughness augmentation to the heat transport. Figure 6 shows the surface temperature, which does not rise to the melt temperature of the steel substrate. Material, however, is being removed at the surface due to the local surface material melt temperature of 1,423 K. The same figure presents how the change in phase from " to ( alters the diffusion rate due to different interstitial atomic mobilities.

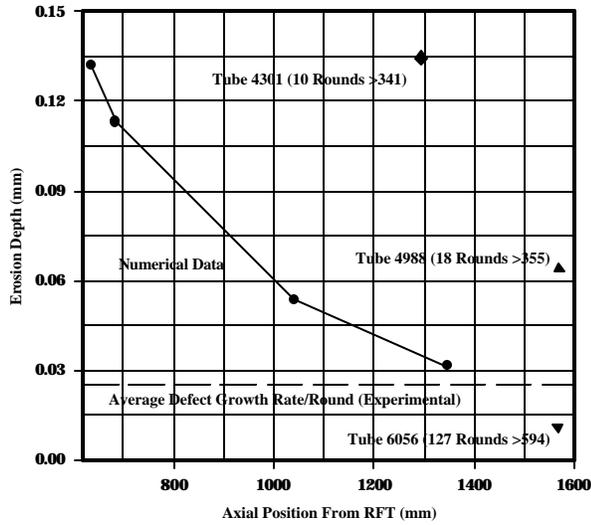

**Figure 5. Average Erosion Depth per Round at the Bottom of a Chrome Chip for an M256 Cannon Firing an M829A2 Cartridge With Surface Roughness Augmentation to the Heat Transport.**

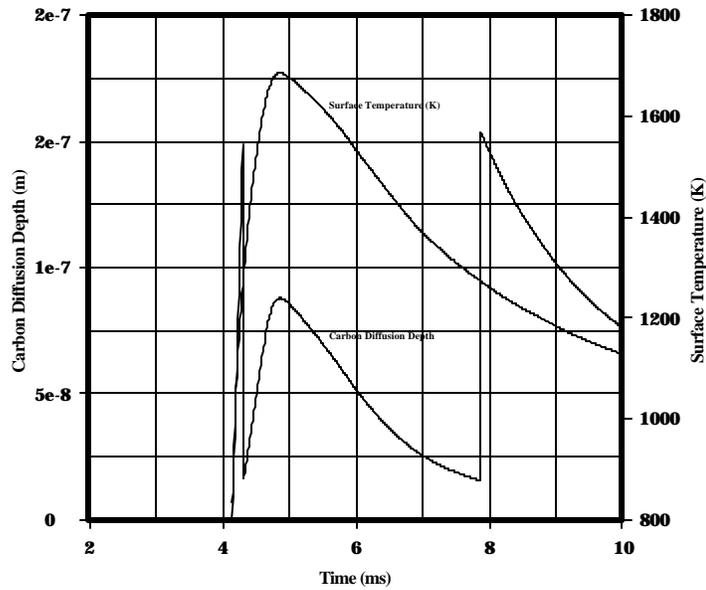

**Figure 6. Surface Temperature and Carbon Diffusion Depth at the Bottom of a Chrome Chip in an M256 Tank Cannon Firing an M829A2 Cartridge, Presented at 1,778 mm From the Rear Face of the Tube Without Surface Roughness Augmentation to the Heat Transport.**

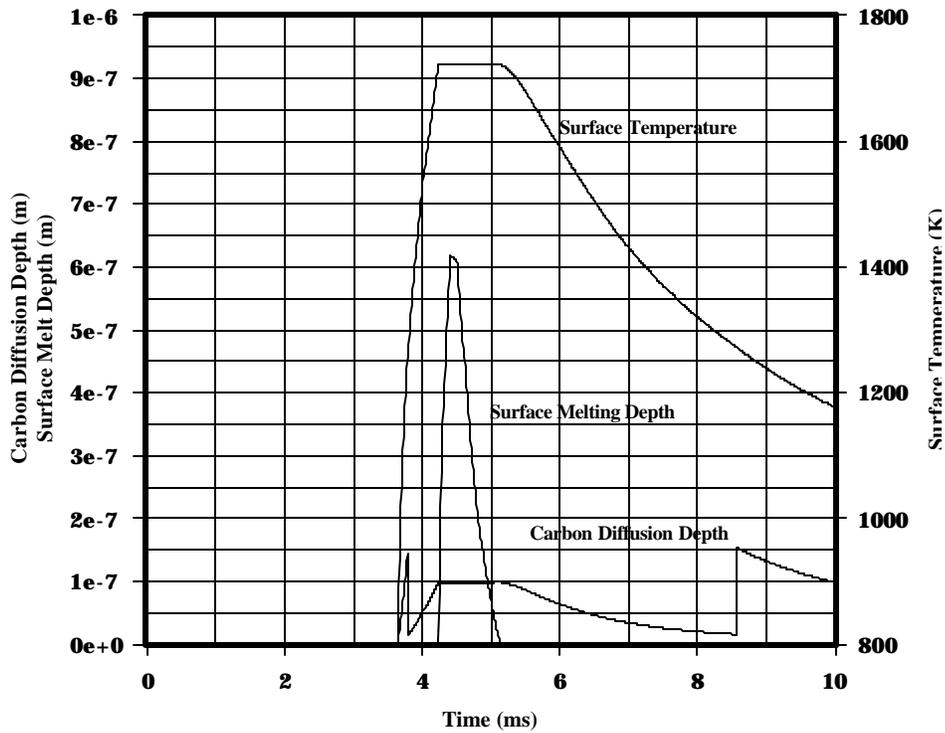


**Figure 7. Surface Temperature, Carbon Diffusion Depth, and Surface Melting Depth in a Chrome Chip of an M256 Tank Cannon, Presented 1,350 mm From the Rear Face of the Tube for an M829A2 Cartridge With Surface Roughness Augmentation to the Heat Transport.**

Figure 7 shows the influence of gross surface melting at the same axial location due to the addition of surface roughness augmentation. Once the surface reaches the base material melt temperature, the carbon diffusion remains constant, as it only depends upon temperature.

The first of the two 25-mm systems in this study is the M791 APDS-T round. Experimental data were obtained from a late 1980's study performed by Veritay Inc. [28] in their instrumented test fixture. The data included averaged erosion rate/round (over 20 individual rounds were averaged) at a series of axial locations given with respect to the commencement of full rifling. When the calculations were performed using the interior ballistic data provided by Benet Laboratories [29], the results were presented with respect


to the rear face of the tube (RFT). This leads to a possible discrepancy of the actual location of the origin of rifling as this location has a tendency to move down-bore as the tube has more rounds fired through it.

The surface temperatures of the cannon firing the M791 cartridge are shown in Figure 8. While these temperatures do not reach the bulk melting temperature of the steel used in the 25-mm nonchromed nitrided Bushmaster cannon of 1,792 K, there is material loss nonetheless. The nitriding was not taken into account in these calculations and would cause some differences in subsurface carbon diffusion. Again, as in the previous example, the material is being lost in this case due to the material transformation to iron carbide and the subsequent removal of this very thin layer when the surface temperature is above the melt temperature of the iron carbide.

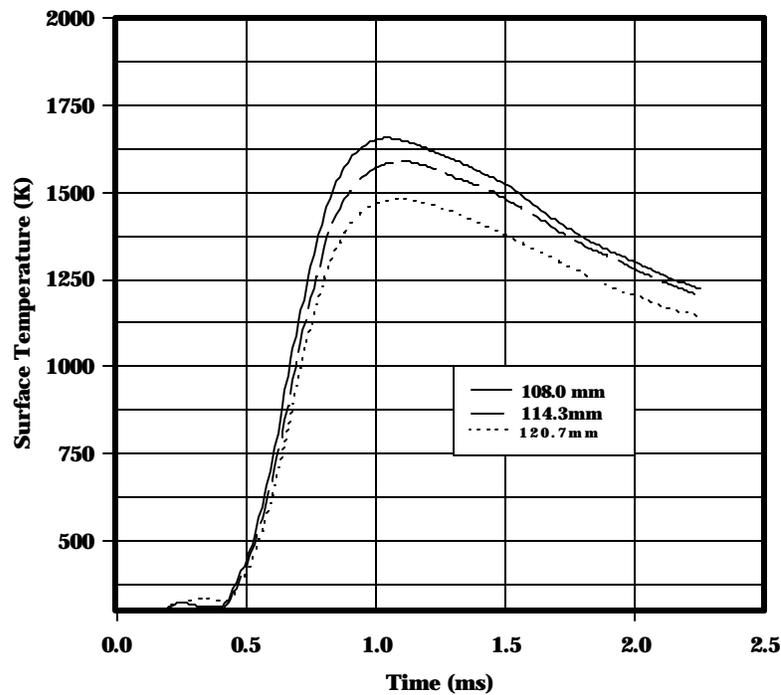


**Figure 8. Surface Temperatures for Three Axial Locations of an M791 Cartridge Fired in an M242, 25-mm Bushmaster Cannon.**

The result of the computed surface material removal for the M791 is presented in Figure 9 along with the experimental data and the location of full rifling. Although the axial location seems to be shifted as stated before, the magnitude of material loss appears to be correct. The surface roughness augmentation to the heat transfer was not used in this case as the surface is not chromed and therefore does not have the site for high recirculating flows.

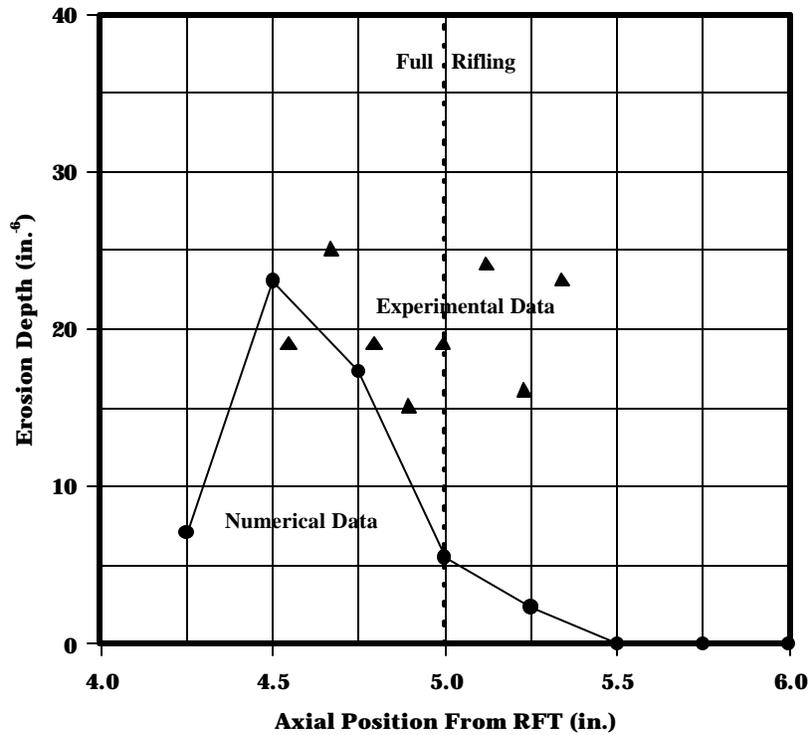


**Figure 9. Computed and Experimental Erosion per Round for an M791 Cartridge Fired in a 25-mm Bushmaster Cannon. Note That the Experimental Data Were Originally Presented With Respect to the Commencement of “Full Rifling,” While the Computational Data Are Presented With Respect to the RFT.**

Figure 10 shows the bore surface temperatures for the cannon firing the 616W (M919 original) cartridge. Also, for this case, the melting temperature of the base material of the Bushmaster cannon is not reached. However, the temperatures are indeed somewhat higher in this case than for the M791 cartridge, and the surface material removed, shown in Figure 11, reflects the higher diffusion of carbon into the gun surface.

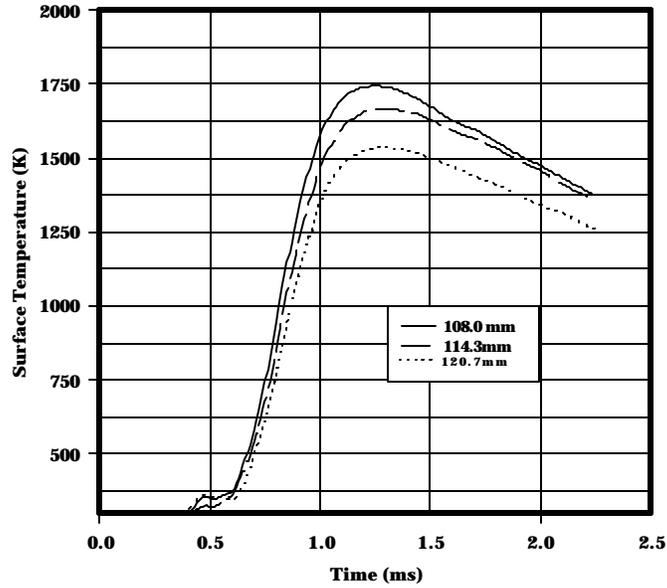

**Figure 10** Surface Temperatures for Three Axial Locations for a 616W (Original M919 APFSDS) Cartridge Fired in an M242 Bushmaster Cannon.

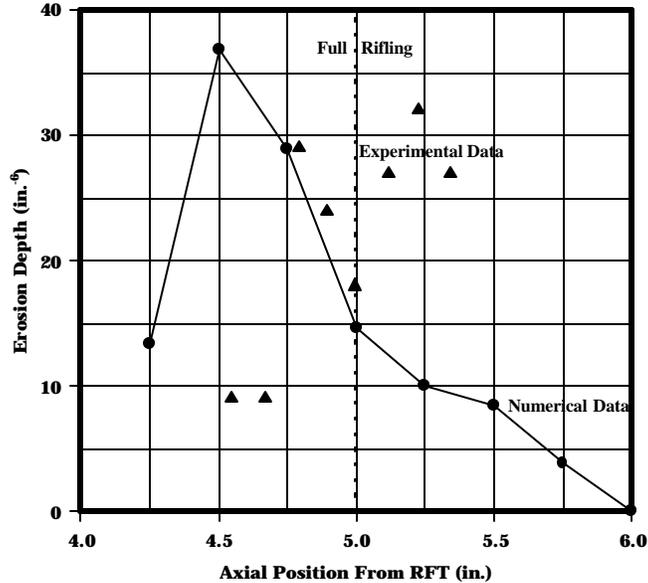

**Figure 11** Computed and Experimental Erosion per Round for a 616W (Original M919 APFSDS) Cartridge Fired in an M242, 25-mm Bushmaster Cannon. Note That the Experimental Data Were Originally Presented With Respect to the Commencement of “Full Rifling,” While the Computational Data Are Presented With Respect to the RFT.

The experimental data in Figure 11 again appears to be shifted with respect to the commencement of rifling, while the magnitude tracks the experimental data well. From Figures 11 and 9, it is shown that the proportional experimental increase in material loss between the M791 and 616W is closely represented in the numerical calculations.

## **9. Concluding Remarks**

An analytical description of the processes involved in the mechanistic description of the gas-surface interaction has been presented to include the melt wipe mechanism, equilibrium chemistry, surface control volume, heat transfer and roughness augmentation, as well as the multicomponent mass transport, and subsurface carbon diffusion.

Three systems were investigated: the M829A2 120-mm tank cartridge, and two 25-mm cartridges: the M791-APDS-T and the 616W-APFSDS. The calculated erosion for the M829A2 cartridge, given the assumption of a chip in the chrome plating, compared well with the experimental data once the surface roughness was incorporated into the heat transport. Neither of the 25-mm systems reached the bulk melting temperature of the base material for the Bushmaster barrel, although both erode. Carbon diffusion limited erosion predicted the amount of material lost in the M791 and 616W cartridges reasonably well.

Other constitutive models and/or conceptual ideas and additional physics are to be investigated to determine their level of importance to surface degradation/erosion, thus providing insight into the mechanisms for erosion and possibly the mitigation thereof through additives to control the heat transfer, gas chemistry, or possibly altering the structure or physics of the surface.

INTENTIONALLY LEFT BLANK.

## 10. References

1. Ward, J. R., T. L. Brosseau, R. P. Kaste, I. C. Stobie, and B. Bensinger. "Erosivity of LOVA Propellants." BRL-TR-02368, U.S. Army Ballistic Research Laboratory, Aberdeen Proving Ground, MD, September 1981.
2. Caveny, L. H. "Steel Erosion Produced by Double Base, Triple Base, and RDX Composite Propellants of Various Flame Temperatures." ARLCD-CR-80016, U.S. Army Armament Research and Development Command, Picatinny Arsenal, NJ, October 1980.
3. Huang, P., M. Cole, and C. Hubbard. Personal communication. U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, April 1998.
4. Montgomery, J. Personal communication. U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, March 1998.
5. Evans, M. R. "User's Manual for Transient Boundary Layer Integral Matrix Procedure TBLIMP." Aerotherm UM-74-55, Prepared for Naval Ordnance Station, Indian Head, MD, October 1974.
6. Dunn, S., D. Coats, G. Nickerson, S. Sopok, P. O'Hara, and G. A. Pfligl. "Unified Computer Model for Predicting Thermochemical Erosion in Gun Barrels." AIAA 95-2440, *Proceedings of 31st AIAA/ASME/SAE/ASEE, San Diego, CA, Joint Propulsion Conference and Exhibit*, July 1995.
7. Weinacht, P., and P. J. Conroy. "A Numerical Method for Predicting Thermal Erosion in Gun Tubes." ARL-TR-1156, U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, July 1996.
8. Conroy, P. J., P. Weinacht, and M. J. Nusca. "120-mm Gun Tube Erosion Including Surface Chemistry Effects." ARL-TR-152, U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, 6 October 1997.
9. Gough, P. S. "The XNOVAKTC Code." BRL-CR-627, U.S. Army Ballistic Research Laboratory, Aberdeen Proving Ground, MD, February 1990.
10. Nusca, M. J. "Investigation of Solid Propellant Gun Systems Using the Next-Generation Interior Ballistics Code." *Proceedings of the 31st JANNAF Combustion Subcommittee Meeting*, CPIA Publication No. 620, vol. 1, pp. 279–292, October 1994.

11. Freedman, E. "BLAKE - A Thermodynamic Code Based on Tiger: Users' Guide and Manual." BRL-TR-02411, U.S. Army Ballistic Research Laboratory, Aberdeen Proving Ground, MD, July 1982.
12. Anderson, R. D., and K. D. Fickie. "IBHVG2 - A Users Guide." BRL-TR-2829, U.S. Army Ballistic Research Laboratory, Aberdeen Proving Ground, MD, July 1987.
13. Janke, P. J., J. A. Dyvik, and C. L. Marksberry. "Electrothermo-Chemical Propellant Extensions to the IBHVG2 Interior Ballistics Simulation: Model Development and Validation." CPIA Publication No. 620, vol. 3, pp. 171-181, October 1994.
14. Gordon, S., and B. J. McBride. "Computer Program for Calculation of Complex Chemical Equilibrium Compositions, Rocket Performance, Incident and Reflected Shocks, and Chapman-Jouget Detonations." NASA SP-273, NASA Lewis, Cleveland, OH, 1971.
15. Landau, H. G. "Heating Conduction in a Melting Solid." *Quarterly of Applied Mathematics*, vol. 8, pp. 81-94, 1950.
16. Stratford, B. S., and G. S. Beavers. "The Calculation of the Compressible Turbulent Boundary Layer in Arbitrary Pressure Gradient - A Correlation of Certain Previous Methods." Aeronautical Research Council, Royal Armament Research and Development Establishment, Seven Oaks, United Kingdom, R&M, No. 3207, 1961.
17. Conroy, P. J. "Gun Tube Heating." BRL-TR-3300, U. S. Army Ballistic Research Laboratory, Aberdeen Proving Ground, MD, December 1991.
18. Miller, R. *Flow Measurement Handbook*, New York: McGraw-Hill Publishing, 1989.
19. Kakac, S., R. K. Shah, and W. Aung. *Handbook of Single-Phase Heat Transfer*. New York: John Wiley and Sons Inc., 1987.
20. Hirschfelder, J. O, C. F. Curtis, and R. B. Bird. *Molecular Theory of Gases and Liquids*. New York: John Wiley and Sons Inc., March 1964.
21. Anderson, J. D. *Hypersonic + High Temperature Gas Dynamics*. New York: McGraw-Hill, 1989.
22. Ruckenstein, E. "Some Remarks on Renewal Models." *Chemical Engineering Science*, vol. 18, p. 223, 1963.
23. Gutfinger, C. *Topics in Transport Phenomena*. New York: John Wiley and Sons, 1975.
24. Smith, J. M., and H. C. Van Ness. *Introduction to Chemical Engineering Thermodynamics*. New York: McGraw-Hill Book Company, Fourth Edition, p. 516, 1987.

25. Brandes, E. A. *Smithells Metals Reference Handbook, Sixth Edition*. Boston, MA: Butterworth & Co., 1983.
26. Hubbard, C., and R. Gilley. Bore Scope Records. U. S. Army Aberdeen Test Center, Aberdeen Proving Ground, MD, 1998.
27. U.S. Department of the Army. *Evaluation of Cannon Tubes*. TM 9-1000-202-14, 1 March 1992.
28. Talley, J. Q., and J. A. Owczarczak. "25-mm Barrel Erosivity Study." Final Report Prepared for GenCorp Aerojet Corporation, Aerojet Ordnance Division, Downey, CA, August 1991.
29. O'Hara, G. P. Personal communication of 25-mm interior ballistic data decks. Benet Laboratories, Watervliet Arsenal, Watervliet, NY, July 1997.

INTENTIONALLY LEFT BLANK.

## **Appendix A:**

### **Blake Thermochemical Input Decks for Propellants Used in This Study**

INTENTIONALLY LEFT BLANK.

Blake Thermochemical input deck for the 25-mm M791 Cartridge using HC-33 propellant.

```
TIT,HC-33 NOM
ING
PRL,CON,2
REJ,H2S,S2O,SO2,K$,KOH$,K2O,K2O2,KO2,K2,NO2,HNO3
REJ,KCO$,KSO$,K2O$,NA2$,ALN,COF2,F2,ALF3,ALO,ALF2,AL23,AL$
REJ,C2N,C2H,C2,CH2O,CH,CH2,CH3,CN,C2H2,C2H4,C2N2,
REJ,ALOH,A2O2,AHO2,ALOF,AIO2,BAO$
REJ,C(S),K2CO3$,K2SO4$,K2S$
CM2,NC1325,87.87,NG,6.99,PEG,.68,KN,.66,ALC,.5,ACETON,1.4,H2O,.9,C,.15,
DPA,0.85
UNI,ENG
GUN,.05,.05,.6
QUIT
```

Blake Thermochemical input decks for the Original 25-mm M919 Cartridge.

```
TIT,HES9053 (L-751) Propellant
ING
PRL,CON,2
REJ,H2S,S2O,SO2,K$,KOH$,K2O,K2O2,KO2,K2,NO2,HNO3
REJ,KCO$,KSO$,K2O$,NA2$,ALN,COF2,F2,ALF3,ALO,ALF2,AL23,AL$
REJ,C2N,C2H,C2,CH2O,CH,CH2,CH3,CN,C2H2,C2H4,C2N2,
REJ,ALOH,A2O2,AHO2,ALOF,AIO2,BAO$
REJ,C(S),K2CO3$,K2SO4$,K2S$
CM2,NC1300,34.40,NG,14.91,RDX,45.60,TRAC,2.90,PEG,0.31,EC,0.52,KN,0.75,
KS,0.75,H2O,.10,C,0.20
UNI,ENG
GUN,.05,.05,.6
QUIT
```

```
TIT,HES9053 (L-752) Propellant
ING
PRL,CON,2
REJ,H2S,S2O,SO2,K$,KOH$,K2O,K2O2,KO2,K2,NO2,HNO3
REJ,KCO$,KSO$,K2O$,NA2$,ALN,COF2,F2,ALF3,ALO,ALF2,AL23,AL$
REJ,C2N,C2H,C2,CH2O,CH,CH2,CH3,CN,C2H2,C2H4,C2N2,
REJ,ALOH,A2O2,AHO2,ALOF,AIO2,BAO$
REJ,C(S),K2CO3$,K2SO4$,K2S$
CM2,NC1300,35.38,NG,14.71,RDX,43.48,TRAC,3.04,PEG,1.36,EC,0.52,KN,0.84,
KS,0.77,H2O,.23,C,0.20
UNI,ENG
GUN,.05,.05,.4
QUIT
```

```
TIT,HES9053 (L-753) Propellant
ING
PRL,CON,2
REJ,H2S,S2O,SO2,K$,KOH$,K2O,K2O2,KO2,K2,NO2,HNO3
REJ,KCO$,KSO$,K2O$,NA2$,ALN,COF2,F2,ALF3,ALO,ALF2,AL23,AL$
REJ,C2N,C2H,C2,CH2O,CH,CH2,CH3,CN,C2H2,C2H4,C2N2,
REJ,ALOH,A2O2,AHO2,ALOF,AIO2,BAO$
REJ,C(S),K2CO3$,K2SO4$,K2S$
CM2,NC1300,35.71,NG,12.73,RDX,44.78,TRAC,3.24,PEG,1.08,EC,0.63,KS,1.05,
KN,0.78,H2O,.24,C,0.020
UNI,ENG
GUN,.05,.05,.4
QUIT
```

```
TIT,HES9053 (L-754) Propellant
ING
PRL,CON,2
REJ,H2S,S2O,SO2,K$,KOH$,K2O,K2O2,KO2,K2,NO2,HNO3
REJ,KCO$,KSO$,K2O$,NA2$,ALN,COF2,F2,ALF3,ALO,ALF2,AL23,AL$
REJ,C2N,C2H,C2,CH2O,CH,CH2,CH3,CN,C2H2,C2H4,C2N2,
REJ,ALOH,A2O2,AHO2,ALOF,AIO2,BAO$
REJ,C(S),K2CO3$,K2SO4$,K2S$
CM2,NC1300,32.25,NG,14.94,RDX,47.73,TRAC,2.75,PEG,0.35,EC,0.45,KS,0.78,
KN,0.75,H2O,.23,C,0.20
```

UNI,ENG  
GUN,.05,.05,.4  
QUIT

Blake Thermochemical input deck for 120-mm Cartridges using nominal JA2 propellant.

TIT,JA-2 - NOMINAL  
PRL,CON,2  
REJ,H2S,S2O,SO2,K\$,KOH\$,K2O,K2O2,KO2,K2,NO2,HNO3  
REJ,KCO\$,KSO\$,K2O\$,NA2\$,ALN,COF2,F2,ALF3,ALO,ALF2,AL23,AL\$  
REJ,C2N,C2H,C2,CH2O,CH,CH2,CH3,CN,C2H2,C2H4,C2N2,  
REJ,ALOH,A2O2,AHO2,ALOF,AIO2,BAO\$  
REJ,C(S),K2CO3\$,K2SO4\$,K2S\$  
CM2,NC1298,59.02,NG,14.78,DEGDN,24.60,AKAR2,.69,BAO,0.0496,  
C,.0496,H2O,.5  
UNI,ENG  
GUN,.05,.05,.4  
QUIT

## **Appendix B:**

### **XKTC Interior Ballistic Input Decks Used in This Study**

INTENTIONALLY LEFT BLANK.

An XKTC input deck of an M829A2 round (Courtesy of Dr. G. Peter O'Hara, Benet Labs)

M829A2 APFSDS-T

TFFFTTT001000001060000010010000000

```
69 -3 099999 .0001
0.015 186.660 0.00025 2.000 0.050 0.005 0.0001 0.0001
1000 100 1100 100 1500 100
6 4 3 4 0 0 3 2 0 0 0 8 0 0 0 1
0 0 0
5.290E+02 1.470E+01 2.890E+01 1.400E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00
5.290E+02 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00
Stick 0.000E+00 7.500E-01 4.400E-01 5.763E-02 0.000E+00 0.000E+00
1.925E+01 2.200E+01 8.600E-01 0.000E+00 0.000E+00
7 4.310E-01 3.100E-02 8.750E-01 7.000E+00 0.000E+00 0 0.000E+00 0
1.000E+04 1.000E+00 4.175E+04 0.000E+00 5.000E-01
1.000E+04 4.040E-03 7.162E-01 1.000E+05 8.600E-04 8.796E-01 0.000E+00 8.000E+02
2.770E-02 1.345E-04 6.000E-01
2.037E+07 2.482E+01 1.227E+00 2.698E+01
Stick 7.500E-01 1.925E+01 1.490E+00 5.763E-02 0.000E+00 0.000E+00
7 3.840E-01 3.900E-02 5.980E-01 7.000E+00 0.000E+00 0 0.000E+00 0
1.000E+04 1.000E+00 4.175E+04 0.000E+00 5.000E-01
1.000E+04 4.040E-03 7.162E-01 1.000E+05 8.600E-04 8.796E-01 0.000E+00 8.000E+02
2.770E-02 1.345E-04 6.000E-01
2.037E+07 2.482E+01 1.227E+00 2.698E+01
JA2H - 7.500E-01 1.925E+01 1.600E+01 5.763E-02 0.000E+00 0.000E+00
15 6.710E-01 3.700E-02 8.750E-01 1.900E+01 0.000E+00 0 0.000E+00 0
1.000E+04 1.000E+00 4.175E+04 0.000E+00 5.000E-01
1.000E+04 4.040E-03 7.162E-01 1.000E+05 8.600E-04 8.796E-01 0.000E+00 8.000E+02
2.770E-02 1.345E-04 6.000E-01
2.037E+07 2.482E+01 1.227E+00 2.698E+01
9.968E+06 3.093E+01 1.221E+00 2.300E+01
0.000E+00 2.500E-04 1.250E-03 1.500E-03
5.000E-01 4.800E+00 4.810E+00
0.000E+00 0.000E+00 0.000E+00
1.400E+01 1.400E+01 0.000E+00
1.400E+01 1.400E+01 0.000E+00
0.000E+00 0.000E+00 0.000E+00
0.000E+00 2.250E+00 3.000E+00 3.090E+00 1.900E+01 3.090E+00 2.200E+01 2.380E+00
2.373E+01 2.360E+00 2.087E+02 2.360E+00
0.000E+00 1.000E+02 1.000E+00 1.500E+03 1.500E+00 4.000E+02 2.500E+02 4.000E+02
1.400E+00 1.470E+01 5.290E+02 2.890E+01
5.000E-02 4.850E-01 6.000E+00 2.000E+00
7.770E+00 2.280E-02 7.000E-01
0.000E+00 1.000E+01 0.000E+00 1.000E+00
2.200E+01 1.720E+01 4.400E+01 0.000E+00 0.000E+00 4.057E+03
3.0 19. 30. 41. 60. 90. 120. 19.
7 2 0 0 0 0 0 1 0 0 0 0 0 0
0.000E+00 0.000E+00 7.200E-01 5.930E-01 4.380E+00 5.930E-01 4.880E+00 7.300E-01
6.750E+00 7.300E-01 1.196E+01 1.170E+00 1.546E+01 1.420E+00
3 4 0 0
0.000E+00 1.450E-01 1.800E+01 1.450E-01 2.220E+01 5.000E-03
2.950E-02 1.470E+01 4.550E-02 1.100E+04 4.970E-02 2.500E+04 5.480E-02 1.000E+05
2 0 0
1.000E+04 1.310E-04 1.301E+00 1.000E+05 3.950E+00 1.761E-01
0.000E+00 8.000E+02 2.770E-02 1.345E-04 0.000E+00
9.300E+06 2.239E+01 1.258E+00
```

An XKTC input deck of an M791 round (Courtesy of Dr. G. Peter O'Hara, Benet Labs)

```

25MM M242          M791 - 135 gm          RESISTANCE-PERRIN
TTFBTTT0010000010101000100000000000
  75  -2   099999   0   0   0.00001
    0.003   73.400   0.0002   1.500   0.050   0.01   0.0001   0.0001
1000  50 1100   50
  10   3   3   10   2   0   1   1   0   0   0   5   0   0   0   0
  0   0   0
5.300E+02 1.470E+01 2.890E+01 1.400E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00
5.300E+02 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00
7 Perf HC33          7.300E-02 4.447E+00 2.141E-01 5.560E-02 0.000E+00 0.000E+00
  7 1.040E-01 1.000E-02 1.100E-01 7.000E+00 0.000E+00 0 0.000E+00 0
1.740E+03 1.000E+00 5.000E+04 0.000E+00 5.000E-01
4.000E+03 1.390E-03 8.053E-01 0.000E+00 5.300E+02 2.770E-02 1.345E-04 6.000E-01
1.837E+07 2.511E+01 1.234E+00 2.801E+01
1.837E+07 1.837E+07 9.500E-01 1.000E+00 2.370E-03
9.968E+06 3.093E+01 1.221E+00 4.348E-02
0.000E+00 1.200E-04 2.500E-04
7.300E-02 2.730E-01 1.073E+00
0.000E+00 0.000E+00 0.000E+00
0.000E+00 3.000E+00 1.000E+00
0.000E+00 0.000E+00 0.000E+00
0.000E+00 2.500E-01 7.300E-02 2.875E-01 1.450E-01 4.865E-01 2.800E-01 5.800E-01
5.530E-01 6.615E-01 8.330E-01 6.735E-01 3.876E+00 6.715E-01 4.447E+00 4.815E-01
4.983E+00 5.040E-01 7.886E+01 5.040E-01
0.000E+00 2.500E+03 3.600E-02 3.519E+03 9.600E-02 4.738E+03 2.040E-01 4.738E+03
7.480E-01 2.126E+03 2.190E+00 1.220E+03 5.096E+00 8.520E+02 1.109E+01 7.360E+02
2.941E+01 5.640E+02 9.000E+01 5.640E+02
7.847E+00 2.280E-02 7.000E-01
0.000E+00 5.300E+02 7.777E+01 5.300E+02
0.000E+00 1.000E+00 1.000E+00 0.000E+00 1.000E+00
4.700E+00 2.977E-01 1.000E-02 6.000E+00 0.000E+00 0.000E+00
  0.00   4.25   4.5   4.75   5.00
  0.07   0.00   0.00   2   0
  0   0   0   0   0   0   0   0   0   0   0   0   0

```

An XKTC input deck of an "original" M919 round (Courtesy of Dr. G. Peter O'Hara, Benet Labs)

```
25MM M242                M919 Round - 132 gm RESISTANCE-PERRIN
TTFFTTT0010000010401000100000000000
 7099999  0999999  0  0  0.00001
   .005   74.105  0.00002  1.500  0.050  0.003  0.0001  0.0001
 10  3  3  10  2  0  1  2  0  0  0  5  0  0  0  0
  0  0  0
5.300E+02 1.470E+01 2.890E+01 1.400E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00
5.300E+02 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00 0.000E+00
94.5 gm - HES-9053 7.300E-02 4.647E+00 2.083E-01 6.033E-02 0.000E+00 0.000E+00
 7 1.300E-01 1.250E-02 1.375E-01 7.000E+00 0.000E+00 0 0.000E+00 0
1.740E+03 1.000E+00 5.000E+04 0.000E+00 5.000E-01
4.000E+03 1.633E-04 1.179E+00 5.000E+03 5.077E-03 6.998E-01 0.000E+00 8.020E+02
2.770E-02 1.345E-04 6.000E-01
2.028E+07 2.498E+01 1.232E+00 2.847E+01
1.927E+07 2.028E+07 9.000E-01 1.000E+00 2.370E-03
9.968E+06 3.093E+01 1.221E+00 4.348E-02
0.000E+00 1.200E-04 2.500E-04
8.730E-01 1.073E+00 1.873E+00
0.000E+00 0.000E+00 0.000E+00
0.000E+00 3.000E+00 1.000E+00
0.000E+00 0.000E+00 0.000E+00
0.000E+00 2.500E-01 7.300E-02 2.875E-01 1.450E-01 4.865E-01 2.800E-01 5.800E-01
5.530E-01 6.615E-01 8.330E-01 6.735E-01 3.876E+00 6.735E-01 4.447E+00 4.815E-01
4.983E+00 5.040E-01 7.886E+01 5.040E-01
0.000E+00 2.500E+03 3.600E-02 3.519E+03 9.600E-02 4.738E+03 2.040E-01 4.738E+03
7.480E-01 2.126E+03 2.190E+00 1.220E+03 5.096E+00 8.520E+02 1.109E+01 7.360E+02
2.941E+01 5.640E+02 9.000E+01 5.640E+02
1.400E+00 1.470E+01 5.300E+02 2.890E+01
7.847E+00 2.280E-02 7.000E-01
0.000E+00 5.300E+02 7.886E+01 5.300E+02
2.500E+01 7.600E+01 0.000E+00 0.000E+00 1.000E+00
4.753E+00 2.913E-01 1.000E-02 6.000E+00 0.000E+00 0.000E+00
  0.00  4.00  4.25  4.5  4.75  5.00
```

INTENTIONALLY LEFT BLANK.

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC DDA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218	1	DIRECTOR US ARMY RESEARCH LAB AMSRL DD 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	HQDA DAMO FDQ D SCHMIDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460	1	DIRECTOR US ARMY RESEARCH LAB AMSRL CS AS (RECORDS MGMT) 2800 POWDER MILL RD ADELPHI MD 20783-1145
1	OSD OUSD(A&T)/ODDDR&E(R) R J TREW THE PENTAGON WASHINGTON DC 20301-7100	3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1145
1	DPTY CG FOR RDA US ARMY MATERIEL CMD AMCRDA 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001		<u>ABERDEEN PROVING GROUND</u>
1	INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN PO BOX 202797 AUSTIN TX 78720-2797	4	DIR USARL AMSRL CI LP (BLDG 305)
1	DARPA B KASPAR 3701 N FAIRFAX DR ARLINGTON VA 22203-1714		
1	NAVAL SURFACE WARFARE CTR CODE B07 J PENNELLA 17320 DAHLGREN RD BLDG 1470 RM 1101 DAHLGREN VA 22448-5100		
1	US MILITARY ACADEMY MATH SCI CTR OF EXCELLENCE DEPT OF MATHEMATICAL SCI MADN MATH THAYER HALL WEST POINT NY 10996-1786		

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	HQDA DIR R&D SAAL TR W MORRISON SUITE 9800 2511 JEFFERSON DAVIS HWY ARLINGTON VA 22201	1	PM PEO ARMAMENTS TANK MAIN ARMAMENT SYS AMCPM TMA 105 PICATINNY ARSENAL NJ 07806-5000
1	HQS US ARMY MATERIEL CMD AMCICP AD 5001 EISENHOWER AVE ALEXANDRIA VA 22331-0001	1	PM PEO ARMAMENTS TANK MAIN ARMAMENT SYS AMCPM TMA AS H YUEN PICATINNY ARSENAL NJ 07806-5000
1	US ARMY BMDS CMD ADVANCED TECHLGY CTR PO BOX 1500 HUNTSVILLE AL 35807-3801	2	CDR US ARMY ARDEC AMSTA AR CCH B C MANDALA E FENNELL PICATINNY ARSENAL NJ 07806-5000
1	OFC OF THE PRODUCT MGR SFAE AR HIP IP R DE KLEINE 155MM HOWITZER M109A6 PALADIN PICATINNY ARSENAL NJ 07806-5000	1	CDR US ARMY ARDEC AMSTA AR CCS PICATINNY ARSENAL NJ 07806-5000
1	PM CRUSADER MUNITIONS SFAE GCSS CRM LTC D ARMOUR BLDG 171A PICATINNY ARSENAL NJ 07806-5000	1	CDR US ARMY ARDEC AMSTA AR WE D DOWNS PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC PROD BASE MODRNZTN AGENCY AMSMC PBM A SIKLOSI PICATINNY ARSENAL NJ 07806-5000	10	CDR US ARMY ARDEC AMSTA AR WEE M PADUANO S EINSTEIN S WESTLEY S BERNSTEIN J RUTKOWSKI B BRODMAN P O-REILLY R CIRINCIONE P HUI J O-REILLY PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC PROD BASE MODRNZTN AGENCY AMSTA AR WES L LAIBSON PICATINNY ARSENAL NJ 07806-5000		
1	PM PEO ARMAMENTS TANK MAIN ARMAMENT SYS AMCPM TMA PICATINNY ARSENAL NJ 07806-5000	3	CDR US ARMY ARDEC AMSTA AR AEE WW M MEZGER D WIEGAND P LU PICATINNY ARSENAL NJ 07806-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	CDR US ARMY ARDEC AMSTA AR DBS T G FERDINAND PICATINNY ARSENAL NJ 07806-5000
1	COMMANDER AMSTA AR FS T GORA PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC AMSTA AR FS DH PICATINNY ARSENAL NJ 07806-5000
2	CDR US ARMY ARDEC AMSTA AR FSA S R KOPMANN B MACHAK PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY ARDEC AMSTA AR FSA D K CHUNG PICATINNY ARSENAL NJ 07806-5000
1	DIR BENET WEAPONS LAB AMSTA AR CCB TA G A PFLEGL WATERVLIET NY 12189-4050
1	DIR BENET WEAPONS LAB AMSTA AR CCB T S SOPOK WATERVLIET NY 12189-4050
1	DIR BENET WEAPONS LAB AMSTA AR CCB D R HASENBEIN WATERVLIET NY 12189-4050
2	CDR US ARMY RSRCH OFC TECH LIB D MANN PO BOX 12211 RESEARCH TRIANGLE PARK NC 27709-2211

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	PM US TANK AUTOMOTIVE CMD AMCPM ABMS T DEAN WARREN MI 48092-2498
1	PM US TANK AUTOMOTIVE CMD FIGHTING VEHICLE SYSTEMS SFAE ASM BV WARREN MI 48397-5000
1	PM ABRAMS TANK SYSTEM SFAE ASM AB WARREN MI 48397-5000
1	DIR HQ TRAC RPD ATCD MA FT MONROE VA 23651-5143
1	COMMANDER RADFORD ARMY AMMUNITION PLANT SMCAR QA HI LIB RADFORD VA 24141-0298
1	COMMANDER US ARMY NGIC AMXST MC 3 220 SEVENTH ST NE CHARLOTTESVILLE VA 22901-5396
1	COMMANDANT USAFAC&S ATSF CD COL T STRICKLIN FT SILL OK 73503-5600
1	COMMANDANT USAF&S ATSF CN P GROSS FT SILL OK 73503-5600
4	CDR NAVAL RSRCH LAB TECH LIBRARY CODE 4410 K KAILASANATE J BORIS E ORAN WASHINGTON DC 20375-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	OFFICE OF NAVAL RSRCH CODE 473 J GOLDWASSER 800 N QUINCY ST ARLINGTON VA 22217-9999	1	CDR NAVAL AIR WARFARE CTR INFORMATION SCIENCE DIV CHINA LAKE CA 93555-6001
1	OFFICE OF NAVAL TECHLGY ONT 213 D SIEGEL 800 N QUINCY ST ARLINGTON VA 22217-5000	1	WL MNME ENERGETIC MATERIALS BR 2306 PERIMETER RD STE 9 EGLIN AFB FL 32542-5910
6	CDR NAVAL SURFACE WARFARE CTR T C SMITH S MITCHELL S PETERS J CONSAGA C GOTZMER TECH LIB INDIAN HEAD MD 20640-5000	1	SDIO DA E GERRY PENTAGON WASHINGTON DC 21301-7100
1	CDR NAVAL SURFACE WARFARE CTR CODE G30 GUNS & MUNITIONS DIV DAHLGREN VA 22448-5000	2	HQ DTRA D LEWIS A FAHEY 6801 TELEGRAPH RD ALEXANDRIA VA 22310-3398
1	CDR NAVAL SURFACE WARFARE CTR CODE G32 GUNS SYSTEMS DIV DAHLGREN VA 22448-5000	1	DIR SANDIA NATL LABS M BAER DEPT 1512 PO BOX 5800 ALBUQUERQUE NM 87185
1	CDR NAVAL SURFACE WARFARE CTR CODE E23 TECH LIB DAHLGREN VA 22448-5000	1	DIR SANDIA NATL LABS R CARLING COMBUSTION RSRCH FACILITY LIVERMORE CA 94551-0469
1	CDR NAVAL SURFACE WARFARE CTR CODE E23 TECH LIB DAHLGREN VA 22448-5000	2	DIR LLNL L 355 A BUCHINGHAM M FINGER PO BOX 808 LIVERMORE CA 94550-0622
2	CDR NAVAL AIR WARFARE CTR CODE 388 C F PRICE T BOGGS CHINA LAKE CA 93555-6001	2	BATTELLE TWSTIAC V LEVIN 505 KING AVE COLUMBUS OH 43201-2693
2	CDR NAVAL AIR WARFARE CTR CODE 3895 T PARR R DERR CHINA LAKE CA 93555-6001	1	BATELLE PNL M GARNICH PO BOX 999 RICHLAND WA 99352

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	CPI JHU H J HOFFMAN 10630 LITTLE PATUXENT PKWY STE 202 COLUMBIA MD 21044-3200	1	RUTGERS UNIVERSITY DEPT OF MECH AND AERO ENGRG S TEMKIN UNIV HEIGHTS CAMPUS NEW BRUNSWICK NJ 08903
1	AFELM THE RAND CORP LIBRARY D 1700 MAIN ST SANTA MONICA CA 90401-3297	1	UNIV OF UTAH DEPT OF CHEMICAL ENGRG A BAER SALT LAKE CITY UT 84112-1194
1	BRIGHAM YOUNG UNIV M BECKSTEAD DEPT OF CHEMICAL ENGRG PROVO UT 84601	1	ARROW TECHLGY ASSOC INC 1233 SHELBURNE RD D-8 SOUTH BURLINGTON VT 05403
1	CALIF INSTITUTE OF TECHLGY F E C CULICK 204 KARMAN LAB MAIN STOP 301 46 1201 E CALIFORNIA STR PASADENA CA 91109	1	AAI CORPORATION D CLEVELAND PO BOX 126 HUNT VALLEY MD 21030-0126
1	MILLERSVILLE UNIV PHYSICS DEPT C W PRICE MILLERSVILLE PA 17551	7	ALLIANT TECHSYSTEMS INC R E TOMPKINS J BODE C CANDLAND L OSGOOD R BURETTA R BECKER M SWENSON 600 SECOND ST NE HOPKINS MN 55343
2	UNIV OF ILLINOIS DEPT OF MECH INDUSTRY ENGRG H KRIER R BEDDINI 144 MEB 1206 N GREEN ST URBANA IL 61801-2978	1	ELI FREEDMAN AND ASSOC E FREEDMAN 2411 DIANA RD BALTIMORE MD 21209-1525
1	UNIV OF MASSACHUSETTS DEPT OF MECHANICAL ENGRG K JAKUS AMHERST MA 01002-0014	6	ALLIANT TECHSYSTEMS INC L GIZZI D A WORRELL W J WORRELL C CHANDLER S RITCHIE A ZEIGLER RADFORD ARMY AMMO PLANT RADFORD VA 24141-0299
1	UNIV OF MINNESOTA DEPT OF MECHANICAL ENGRG E FLETCHER MINNEAPOLIS MN 55414-3368	2	ALLIANT TECHSYSTEMS INC W B WALKUP T F FARABAUGH ALLEGHENY BALLISTICS LAB PO BOX 210 ROCKET CENTER WV 26726
4	PENNSYLVANIA STATE UNIV DEPT OF MECHANICAL ENGRG V YANG K KUO S THYNELL G SETTLES UNIVERSITY PARK PA 16802-7501		

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	ALLIANT TECHSYSTEMS INC R CARTWRIGHT AEROSPACE 100 HOWARD BLVD KENVILLE NJ 07847	1	SOUTHWEST RSRCH INST J P RIEGEL 6220 CULEBRA RD PO DRAWER 28510 SAN ANTONIO TX 78228-0510
1	L MARTIN ARM SYS J TALLEY RM 1309 LAKESIDE AVE BURLINGTON VT 05401	1	KELLER SERVICES GEORGE KELLER 3510 GARRETT COURT ABERDEEN MD 21001-1232
1	PRIMEX F E WOLF BADGER ARMY AMMO PLANT BARABOO WI 53913	3	VERITAY TECHGY INC E FISHER R SALIZONI J BARNES 4845 MILLERSPORT HWY EAST AMHERST NY 14501-0305
3	PRIMEX E J KIRSCHKE A F GONZALEZ J DRUMMOND D W WORTHINGTON PO BOX 222 SAINT MARKS FL 32355-0222	1	PRIMEX E STEINER DIR LARGE CAL R & D PO BOX 127 RED LION PA 17356
2	PRIMEX N HYLTON J BUZZETT 10101 9TH ST NORTH ST PETERSBURG FL 33716	1	SRI INTERNATIONAL TECH LIB PROPULSION SCIENCES DIV 333 RAVENWOOD AVE MENLO PARK CA 94025-3493
1	PAUL GOUGH ASSOC INC P S GOUGH 1048 SOUTH ST PORTSMOUTH NH 03801-5423		<u>ABERDEEN PROVING GROUND</u>
1	FRELIN ASSOCIATES INC 4411 QUAKER HILLS CT HAVRE DE GRACE MD 21078	1	CDR USAATC STECs LI R HENDRICKSEN
1	GEN DYN DEF SYS (PCRL) N MESSINA PRINCETON CORPORATE PLAZA 11 DEERPARK DR BLDG IV STE 119 MONMOUTH JUNCTION NJ 08852	28	DIR USARL AMSRL WM B A HORST AMSRL WM BE T MINOR T COFFEE G WREN C LEVERITT W OBERLE L M CHANG J COLBURN P CONROY D KOOKER M NUSCA
2	ROCKWELL INTRNTNL SCIENCE CTR DR S CHAKRAVARTHY DR S PALANISWAMY 1049 CAMINO DOS RIOS PO BOX 1085 THOUSAND OAKS CA 91360		

NO. OF  
COPIES ORGANIZATION

NO. OF  
COPIES ORGANIZATION

ABERDEEN PROVING GROUND (CONTINUED)

AMSRL WM BC  
P PLOSTINS  
M BUNDY  
B GUIDOS  
D LYON  
J GARNER  
V OSKAY  
P WEINACHT  
AMSRL WM BD  
A JUHASZ  
M MCQUAID  
B FORCH  
C CHABOŁOWSKI  
AMSRL WM MC  
J MONTGOMERY  
J BEATTY  
R ADLER  
AMSRL WM MB  
L BURTON  
AMSRL CI HA  
W STUREK  
AMSRL CI  
C NIETUBICZ

INTENTIONALLY LEFT BLANK.

<b>REPORT DOCUMENTATION PAGE</b>			<i>Form Approved OMB No. 0704-0188</i>	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson				
<b>1. AGENCY USE ONLY (Leave blank)</b>		<b>2. REPORT DATE</b> September 1999	<b>3. REPORT TYPE AND DATES COVERED</b> Final, Nov 97 - Mar 98	
<b>4. TITLE AND SUBTITLE</b> An Investigation of the Erosion Physics/Mechanisms of Current Army Systems (Point Studies)			<b>5. FUNDING NUMBERS</b>  IL162618AH80	
<b>6. AUTHOR(S)</b>  Paul J. Conroy, Paul Weinacht, and Michael J. Nusca				
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b>  U.S. Army Research Laboratory ATTN: AMSRL-WM-BE Aberdeen Proving Ground, MD 21005-5066			<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b>  ARL-TR-2054	
<b>9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES)</b>			<b>10. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>	
<b>11. SUPPLEMENTARY NOTES</b>				
<b>12a. DISTRIBUTION/AVAILABILITY STATEMENT</b>  Approved for public release; distribution is unlimited.			<b>12b. DISTRIBUTION CODE</b>	
<b>13. ABSTRACT (Maximum 200 words)</b>  Future systems performance requirements have led to a heightened awareness of the erosion issue and to the development of erosion investigations in the U.S. Army and Navy. These investigations involve experimental and modeling efforts to understand the thermal, chemical, and mechanical contributions to erosion/wear. A description of the mechanistic erosion representation follows in this report. The calculation procedure is illustrated, including details of the mass transport scheme, gas-surface interface, surface melt wipe model with dynamic gridding, and the equilibrium kinetics model, which utilizes the NASA Lewis thermochemical library.  The following cartridges are investigated: the M829A2 APFSDS in the M256 120-mm tank cannon and the M791-APDS-T and 616W-APFS (the "original" M919), both in the 25-mm Bushmaster cannon. The resulting mass lost per round for these systems compares well qualitatively with the experimental data, providing some support to the assumptions in the code. The primary conclusion is that carburization leading to iron carbide formation is an important contributing factor for much of the material lost from the steel barrel once it is exposed through cracks or chips in the surface coating.				
<b>14. SUBJECT TERMS</b>  gun tube erosion, heat transfer, carburization			<b>15. NUMBER OF PAGES</b> 45	
			<b>16. PRICE CODE</b>	
<b>17. SECURITY CLASSIFICATION OF REPORT</b> UNCLASSIFIED	<b>18. SECURITY CLASSIFICATION OF THIS PAGE</b> UNCLASSIFIED	<b>19. SECURITY CLASSIFICATION OF ABSTRACT</b> UNCLASSIFIED	<b>20. LIMITATION OF ABSTRACT</b> UL	

INTENTIONALLY LEFT BLANK.

**USER EVALUATION SHEET/CHANGE OF ADDRESS**

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

- 1. ARL Report Number/Author ARL-TR-2054 (Conroy) Date of Report September 1999
- 2. Date Report Received \_\_\_\_\_
- 3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_
- 4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_
- 5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_
- 6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

CURRENT ADDRESS	_____
	Organization
	_____
	Name <span style="float: right;">E-mail Name</span>
_____	
Street or P.O. Box No.	
_____	
City, State, Zip Code	

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

OLD ADDRESS	_____
	Organization
	_____
	Name
_____	
Street or P.O. Box No.	
_____	
City, State, Zip Code	

(Remove this sheet, fold as indicated, tape closed, and mail.)  
**(DO NOT STAPLE)**

---

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS

**BUSINESS REPLY MAIL**  
FIRST CLASS PERMIT NO 0001,APG,MD

POSTAGE WILL BE PAID BY ADDRESSEE

DIRECTOR  
US ARMY RESEARCH LABORATORY  
ATTN AMSRL WM BE  
ABERDEEN PROVING GROUND MD 21005-5066



NO POSTAGE  
NECESSARY  
IF MAILED  
IN THE  
UNITED STATES

