

ARMY RESEARCH LABORATORY



# Accelerated Adhesive Curing for Induction-Based Repair of Composites

by Steven H. McKnight, Bruce K. Fink, Sean Wells,  
Shridhar Yarlagadda, and John W. Gillespie Jr.

ARL-TR-2103

October 1999

Approved for public release; distribution is unlimited.

DTIC QUALITY INSPECTED 1

20000118 061

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# **Army Research Laboratory**

Aberdeen Proving Ground, MD 21005-5069

---

---

ARL-TR-2103

October 1999

## **Accelerated Adhesive Curing for Induction-Based Repair of Composites**

Steven H. McKnight and Bruce K. Fink  
Weapons and Materials Research Directorate, ARL

Sean Wells, Shridhar Yarlagadda, and John W. Gillespie Jr.  
University of Delaware

---

---

## Abstract

---

A methodology for accelerated curing of commercially available room-temperature curing paste adhesives is outlined. Cure kinetics of the adhesive were studied by thermochemical analysis, and degree of cure was related to processing parameters and cure cycles. Increasing the cure temperature to 100°C reduced the cure time from 16 hr to approximately 15 min for 98% cure. Induction-heating techniques were used to demonstrate rapid heating of adhesives at the bondline for lap shear specimens.

## **Acknowledgments**

Sean Wells is an Undergraduate Research Assistant at the University of Delaware's Center for Composite Materials (UD-CCM) in Newark, Delaware. Dr. Shridhar Yarlagadda is a Research Associate at UD-CCM and Dr. John Gillespie is a professor in the Material Science Program at UD and is Technical Director of UD-CCM. This research was funded by the U.S. Army Research Laboratory (ARL) through the Composite Materials Research cooperative agreement with UD-CCM.

INTENTIONALLY LEFT BLANK.

# Table of Contents

	<u>Page</u>
Acknowledgments.....	iii
List of Figures.....	vii
List of Tables .....	ix
1. Introduction .....	1
2. Thermochemical Analysis.....	2
3. Induction Heating.....	8
4. Conclusions .....	9
5. References .....	11
Distribution List .....	13
Report Documentation Page .....	23

INTENTIONALLY LEFT BLANK.

## List of Figures

<u>Figure</u>		<u>Page</u>
1.	DSC Heat Flow for Isothermal Cure at 110°C and the Associated Degree of Conversion With Time.....	4
2.	Degree of Conversion Versus Time for Increasing Isothermal Cure Temperature .....	5
3.	Plot of $d\alpha/dt$ Versus $\alpha$ for a Typical Isotherm With Associated Fit.....	6
4.	Arrhenius Relationship for the Parameter $k_2$ Used in the Kinetic Model .....	7
5.	Model Predictions for Cure Time Compared to the Experimentally Observed Cure Times.....	7
6.	Typical Temperature Profiles for Induction Heated Adhesive Joints $T_{max} = 150^\circ\text{C}$ (Dotted Line) and $205^\circ\text{C}$ (Solid Line) .....	8
7.	Typical Measured Temperature Profile at Bondline at Steady State by Infrared Thermometry .....	9

INTENTIONALLY LEFT BLANK.

## List of Tables

<u>Table</u>	<u>Page</u>
1. Kinetic Model Parameters.....	6

INTENTIONALLY LEFT BLANK.

# 1. Introduction

The motivation for this work arises from the expanding use and complexity of design of composites in military vehicles and, with that, the increasing need for field expedient and depot-level repair procedures for these components.

A critical issue in adhesive-based repair of composites is the application of sufficient heat and pressure at the bondline. It is highly desirable that thermal generation be localized at the bondline and be evenly distributed (taking into account thermal conductive losses). One method of rapidly applying localized heating at the bondline is induction heating [1].

Electromagnetic induction heating techniques are well known and widely used for metals and alloys. Recently, significant research has been undertaken to adapt induction heating to composites for benefits such as cost and reduced processing times. One of the heating techniques uses hysteresis losses in ferromagnetic particles subjected to high-frequency magnetic fields as the heat-generation mechanism. Another generates heat through joule losses caused by the formation of eddy currents through Faraday's Law. Both of these heating techniques can be applied to the repair of composites through the use of a susceptor material placed at the bondline or through the susceptorless heating of carbon-fiber-based systems [2, 3]. Susceptor layers are used to promote localized uniform heating to produce desired process temperatures in the bondline. When susceptors are used, the remotely located induction coil transfers electromagnetic energy to the susceptor, which in turn, generates thermal energy in the plane of the bondline. These techniques allow rapid heating of the susceptor material and, through thermal conduction, rapid heating of the adjacent adhesive. These methods have traditionally been plagued by nonuniformity of heating in the plane of the bondline. Several techniques have recently been developed [3, 4] that enable uniform heating of the susceptor in the plane of the bondline.

Appropriate process windows are needed for each adhesive system to be used. In this study, eddy-current-based susceptors are formed from electrically conductive meshes and an

epoxy-based adhesive. Room-temperature curing adhesives that are often used in the repair of composites require from days to weeks to achieve full cure. This work establishes a methodology for relating cure cycles to degree of cure predictions for accelerated curing of adhesives for repair. Furthermore, the induction heating is used to accelerate the cure of a room-temperature curing epoxy adhesive placed at composite-to-composite bondline.

## 2. Thermochemical Analysis

In order to maximize the benefits of accelerated cure of adhesives using induction heating, a process window must be established for the adhesives of interest. The process window would then be used to optimize the bonding process in terms of time and temperature. Issues that dictate the process window include cure kinetics, evolution of exotherms, flow and wetting, and thermally induced residual stresses. Adhesive cure is the most dominant of these issues and must be addressed to determine cure time as a function of temperature, as well as ultimate degree of cure. In this study, we have chosen a typical room-temperature curing epoxy for evaluation of accelerated cure properties.

Differential scanning calorimetry (DSC) has been widely used to characterize the cure kinetics of thermosetting polymers including polyesters [5], epoxies [6], vinyl esters, and bismaleimides. Since the heat evolution  $dQ/dt$  measured by the DSC results from the chemical cross-linking reaction, it is possible to relate the heat evolution ( $dQ/dt$ ) to the rate of reaction ( $d\alpha/dt$ ) and the conversion ( $\alpha$ ). This can be accomplished by using the following relationships:

$$\frac{d\alpha}{dt} = \frac{1}{\Delta H_{tot}} \left( \frac{dQ}{dt} \right)_t, \quad (1)$$

$$\frac{d\alpha}{dt} = \frac{1}{\Delta H_{tot}} \int_{t_0}^t \left( \frac{dQ}{dt} \right) dt, \quad (2)$$

where  $\Delta H_{\text{tot}}$  is the total heat of reaction, generally determined by averaging the reaction exotherms measured from several dynamic-temperature DSC runs. Various chemical kinetic models can then be fit using data that are obtained from isothermal DSC experiments.

The mechanistic models of thermoset cure that usually provide a more accurate representation of cross-linking reactions are not generally applicable to complex systems such as formulated adhesives. Since the goal of this work is to provide a process window for accelerated cure, the specific cure mechanisms need not be critically assessed. Alternatively, there are several empirical models that have been successfully used to predict to cure of thermosetting polymers. One popular model was proposed by Kamal and Sourour [7]. Their model (equation [3]) has found widespread acceptance for a number of cross-linking reactions (including epoxies) and will be used to fit the adhesive studied here.

$$\frac{d\alpha}{dt} = (k_1 + k_2\alpha^m)(\alpha_u - \alpha)^n \quad (3)$$


In this expression,  $\alpha$  is the degree of conversion,  $\alpha_u$  is the temperature-dependent maximum conversion,  $k_1$  and  $k_2$  are Arrhenius-type rate constants, and  $m$  and  $n$  are constants usually assumed to sum to 2 but often allowed to vary freely. The  $\alpha_u$  term arises from the fact that the entire heat of reaction is not released during isothermal cure due to the decreased mobility of the polymer chains as cross-linking occurs. By performing a series of isothermal cures, values for the model parameters can be determined and used to predict the cure kinetics of the adhesive.

The material studied here was a two-part epoxy room-temperature-curing paste adhesive from Ciba. It was selected because of our prior experience with the system for composite and metal bonding. Additionally, the manufacturers suggest a 16-hr cure time at room temperature, making it an ideal candidate for accelerated cure studies.


Several (10) dynamic DSC runs were performed to evaluate  $\Delta H_{\text{tot}}$  and the glass transition temperature ( $T_g$ ) of the cured material. Resin and hardener were mixed one to one by weight and

immediately inserted into the DSC (TA Instruments 2908), where they were heated at 10°C/min to 200°C. The resulting cure exotherm was integrated to evaluate the heat of reaction. A second heat of each sample was performed in order to measure the  $T_g$  of the cured material. The average and standard deviation of  $\Delta H_{tot}$  was  $190.5 \pm 10.2$  J/g and  $T_g$  was  $102 \pm 14^\circ\text{C}$ . This value of  $\Delta H_{tot}$  is used in equations (1) and (2) to relate the isothermal heat data to  $\alpha$  and  $d\alpha/dt$ .

Next, isothermal scans were performed at temperatures ranging from 40°C to 150°C. Samples were mixed and placed in the preheated DSC cell. Data were collected until the heat flow returned to the baseline value. The isothermal heat flow was related to  $\alpha$  and  $d\alpha/dt$  using equations (1) and (2). A typical DSC isotherm and the resulting conversion vs. time are shown in Figure 1. Figure 2 shows the general trend of increased conversion and rate of reaction with increasing cure temperature.

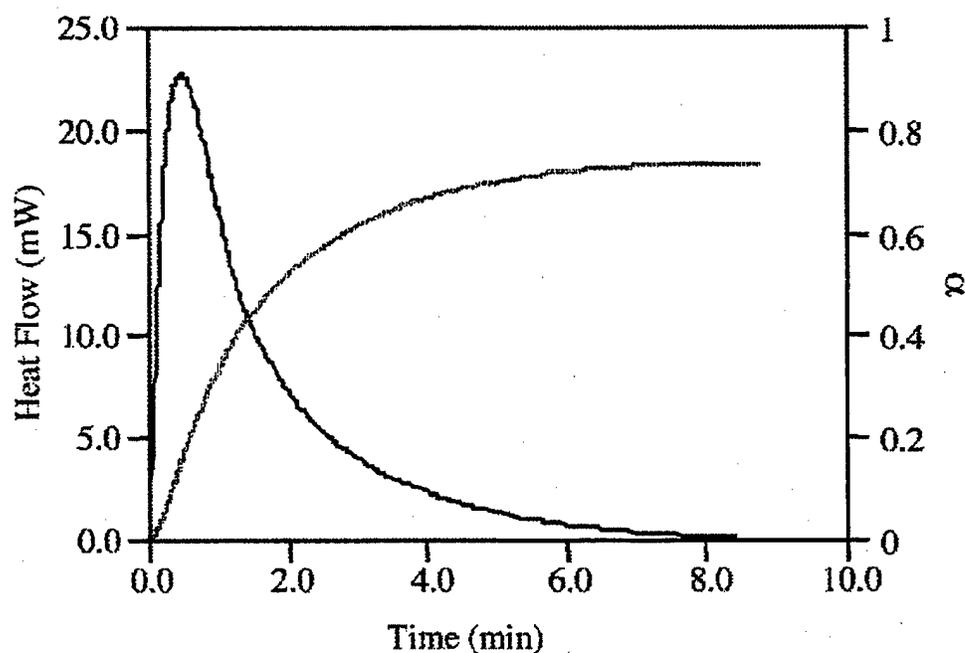

**Figure 1. DSC Heat Flow for Isothermal Cure at 110°C and the Associated Degree of Conversion With Time.**

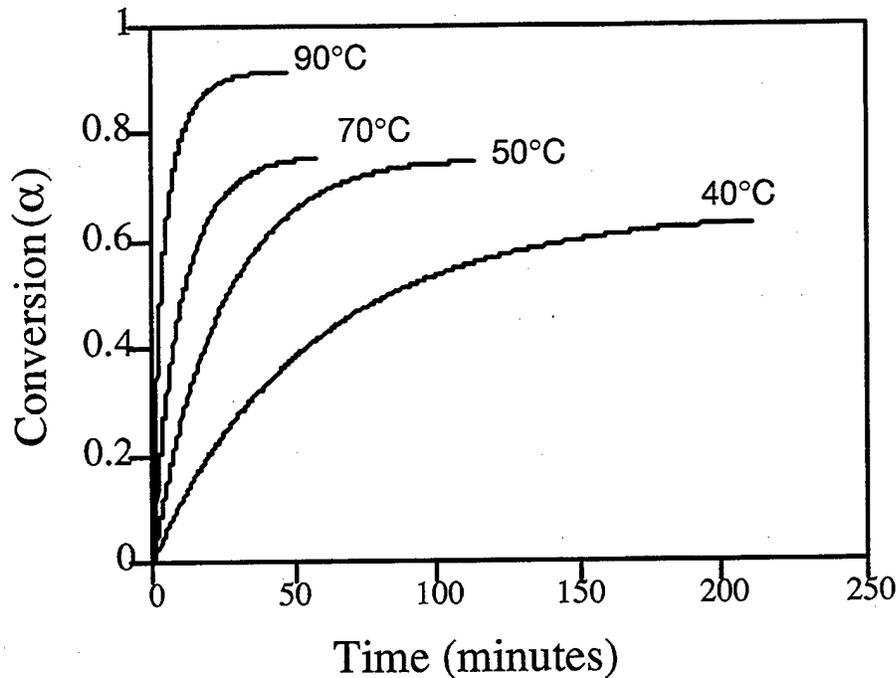


**Figure 2. Degree of Conversion Versus Time for Increasing Isothermal Cure Temperature.**

Equation (3) was then used to fit the  $d\alpha/dt$  versus  $\alpha$  curves for each isotherm. A value of  $\alpha_{\infty}$  was determined from the asymptotic conversion from each test, and  $m$  and  $n$  were permitted to vary freely. Figure 3 shows typical data and the associated fit. Analysis of each experiment produces values for all of the kinetic parameters at that specific temperature. The temperature dependence of  $\alpha_{\infty}$  was found to be linear and is shown in Table 1. The Arrhenius parameters for  $k_2$  were evaluated as shown in Figure 4 (analysis of the data indicated that  $k_1 \approx 0$  regardless of temperature and was subsequently neglected). A summary of all of the parameters is listed in Table 1.

The use of the model will enable prediction of the entire curing process over a wide range of processing temperatures. Initially, however, the prediction of cure time at a specific temperature is of greatest interest to applying induction techniques to accelerate adhesive cure. Here, cure time is defined as the amount of time necessary to reach 98% of  $\alpha_{\infty}$  for each temperature.

**Table 1. Kinetic Model Parameters**

Parameter	Value
m	$0.28 \pm 0.03$
n	$1.67 \pm 0.32$
$k_2(T)$	$9.8 \times 10^6 \exp(-6306/T \text{ [K]})$ (1/min)
$\alpha_u(T)$	$0.62 + 1.3 \times 10^{-3} T \text{ (}^\circ\text{C)}$ ( $40 < T < 150^\circ\text{C}$ )

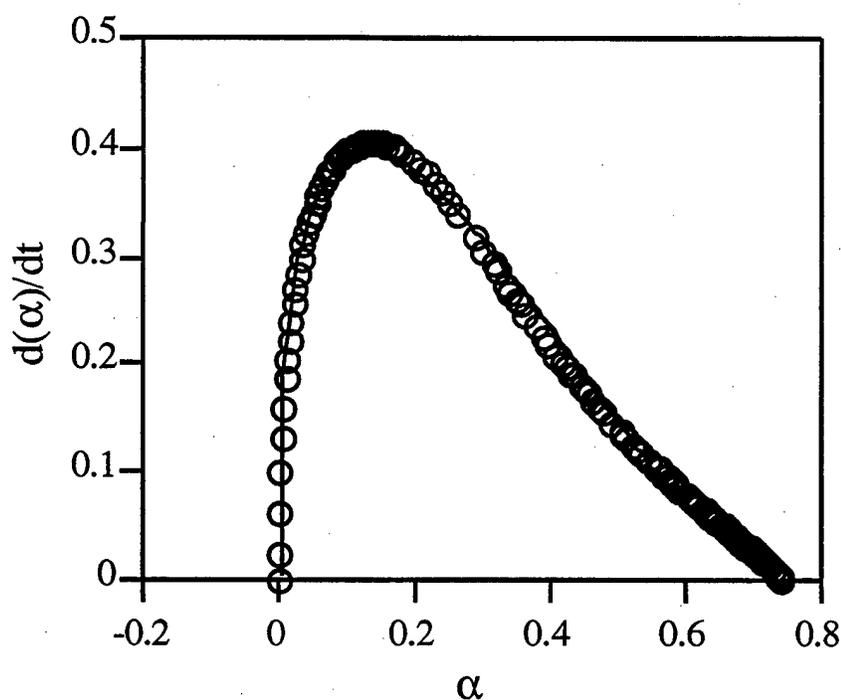

**Figure 3. Plot of  $d\alpha/dt$  Versus  $\alpha$  for a Typical Isotherm With Associated Fit.**

Figure 5 shows model predictions for cure time compared to the experimentally observed cure times. While the agreement is not perfect, it does permit an estimate of minimum cure time at each temperature. These values will be used to determine process windows for the induction assisted accelerated cure of this adhesive.

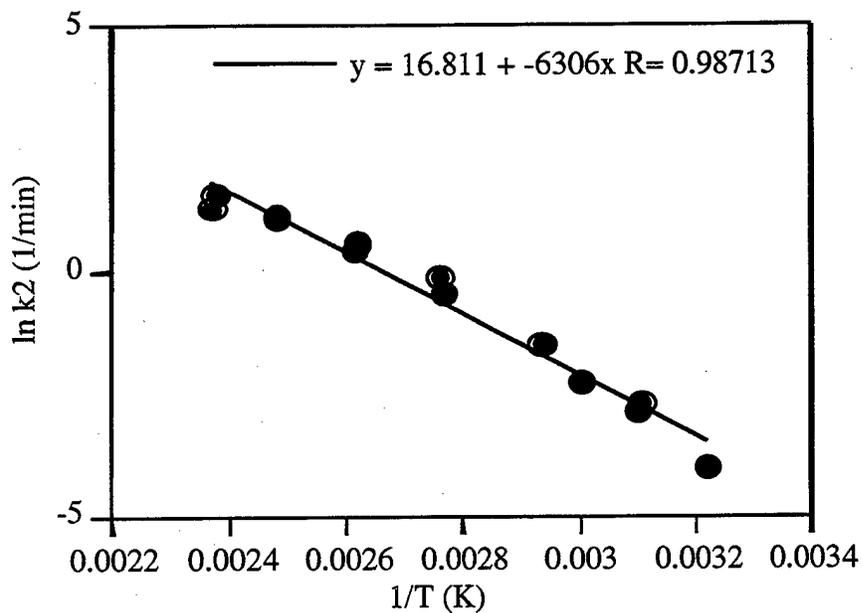


Figure 4. Arrhenius Relationship for the Parameter  $k_2$  Used in the Kinetic Model.


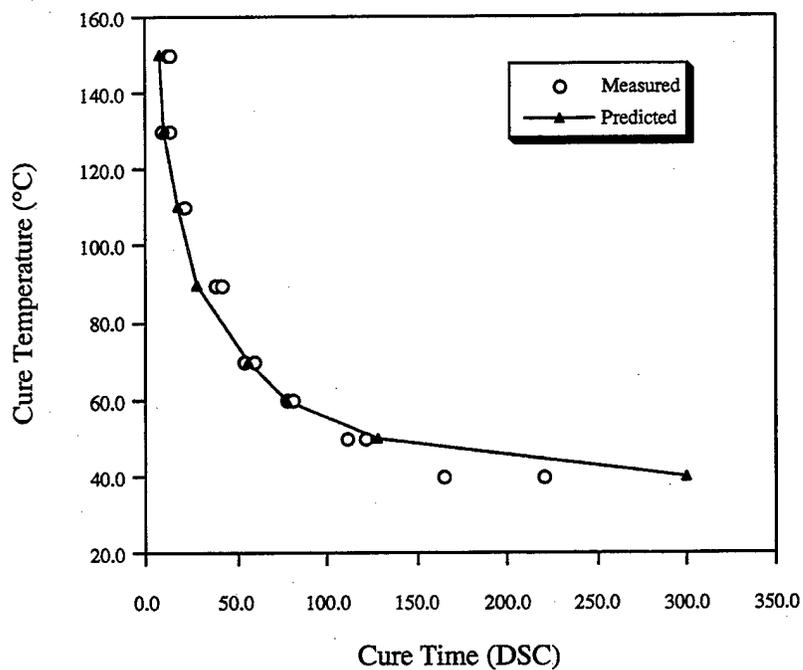


Figure 5. Model Predictions for Cure Time Compared to Experimentally Observed Cure Times.


### 3. Induction Heating

Appropriate cure times for this adhesive can now be selected for any process temperature. This approach was used to select cure cycles for induction heating of the composite adhesive joints. Cure cycles chosen ranged from heating to 90–190°C under vacuum consolidation. Single lap shear specimens were fabricated by induction heating using a stainless steel mesh as the susceptor. An “earmuff” type induction coil was used and it carried currents between 25–40 Amps at a frequency of 284 kHz. Typical temperature profiles during induction heating of lap shear specimens are shown in Figures 6 and 7.

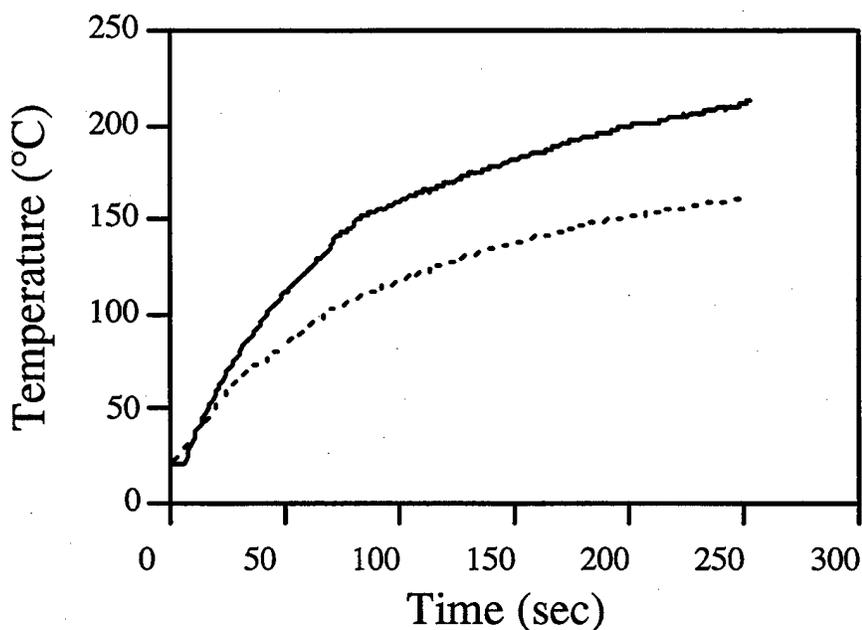

**Figure 6. Typical Temperature Profiles for Induction Heated Adhesive Joints.**  
 $T_{\max} = 150^{\circ}\text{C}$  (Dotted Line) and  $205^{\circ}\text{C}$  (Solid Line).

For baseline comparisons, lap shear specimens were fabricated under oven cure conditions with vacuum consolidation. Lap shear tests showed comparable bond strengths between induction-fabricated specimens and oven-cured specimens.

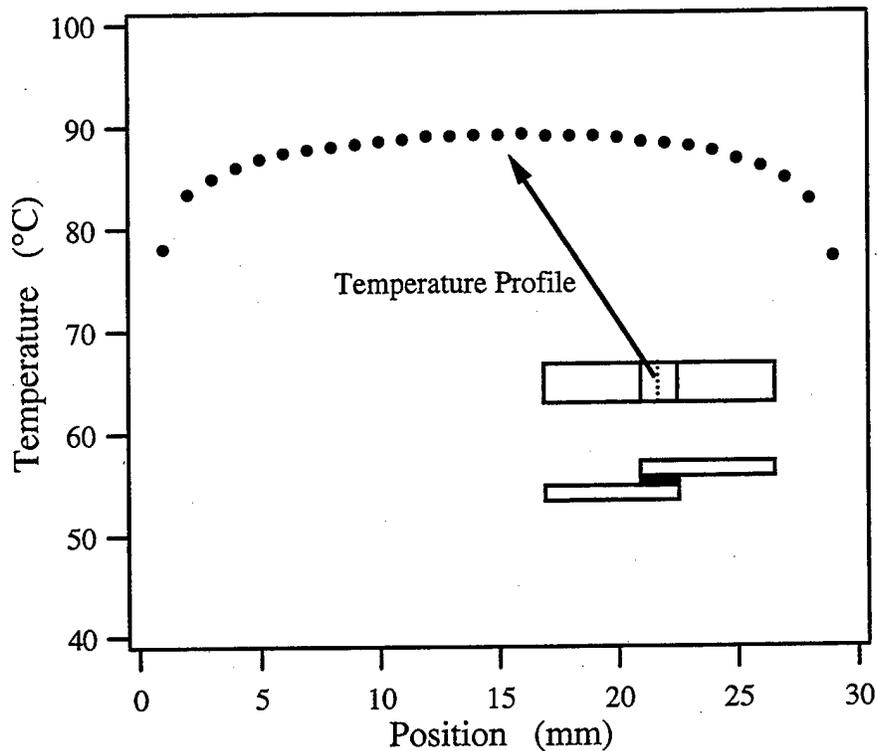

**Figure 7. Typical Measured Temperature Profile at Bondline at Steady State by Infrared Thermometry.**

## 4. Conclusions

This report has described a methodology that can be used to accelerate the cure of room-temperature curing adhesives for rapid repair. Cross-linking reaction kinetics were developed and employed to determine cure cycles for a commercially available epoxy paste adhesive. This paste adhesive was combined with a metal screen to form a susceptor layer for bonding composite adherends. Induction techniques were used to rapidly heat the interface and cure the adhesive. Adhesive taken from the bondline demonstrated full cure at times determined from the kinetic models.

INTENTIONALLY LEFT BLANK.

## 5. References

1. Bourbon, P. E., E. Karamuk, R. C. Don, and J. W. Gillespie, Jr. "Induction Heating for Rehabilitation of Steel Structures Using Composites." *Proceedings of the ASCE Materials Engineering Conference, New Materials and Methods for Repair*, San Diego, CA, 1994.
2. Fink, B. K., R. L. McCullough, and J. W. Gillespie, Jr. "Experiment Verification of Models for Induction Heating of Continuous-Carbon-Fiber Composites." *Polymer Composites*, vol. 17, no. 2, pp. 198-209, 1996.
3. Fink, B. K., and J. W. Gillespie, Jr. Composite Tech Brief No. 108 ver. 97A. University of Delaware, 1997.
4. Yarlagadda, S., B. K. Fink, and J. W. Gillespie, Jr. *Journal of Thermoplastic Composite Materials*. Vol. 11, no. 4, pp. 321-337, July 1998.
5. Lee, D., and C. D. Han. *Polymer Engineering and Science*. Vol. 34, no. 9, pp. 742-794, 1994.
6. Kenny, J. M., A. Apicella, and L. Nicolais. *Polymer Engineering and Science*. Vol. 29, no. 15, pp. 973-983, 1989.
7. Kamal, M. R., and S. Sourour. "Kinetics and Thermal Characterization of Thermoset Cure." *Polymer Engineering and Science*, vol. 13, no. 1, pp. 59-64, 1973.

INTENTIONALLY LEFT BLANK.

NO. OF  
COPIES ORGANIZATION

- 2 DEFENSE TECHNICAL  
INFORMATION CENTER  
DTIC DDA  
8725 JOHN J KINGMAN RD  
STE 0944  
FT BELVOIR VA 22060-6218
- 1 HQDA  
DAMO FDQ  
D SCHMIDT  
400 ARMY PENTAGON  
WASHINGTON DC 20310-0460
- 1 OSD  
OUSD(A&T)/ODDDR&E(R)  
R J TREW  
THE PENTAGON  
WASHINGTON DC 20301-7100
- 1 DPTY CG FOR RDA  
US ARMY MATERIEL CMD  
AMCRDA  
5001 EISENHOWER AVE  
ALEXANDRIA VA 22333-0001
- 1 INST FOR ADVNCD TCHNLGY  
THE UNIV OF TEXAS AT AUSTIN  
PO BOX 202797  
AUSTIN TX 78720-2797
- 1 DARPA  
B KASPAR  
3701 N FAIRFAX DR  
ARLINGTON VA 22203-1714
- 1 NAVAL SURFACE WARFARE CTR  
CODE B07 J PENNELLA  
17320 DAHLGREN RD  
BLDG 1470 RM 1101  
DAHLGREN VA 22448-5100
- 1 US MILITARY ACADEMY  
MATH SCI CTR OF EXCELLENCE  
DEPT OF MATHEMATICAL SCI  
MADN MATH  
THAYER HALL  
WEST POINT NY 10996-1786

NO. OF  
COPIES ORGANIZATION

- 1 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL DD  
J J ROCCHIO  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197
- 1 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL CS AS (RECORDS MGMT)  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145
- 3 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL CI LL  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145
- ABERDEEN PROVING GROUND
- 4 DIR USARL  
AMSRL CI LP (BLDG 305)

NO. OF  
COPIES ORGANIZATION

- 1 DIRECTOR  
USARL  
AMSRL CP CA D SNIDER  
2800 POWDER MILL RD  
ADELPHI MD 20783
- 1 COMMANDER  
USA ARDEC  
AMSTA AR FSE T GORA  
PICATINNY ARSENAL NJ  
07806-5000
- 3 COMMANDER  
USA ARDEC  
AMSTA AR TD  
PICATINNY ARSENAL NJ  
07806-5000
- 5 COMMANDER  
USA TACOM  
AMSTA JSK  
S GOODMAN  
J FLORENCE  
AMSTA TR D  
B RAJU  
L HINOJOSA  
D OSTBERG  
WARREN MI 48397-5000
- 5 PM SADARM  
SFAE GCSS SD  
COL B ELLIS  
M DEVINE  
W DEMASSI  
J PRITCHARD  
S HROWNAK  
PICATINNY ARSENAL NJ  
07806-5000
- 1 COMMANDER  
USA ARDEC  
F MCLAUGHLIN  
PICATINNY ARSENAL NJ  
07806-5000

NO. OF  
COPIES ORGANIZATION

- 5 COMMANDER  
USA ARDEC  
AMSTA AR CCH  
S MUSALLI  
R CARR  
M LUCIANO  
T LOUCEIRO  
PICATINNY ARSENAL NJ  
07806-5000
- 4 COMMANDER  
USA ARDEC  
AMSTA AR (2 CPS)  
E FENNELL (2 CPS)  
PICATINNY ARSENAL NJ  
07806-5000
- 1 COMMANDER  
USA ARDEC  
AMSTA AR CCH P J LUTZ  
PICATINNY ARSENAL NJ  
07806-5000
- 1 COMMANDER  
USA ARDEC  
AMSTA AR FSF T C LIVECCHIA  
PICATINNY ARSENAL NJ  
07806-5000
- 1 COMMANDER  
USA ARDEC  
AMSTA AR QAC T/C C PATEL  
PICATINNY ARSENAL NJ  
07806-5000
- 2 COMMANDER  
USA ARDEC  
AMSTA AR M  
D DEMELLA  
F DIORIO  
PICATINNY ARSENAL NJ  
07806-5000

NO. OF  
COPIES ORGANIZATION

3 COMMANDER  
USA ARDEC  
AMSTA AR FSA  
A WARNASH  
B MACHAK  
M CHIEFA  
PICATINNY ARSENAL NJ  
07806-5000

1 COMMANDER  
SMCWV QAE Q  
B VANINA  
BLDG 44 WATERVLIET ARSENAL  
WATERVLIET NY 12189-4050

1 COMMANDER  
SMCWV SPM  
T MCCLOSKEY  
BLDG 253 WATERVLIET ARSENAL  
WATERVLIET NY 12189-4050

8 DIRECTORECTOR  
BENET LABORATORIES  
AMSTA AR CCB  
J KEANE  
J BATTAGLIA  
J VASILAKIS  
G FFIAR  
V MONTVORI  
G DANDREA  
R HASENBEIN  
AMSTA AR CCB R  
S SOPOK  
WATERVLIET NY 12189-4050

1 COMMANDER  
SMCWV QA QS K INSCO  
WATERVLIET NY 12189-4050

1 COMMANDER  
PRODUCTION BASE MODERN  
ACTY  
USA ARDEC  
AMSMC PBM K  
PICATINNY ARSENAL NJ  
07806-5000

NO. OF  
COPIES ORGANIZATION

1 COMMANDER  
USA BELVOIR RD&E CTR  
STRBE JBC  
FT BELVOIR VA 22060-5606

2 COMMANDER  
USA ARDEC  
AMSTA AR FSB G  
M SCHIKSNIS  
D CARLUCCI  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY COLD REGIONS  
RESEARCH & ENGINEERING CTR  
P DUTTA  
72 LYME RD  
HANVOVER NH 03755

1 DIRECTOR  
USARL  
AMSRL WT L D WOODBURY  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145

1 COMMANDER  
USA MICOM  
AMSMI RD W MCCORKLE  
REDSTONE ARSENAL AL  
35898-5247

1 COMMANDER  
USA MICOM  
AMSMI RD ST P DOYLE  
REDSTONE ARSENAL AL  
35898-5247

1 COMMANDER  
USA MICOM  
AMSMI RD ST CN T VANDIVER  
REDSTONE ARSENAL AL  
35898-5247

2 US ARMY RESEARCH OFFICE  
A CROWSON  
K LOGAN  
PO BOX 12211  
RESEARCH TRIANGLE PARK NC  
27709-2211

NO. OF  
COPIES ORGANIZATION

3 US ARMY RESEARCH OFFICE  
ENGINEERING SCIENCES DIV  
R SINGLETON  
G ANDERSON  
K IYER  
PO BOX 12211  
RESEARCH TRIANGLE PARK NC  
27709-2211

5 PM TMAS  
SFAE GSSC TMA  
COL PAWLICKI  
K KIMKER  
E KOPACZ  
R ROESER  
B DORCY  
PICATINNY ARSENAL NJ  
07806-5000

1 PM TMAS  
SFAE GSSC TMA SMD  
R KOWALSKI  
PICATINNY ARSENAL NJ  
07806-5000

3 PEO FIELD ARTILLERY SYSTEMS  
SFAE FAS PM  
H GOLDMAN  
T MCWILLIAMS  
T LINDSAY  
PICATINNY ARSENAL NJ  
07806-5000

2 PM CRUSADER  
G DELCOCO  
J SHIELDS  
PICATINNY ARSENAL NJ  
07806-5000

3 NASA LANGLEY RESEARCH CTR  
MS 266  
AMSRL VS  
W ELBER  
F BARTLETT JR  
C DAVILA  
HAMPTON VA 23681-0001

NO. OF  
COPIES ORGANIZATION

2 COMMANDER  
DARPA  
S WAX  
2701 N FAIRFAX DR  
ARLINGTON VA 22203-1714

6 COMMANDER  
WRIGHT PATTERSON AFB  
WL FIV  
A MAYER  
WL MLBM  
S DONALDSON  
T BENSON-TOLLE  
C BROWNING  
J MCCOY  
F ABRAMS  
2941 P ST STE 1  
DAYTON OH 45433

2 NAVAL SURFACE WARFARE CTR  
DAHLGREN DIV CODE G06  
R HUBBARD CODE G 33 C  
DAHLGREN VA 22448

1 NAVAL RESEARCH LAB  
I WOLOCK CODE 6383  
WASHINGTON DC 20375-5000

1 OFFICE OF NAVAL RESEARCH  
MECH DIV  
Y RAJAPAKSE CODE 1132SM  
ARLINGTON VA 22271

1 NAVAL SURFACE WARFARE CTR  
CRANE DIV  
M JOHNSON CODE 20H4  
LOUISVILLE KY 40214-5245

1 DAVID TAYLOR RESEARCH CTR  
SHIP STRUCTURES &  
PROTECTION DEPT  
J CORRADO CODE 1702  
BETHESDA MD 20084

2 DAVID TAYLOR RESEARCH CTR  
R ROCKWELL  
W PHYLLAIER  
BETHESDA MD 20054-5000

NO. OF  
COPIES ORGANIZATION

1 DEFENSE NUCLEAR AGENCY  
INNOVATIVE CONCEPTS DIV  
R ROHR  
6801 TELEGRAPH RD  
ALEXANDRIA VA 22310-3398

1 EXPEDITIONARY WARFARE  
DIV N85 F SHOUP  
2000 NAVY PENTAGON  
WASHINGTON DC 20350-2000

1 OFFICE OF NAVAL RESEARCH  
D SIEGEL 351  
800 N QUINCY ST  
ARLINGTON VA 22217-5660

7 NAVAL SURFACE WARFARE CTR  
J H FRANCIS CODE G30  
D WILSON CODE G32  
R D COOPER CODE G32  
E ROWE CODE G33  
T DURAN CODE G33  
L DE SIMONE CODE G33  
DAHLGREN VA 22448

1 COMMANDER  
NAVAL SEA SYSTEM CMD  
P LIESE  
2351 JEFFERSON DAVIS HIGHWAY  
ARLINGTON VA 22242-5160

1 NAVAL SURFACE WARFARE CTR  
M E LACY CODE B02  
17320 DAHLGREN RD  
DAHLGREN VA 22448

1 NAVAL WARFARE SURFACE CTR  
TECH LIBRARY CODE 323  
17320 DAHLGREN RD  
DAHLGREN VA 22448

4 DIR  
LLNL  
R CHRISTENSEN  
S DETERESA  
F MAGMESS  
M FINGER  
PO BOX 808  
LIVERMORE CA 94550

NO. OF  
COPIES ORGANIZATION

2 DIRECTOR  
LLNL  
F ADDESSIO MS B216  
J REPPA MS F668  
PO BOX 1633  
LOS ALAMOS NM 87545

3 UNITED DEFENSE LP  
4800 EAST RIVER DR  
P JANKE MS170  
T GIOVANETTI MS236  
B VAN WYK MS 389  
MINNEAPOLIS MN 55421-1498

4 DIRECTOR  
SANDIA NATIONAL LAB  
APPLIED MECHANICS DEPT  
DIV 8241  
W KAWAHARA  
K PERANO  
D DAWSON  
P NIELAN  
PO BOX 969  
LIVERMORE CA 94550-0096

1 BATTELLE  
C R HARGREAVES  
505 KNIGHT AVE  
COLUMBUS OH 43201-2681

1 PACIFIC NORTHWEST LAB  
M SMITH  
PO BOX 999  
RICHLAND WA 99352

1 LLNL  
M MURPHY  
PO BOX 808 L 282  
LIVERMORE CA 94550

10 UNIV OF DELAWARE  
CTR FOR COMPOSITE MATERIALS  
J GILLESPIE  
201 SPENCER LAB  
NEWARK DE 19716

NO. OF  
COPIES ORGANIZATION

2 THE U OF TEXAS AT AUSTIN  
CTR ELECTROMECHANICS  
A WALLIS  
J KITZMILLER  
10100 BURNET RD  
AUSTIN TX 78758-4497

1 AAI CORPORATION  
T G STASTNY  
PO BOX 126  
HUNT VALLEY MD 21030-0126

1 SAIC  
D DAKIN  
2200 POWELL ST STE 1090  
EMERYVILLE CA 94608

1 SAIC  
M PALMER  
2109 AIR PARK RD S E  
ALBUQUERQUE NM 87106

1 SAIC  
R ACEBAL  
1225 JOHNSON FERRY RD STE 100  
MARIETTA GA 30068

1 SAIC  
G CHRYSSOMALLIS  
3800 W 80TH ST STE 1090  
BLOOMINGTON MN 55431

6 ALLIANT TECHSYSTEMS INC  
C CANDLAND  
R BECKER  
L LEE  
R LONG  
D KAMDAR  
G KASSUELKE  
600 2ND ST NE  
HOPKINS MN 55343-8367

1 CUSTOM ANALYTICAL ENGR  
SYS INC  
A ALEXANDER  
13000 TENSOR LANE NE  
FLINTSTONE MD 21530

NO. OF  
COPIES ORGANIZATION

1 NOESIS INC  
1110 N GLEBE RD STE 250  
ARLINGTON VA 22201-4795

1 ARROW TECH ASSO  
1233 SHELBURNE RD STE D 8  
SOUTH BURLINGTON VT  
05403-7700

5 GEN CORP AEROJET  
D PILLASCH  
T COULTER  
C FLYNN  
D RUBAREZUL  
M GREINER  
1100 WEST HOLLYVALE ST  
AZUSA CA 91702-0296

1 NIST  
STRUCTURE & MECHANICS GRP  
POLYMER DIV POLYMERS RM A209  
G MCKENNA  
GAITHERSBURG MD 20899

1 GENERAL DYNAMICS LAND  
SYSTEM DIVISION  
D BARTLE  
PO BOX 1901  
WARREN MI 48090

4 INSTITUTE FOR ADVANCED  
TECHNOLOGY  
H FAIR  
P SULLIVAN  
W REINECKE  
I MCNAB  
4030 2 W BRAKER LN  
AUSTIN TX 78759

1 PM ADVANCED CONCEPTS  
LORAL VOUGHT SYSTEMS  
J TAYLOR MS WT 21  
PO BOX 650003  
DALLAS TX 76265-0003

NO. OF  
COPIES ORGANIZATION

2 UNITED DEFENSE LP  
P PARA  
G THOMASA  
1107 COLEMAN AVE BOX 367  
SAN JOSE CA 95103

1 MARINE CORPS SYSTEMS CMD  
PM GROUND WPNS  
COL R OWEN  
2083 BARNETT AVE STE 315  
QUANTICO VA 22134-5000

1 OFFICE OF NAVAL RES  
J KELLY  
800 NORTH QUINCEY ST  
ARLINGTON VA 22217-5000

1 NAVSEE OJRI  
G CAMPONESCHI  
2351 JEFFERSON DAVIS HWY  
ARLINGTON VA 22242-5160

1 USAF  
WL MLS O L A HAKIM  
5525 BAILEY LOOP 243E  
MCCLELLAN AFB CA 55552

1 NASA LANGLEY  
J MASTERS MS 389  
HAMPTON VA 23662-5225

2 FAA TECH CTR  
D OPLINGER AAR 431  
P SHYPRYKEVICH AAR 431  
ATLANTIC CITY NJ 08405

1 NASA LANGLEY RC  
CC POE MS 188E  
NEWPORT NEWS VA 23608

1 USAF  
WL MLBC  
E SHINN  
2941 PST STE 1  
WRIGHT PATTERSON AFB OH  
45433-7750

NO. OF  
COPIES ORGANIZATION

4 NIST  
POLYMERS DIVISION  
R PARNAS  
J DUNKERS  
M VANLANDINGHAM  
D HUNSTON  
GAITHERSBURG MD 20899

1 OAK RIDGE NATIONAL LAB  
A WERESZCZAK  
BLDG 4515 MS 6069  
PO BOX 2008  
OAKRIDGE TN 37831-6064

1 COMMANDER  
USA ARDEC  
INDUSTRIAL ECOLOGY CTR  
T SACHAR  
BLDG 172  
PICATINNY ARSENAL NJ  
07806-5000

1 COMMANDER  
USA ATCOM  
AVIATION APPLIED TECH DIR  
J SCHUCK  
FT EUSTIS VA 23604

1 COMMANDER  
USA ARDEC  
AMSTA AR SRE  
D YEE  
PICATINNY ARSENAL NJ  
07806-5000

7 COMMANDER  
USA ARDEC  
AMSTA AR CCH B  
B KONRAD  
E RIVERA  
G EUSTICE  
S PATEL  
G WAGNECZ  
R SAYER  
F CHANG  
BLDG 65  
PICATINNY ARSENAL NJ  
07806-5000

NO. OF  
COPIES ORGANIZATION

NO. OF  
COPIES ORGANIZATION

1 COMMANDER  
USA ARDEC  
AMSTA AR QAC  
T D RIGOGLIOSO  
BLDG 354 M829E3 IPT  
PICATINNY ARSENAL NJ  
07806-5000

5 DIRECTOR  
USARL  
AMSRL WM MB  
A ABRAHAMIAN  
M BERMAN  
A FRYDMAN  
T LI  
W MCINTOSH  
E SZYMANSKI  
2800 POWDER MILL RD  
ADELPHI MD 20783

ABERDEEN PROVING GROUND

67 DIR USARL  
AMSRL CI  
AMSRL CI C  
W STUREK  
AMSRL CI CB  
R KASTE  
AMSRL CI S  
A MARK  
AMSRL SL B  
AMSRL SL BA  
AMSRL SL BE  
D BELY  
AMSRL WM B  
A HORST  
E SCHMIDT  
AMSRL WM BE  
G WREN  
C LEVERITT  
D KOOKER  
AMSRL WM BC  
P PLOSTINS  
D LYON  
J NEWILL

AMSRL WM BD  
S WILKERSON  
R FIFER  
B FORCH  
R PESCE RODRIGUEZ  
B RICE  
AMSRL WM  
D VIECHNICKI  
G HAGNAUER  
J MCCAULEY  
AMSRL WM MA  
R SHUFORD  
S MCKNIGHT  
L GHIORSE  
AMSRL WM MB  
V HARIK  
J SANDS  
W DRYSDALE  
J BENDER  
T BLANAS  
T BOGETTI  
R BOSSOLI  
L BURTON  
S CORNELISON  
P DEHMER  
R DOOLEY  
B FINK  
G GAZONAS  
S GHIORSE  
D GRANVILLE  
D HOPKINS  
C HOPPEL  
D HENRY  
R KASTE  
M LEADORE  
R LIEB  
E RIGAS  
D SPAGNUOLO  
W SPURGEON  
J TZENG  
AMSRL WM MC  
J BEATTY  
AMSRL WM MD  
W ROY  
AMSRL WM T  
B BURNS

NO. OF  
COPIES ORGANIZATION

ABERDEEN PROVING GROUND (CONT)

AMSRL WM TA  
W GILlich  
E RAPACKI  
T HAVEL  
AMSRL WM TC  
R COATES  
W DE ROSSET  
AMSRL WM TD  
W BRUCHEY  
A D GUPTA  
AMSRL WM BB  
H ROGERS  
AMSRL WM BA  
F BRANDON  
W D AMICO  
AMSRL WM BR  
J BORNSTEIN  
AMSRL WM TE  
A NIILER  
AMSRL WM BF  
J LACETERA

INTENTIONALLY LEFT BLANK.

<b>REPORT DOCUMENTATION PAGE</b>			<i>Form Approved OMB No. 0704-0188</i>	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE October 1999	3. REPORT TYPE AND DATES COVERED Final, Jan 98 - Feb 99	
4. TITLE AND SUBTITLE  Accelerated Adhesive Curing for Induction-Based Repair of Composites			5. FUNDING NUMBERS  AH42	
6. AUTHOR(S) Steven H. McKnight, Bruce K. Fink, Sean Wells,* Shridhar Yarlagadda,* and John W. Gillespie Jr.*				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)  U.S. Army Research Laboratory ATTN: AMSRL-WM-MA Aberdeen Proving Ground, MD 21005-5069			8. PERFORMING ORGANIZATION REPORT NUMBER  ARL-TR-2103	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES)			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES * University of Delaware, Newark, DE 19716				
12a. DISTRIBUTION/AVAILABILITY STATEMENT  Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A methodology for accelerated curing of commercially available room-temperature curing paste adhesives is outlined. Cure kinetics of the adhesive were studied by thermochemical analysis, and degree of cure was related to processing parameters and cure cycles. Increasing the cure temperature to 100°C reduced the cure time from 16 hr to approximately 15 min for 98% cure. Induction-heating techniques were used to demonstrate rapid heating of adhesives at the bondline for lap shear specimens.				
14. SUBJECT TERMS induction heating, adhesives, accelerated cure, adhesive bonding, repair, composite, degree of cure			15. NUMBER OF PAGES 26	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

INTENTIONALLY LEFT BLANK.

## USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number/Author ARL-TR-2103 (McKnight) Date of Report October 1999

2. Date Report Received \_\_\_\_\_

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

CURRENT  
ADDRESS

\_\_\_\_\_  
Organization

\_\_\_\_\_  
Name

\_\_\_\_\_  
E-mail Name

\_\_\_\_\_  
Street or P.O. Box No.

\_\_\_\_\_  
City, State, Zip Code

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

OLD  
ADDRESS

\_\_\_\_\_  
Organization

\_\_\_\_\_  
Name

\_\_\_\_\_  
Street or P.O. Box No.

\_\_\_\_\_  
City, State, Zip Code

(Remove this sheet, fold as indicated, tape closed, and mail.)  
**(DO NOT STAPLE)**