

# Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5066

---

---

ARL-MR-477

May 2000

## HSTSS Battery Development for Missile and Ballistic Telemetry Applications

Lawrence W. Burke

Weapons and Materials Research Directorate, ARL

Edward Bukowski

Dynamic Science Incorporated

Colin Newnham and Neil Scholey

Ultralife Batteries (UK), Ltd.

William Hoge and Zhiyaun Ye

Ultralife Batteries, Inc.

---

---

## Abstract

---

The rapid growth in portable and wireless communication products has brought valuable advancements in battery technology. No longer is a battery restricted to a metal container in cylindrical or prismatic format. Today's batteries (both primary and secondary) can be constructed in thin sheets and sealed in foil/plastic laminate packages. Along with improvements in energy density, temperature performance, and environmentally friendly materials, these batteries offer greater packaging options at a significantly lower development cost. Under the Hardened Subminiature Telemetry and Sensor System (HSTSS) Program, these battery technologies have been further developed for high-g telemetry applications. Both rechargeable solid-state lithium-ion polymer and primary lithium manganese dioxide (Li/MnO<sub>2</sub>) batteries are being developed in conjunction with Ultralife Batteries, Inc. Prototypes of both chemistries have been successfully tested in a ballistic environment, while providing high constant rates of discharge, which is essential to these types of applications. Electrical performance and environmental data are reported.

## **Acknowledgments**

The authors would like to acknowledge Messrs. Jonah Faust, Dave Hepner, Peter Muller, Brad Davis, Mike Hollis, Eric Irwin, and Charles Mitchell of the U.S. Army Research Laboratory (ARL) for both their ground- and flight-testing support.

INTENTIONALLY LEFT BLANK.

# Table of Contents

	<u>Page</u>
<b>Acknowledgments</b> .....	iii
<b>List of Figures</b> .....	vii
<b>List of Tables</b> .....	ix
<b>1. Introduction</b> .....	1
<b>2. Background</b> .....	1
<b>3. Rechargeable Solid Polymer Lithium-Ion Technology</b> .....	2
<b>4. Li/MnO<sub>2</sub> Thin Cell Technology</b> .....	3
<b>5. Applications</b> .....	4
<b>6. Artillery Nose Fuse Battery</b> .....	5
<b>7. Solid Polymer Lithium-Ion Nose Fuse Battery</b> .....	5
<b>8. Primary Li/MnO<sub>2</sub> Nose Fuse Battery</b> .....	7
<b>9. KE Projectile Battery</b> .....	8
<b>10. 2.75-in Rocket Battery</b> .....	11
<b>11. Conclusion</b> .....	13
<b>12. References</b> .....	15
<b>Distribution List</b> .....	17
<b>Report Documentation Page</b> .....	23

**INTENTIONALLY LEFT BLANK.**

## List of Figures

<u>Figure</u>	<u>Page</u>
1. Schematic of a Lithium-Ion Polymer Cell Structure.....	3
2. Comparison of Energy Densities for Various Prismatic Battery Chemistries .....	4
3. Typical Cells Constructed Using Thin Cell Technology .....	4
4. Typical Artillery Nose Fuse Instrumentation System .....	5
5. Lithium-Ion Nose Fuse Battery.....	6
6. Lithium-Ion Cell Discharge at 150 mA.....	6
7. Shock Testing of a 16-V Lithium-Ion Nose Fuse Battery .....	7
8. Spin Testing of a 16-V Lithium-Ion Nose Fuse Battery .....	7
9. Li/MnO <sub>2</sub> Nose Fuse Battery Discharge at 250 mA.....	8
10. Unencapsulated and Encapsulated Li/MnO <sub>2</sub> Nose Fuse Batteries.....	8
11. Spin Test of a 24-V Li/MnO <sub>2</sub> Nose Fuse Battery .....	9
12. Flight Data of an Li/MnO <sub>2</sub> Nose Fuse Battery on an M483 Projectile .....	9
13. Li/MnO <sub>2</sub> Tracer-Well Battery Discharge at 150 mA .....	10
14. Package Design of an M735 105-mm KE Projectile .....	10
15. Encapsulated Tracer-Well Assembly and Unencapsulated Tracer-Well Batteries ...	10
16. 2.75-in Rocket Battery .....	12
17. Li/MnO <sub>2</sub> 2.75-in Rocket Battery With 12 25-mA Discharges and a 700-mA Discharge.....	12
18. Exploded View of an Li/MnO <sub>2</sub> 2.75-in Rocket Battery Discharge at 700 mA.....	12

INTENTIONALLY LEFT BLANK.

## List of Tables

<u>Table</u>		Page
1.	Specifications for a Solid Polymer Lithium-Ion Nose Fuse Battery.....	6
2.	Specifications for a Tracer-Well Battery.....	9
3.	Specifications for a 2.75-in Rocket Battery.....	11

INTENTIONALLY LEFT BLANK.

# 1. Introduction

The Hardened Subminiature Telemetry and Sensor System (HSTSS) Program is currently developing state-of-the-art telemetry components and subsystems for missile and ballistic applications. The goal of the program is to provide lower cost, user-configurable telemetry components for making in-flight measurements of smart munitions. Along with these telemetry components comes the need for a power source, which cannot only fit into the constrained dimensions available on a munition but also perform under extreme conditions such as high-g acceleration and spin. The HSTSS Program has identified recent advancements in battery technology, which will provide possible power sources for future telemetry systems. Development with Ultralife Batteries is ongoing in an effort to adapt their commercial technologies to the high-g military environment. This paper reviews the current status of these developments, the battery technologies, battery designs, and test results.

## 2. Background

An onboard telemetry power source usually consists of several cells connected together to give the desired voltage and capacity. Typically, these batteries fall into the following categories: secondary (rechargeable), primary (nonrechargeable), and reserve (activated upon some condition, i.e., spin). These batteries are of fixed dimension, are comprised of free electrolyte, and are often large when compared to other telemetry components. Because these batteries are rigid, the designer has very little flexibility in the package design. If moments of inertia and center of gravity are to be preserved, the job becomes even more challenging. In the past, special order batteries that would meet these requirements have proved to be cost prohibitive.

Under the HSTSS Program, both secondary solid polymer electrolyte lithium-ion batteries and primary lithium manganese dioxide (Li/MnO<sub>2</sub>) batteries are being developed for ballistic applications. Both technologies are available in conformal foil/plastic laminate packaging and

can be rapidly prototyped for most applications. These technologies are being proposed for applications where power requirements are not extreme but where space and packaging flexibility is of major concern. It is expected that these technologies will provide the telemetry engineer with an affordable and reliable power source, while allowing more flexibility in the system package design.

The HSTSS Program started evaluating these technologies nearly 5 yr ago, while under the test technology and demonstration phase of the program. During this period, numerous development contracts have been executed. The early contracts focused on survivability issues of the basic cell structure under high setback and radial accelerations. Research has also been conducted in the areas of assembly and fabrication techniques of multicell batteries and improved energy densities and temperature performance. Basic cell structures of both chemistries have been shown to survive accelerations in excess of 80,000 g's. These works are summarized in Burke, Faulstich, and Newnham [1] and Burke et al. [2, 3]. Since initial evaluations, the technology has matured dramatically. Currently, the HSTSS Program is building demonstration batteries for several munition applications in both the lithium-ion and Li/MnO<sub>2</sub> chemistries.

### **3. Rechargeable Solid Polymer Lithium-Ion Technology**

Lithium-ion technology was first commercialized in 1991 by Sony and is based on a carbon anode, a lithium metal oxide cathode, and a liquid electrolyte. However, since these early liquid-based systems had the need to contain the liquid in a metal can, there were limitations to the applications in which liquid-based systems could be used. In order to overcome these limitations, Ultralife Batteries (and others) has developed a solid polymer lithium-ion battery. In place of the conventional liquid electrolyte is a polymer that functions both as a transporting medium for the lithium ions and an electronic insulator that prevents the electrodes from shorting. By incorporating a lithium salt and organic plasticizers into the polymer matrix, high ionic conductivity, good electrochemical stability, and high mechanical strength have been obtained. A basic schematic of the cell construction is shown in Figure 1.


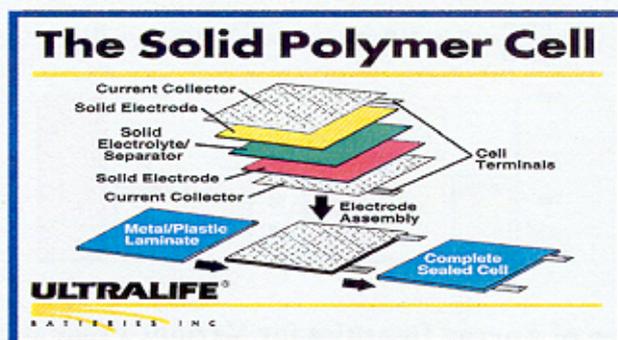


Figure 1. Schematic of a Lithium-Ion Polymer Cell Structure.


The batteries are fabricated by laminating the electrode and electrolyte layers with the proper application of heat and pressure. The whole assembly is contained within a foil laminate package sealed by conventional heat-bonding methods. Due to the nature of the electrode layers, and the use of foil laminate packaging material, the polymer battery can be configured in a variety of thin prismatic shapes, while maintaining a higher energy density than other prismatic battery chemistries (Figure 2). The foil laminate package also allows the cells to be made as thin as 3 mm, compared to 6 mm, when a metal casing is used. Depending on the configuration, energy densities as high as 130 Wh/kg can be achieved, while maintaining a high cycle life (>500 cycles to 80% of initial capacity). The polymer battery is capable of being fully charged in approximately 2.5 hr and can be continuously discharged at 2C (rated capacity), with very little loss in capacity. Higher constant currents can also be sustained, but larger losses in capacity will occur. As a result of using a polymer electrolyte, and the absence of lithium metal, the cells are extremely tolerant of abuse when subjected to short-circuit, overcharge, and forced-discharge conditions. The cells meet the CSA950, IEC950, and UL1950 safety standards for mobile computing systems and pass all Japan Storage Battery Association safety tests.

#### 4. Li/MnO<sub>2</sub> Thin Cell Technology

Ultralife Batteries has developed a line of thin, flat, primary Li/MnO<sub>2</sub> batteries called "Thin Cell." Like the solid polymer lithium-ion cells, these cells are packaged in a foil laminate and can be rapidly prototyped in a range of sizes and shapes, as seen in Figure 3. The internal construction of the Thin Cell is a wound solid cathode structure. However, the electrode stack is

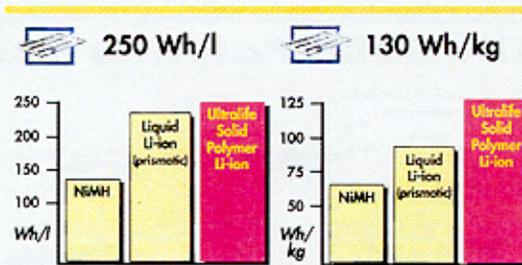

**Figure 2. Comparison of Energy Densities for Various Prismatic Battery Chemistries.**

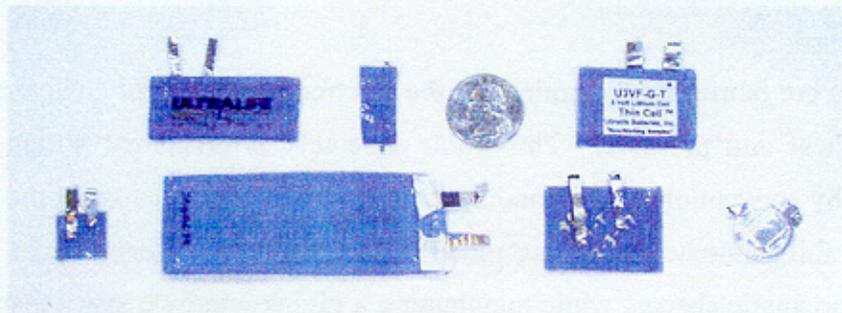

**Figure 3. Typical Cells Constructed Using Thin Cell Technology.**

made thinner and the number of winds is increased in order to increase the surface area and battery performance under high current loads, as compared to commercial cylindrical batteries of this type. The electrode stack can be made as thin as 0.2 mm. Power densities of 500 W/liter (or 250 W/kg) have been demonstrated. Recently, optimization of the electrolyte composition has improved the performance of the cells over the temperature range of  $-20^{\circ}\text{C}$  to  $+70^{\circ}\text{C}$ . The Thin Cell technology is proposed for applications not requiring rechargeability, but needing a greater energy density and package flexibility than existing primary batteries.

## 5. Applications

To further qualify these technologies for ballistic applications, Ultralife Batteries has been contracted by the HSTSS Program to build batteries for actual munition instrumentation systems. Batteries for artillery, rocket, and kinetic energy (KE) munitions are currently being built and are reviewed in the remaining sections.

## 6. Artillery Nose Fuse Battery

One of the most common applications for ballistic instrumentation is the artillery nose fuse (Figure 4). If given the entire fuse cavity, the volume available for an instrumentation package is roughly 147 cm<sup>3</sup>. An artillery projectile can experience setback accelerations as high as 30,000 g's and spin rates up to 300 rps, yielding radial accelerations as high as 25,000 g's, depending on payload location. Both maximum acceleration and spin are achieved in less than 15 ms. The range of a typical artillery projectile is 20 km.

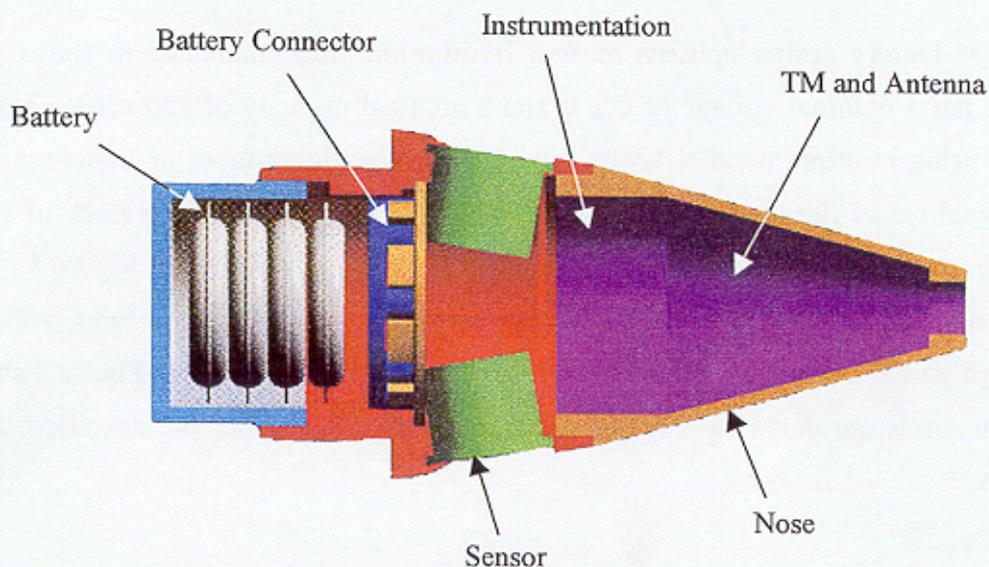


Figure 4. Typical Artillery Nose Fuse Instrumentation System.


## 7. Solid Polymer Lithium-Ion Nose Fuse Battery

A solid polymer lithium-ion nose fuse battery is being developed for projectile test and evaluation applications. The battery is to be located in the rear of the nose fuse cavity, as shown in Figure 4. The specifications for this battery are summarized in Table 1.


**Table 1. Specifications for a Solid Polymer Lithium-Ion Nose Fuse Battery**

Battery Type	Rechargeable Solid Polymer Lithium Ion
Dimension (Outside Diameter × Height)	37.0 mm × 37.0 mm
Minimum Voltage	12.3 V
Maximum Voltage	16.8 V
Constant Current Drain	150 mA
Minimum Duration	30 min (to Minimum Voltage)
Shock Survivability	30,000 g's
Spin Rate	300 rps
Operational Temperature	0° C to +50° C

The nose fuse battery design consists of four lithium-ion cells connected in series. Each disk-shaped cell has a nominal voltage of 4.2 V and a nominal capacity of 120 mAh. The cells are constructed using multiple parallel layers, which minimize the number of interconnections and prevent movement of the electrode assembly within the housing [3]. The stack of cells is then inserted into a prefabricated mold and encapsulated, as shown in Figure 5. This arrangement ensures the survivability of the battery at high-g forces and spin rates, while still providing enough power to meet the electrical requirements of the application. Figure 6 shows a typical electrical discharge curve of a single 4.2-V nose fuse cell under the specified current drain of 150 mA.

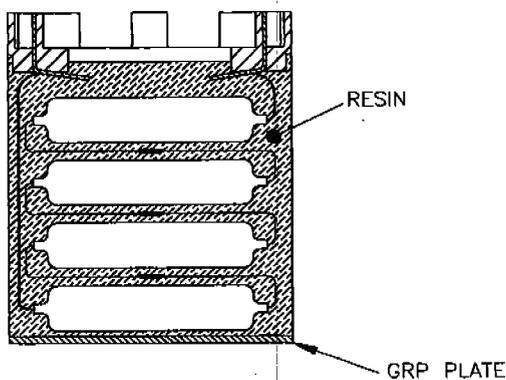


**Figure 5. Lithium-Ion Nose Fuse Battery.**

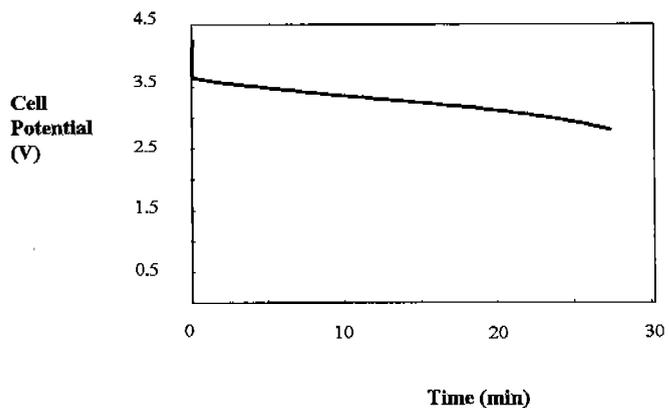

**Figure 6. Lithium-Ion Cell Discharge at 150 mA.**


Single cells of this type have been successfully shock-tested to over 30,000 g's, while under load, and up to 100,000 g's, with no load [2]. To date, only prototype batteries have been supplied for environmental testing. Initial shock table testing of these batteries, while under load, showed a small reduction in the battery voltage due to shock (Figure 7). Post-analysis of the tested batteries indicated a possible movement of the cell structure inside the foil package. To correct this problem, the packaging process has been modified to provide a tighter and more efficient package. Initial spin testing was performed up to 300 rps and showed no voltage dropout (Figure 8).

Ultralife Lithium-Ion Nose Fuse Battery No. 003 - shock no. 1 at 25-mA load

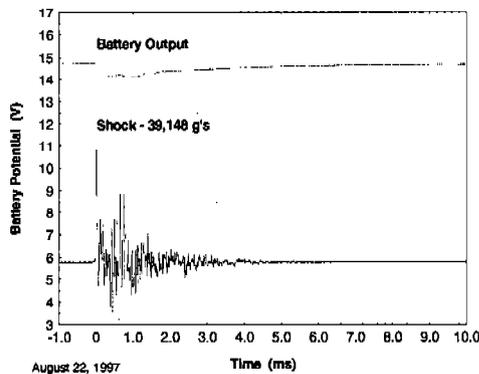

**Figure 7. Shock Testing of a 16-V Lithium-Ion Nose Fuse Battery.**


Ultralife Lithium-Ion Nose Fuse Battery No. 003 - spin no. 2 at 25-mA load

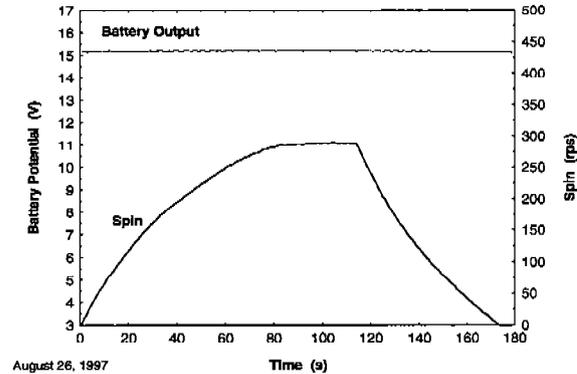


**Figure 8. Spin Testing of a 16-V Lithium-Ion Nose Fuse Battery.**

## 8. Primary Li/MnO<sub>2</sub> Nose Fuse Battery

A primary Li/MnO<sub>2</sub> nose fuse battery has been built for applications requiring a higher rate of discharge. The battery has been designed to fit into the same cavity and meet the same specifications as described in Table 1, but it provides more current (250 mA) over a -20° C to +70° C temperature range (Figure 9). The battery design consists of eight square-shaped cells. These cells are constructed using a solid winding process that employs a very thin electrode material (0.152-mm cathode and 0.076-mm anode). Each cell has a nominal voltage of 3.0 V and a nominal capacity of 166 mAh. The cells are connected in series and encapsulated to ensure high-g force and spin survivability (Figure 10).

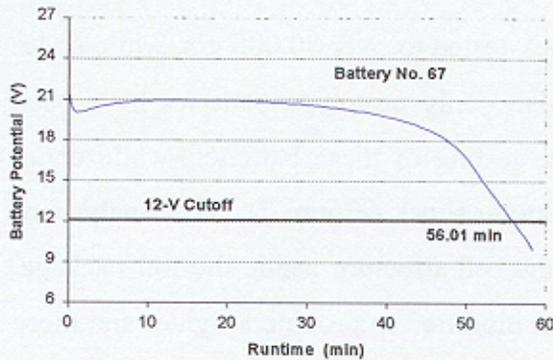

**Figure 9. Li/MnO<sub>2</sub> Nose Fuse Battery Discharge at 250 mA.**

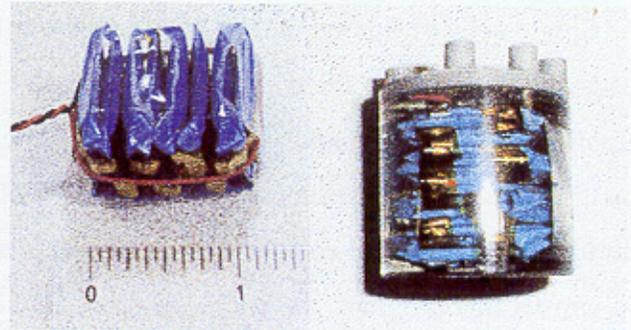



**Figure 10. Unencapsulated and Encapsulated Li/MnO<sub>2</sub> Nose Fuse Batteries.**

Li/MnO<sub>2</sub> nose fuse batteries have been shock-tested under load up to 30,000 g's with a high rate of success. They have also been spin-tested under load up to 300 rps, with only a minimal decrease in voltage (approximately 1 V due to radial acceleration [Figure 11]). This decrease was due to movement of the electrolyte, and changes to the electrolyte chemistry are being considered in order to limit this behavior. The batteries have also been flight-tested on an M483 artillery projectile where they were used to power a U.S. Army Research Laboratory (ARL) yawsonde instrumentation package. The battery output was monitored in flight with a multichannel telemetry system. The system load on the battery was estimated to be 130 mA, and the battery run time prior to launch was estimated at 15 min. Setback acceleration and spin were estimated at 14,000 g's and 265 rps, respectively. The flight time was roughly 52 s. Figure 12 shows the battery output in correlation with the subcarrier oscillator over the duration of the flight.

## 9. KE Projectile Battery

A KE projectile is a long, thin, solid rod that is used to defeat tanks in the battlefield. The only available space for instrumentation is located in the tracer-well cavity of the fins, and possibly in the nose. The volume available in a tracer-well cavity is less than 8 cm<sup>3</sup>, and the environment for this projectile is extreme with launch accelerations over 60,000 g's and propellant flash temperatures over 2,500° C.

Ultralife Li/MnO<sub>2</sub> Nose Fuse Battery No. 57 - spin no. 1 at 250-mA load

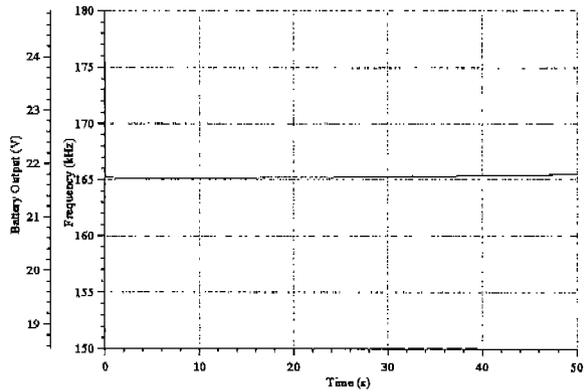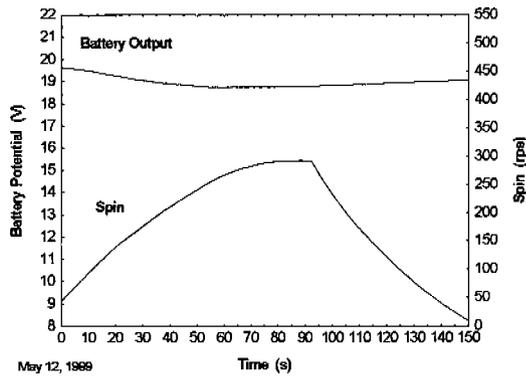

**Figure 11. Spin Test of a 24-V Li/MnO<sub>2</sub> Nose Fuse Battery.**

**Figure 12. Flight Data of an Li/MnO<sub>2</sub> Nose Fuse Battery on an M483 Projectile.**

A primary Li/MnO<sub>2</sub> battery has been developed for powering instrumentation systems on-board these projectiles. The battery has been designed to fit into the tracer-well cavity of the projectile and still meet all of the remaining design requirements shown in Table 2. After several iterations, the battery has been optimized to yield a minimum capacity of 2.5 mAh at 150 mA at room temperature and an 8-mAh minimum capacity at 80 mA at room temperature [4]. Electrical discharge testing has also been performed to verify the electrical performance of the batteries (Figure 13).

**Table 2. Specifications for a Tracer-Well Battery**

Battery Type	Primary Li/MnO <sub>2</sub>
Dimension (Length × Width × Height)	15.5 mm × 15.5 mm × 8.9 mm
Minimum Voltage	6 V
Maximum Voltage	12.8 V
Constant Current Drain	150 mA
Minimum Duration	6 s (to Minimum Voltage)
Shock Survivability	100,000 g <sup>2</sup> s
Spin Rate	100 rps
Operational Temperature	0° C to +50° C

The Li/MnO<sub>2</sub> tracer-well battery has been successfully flight-tested in an M735 105-mm KE projectile. The battery was used to power a telemetry system, which measured the spin history of the projectile. An exploded view of the package design is shown in Figure 14. The battery and electronic assembly were encapsulated to form a stand-alone module that could be inserted into the projectile while in the field (Figure 15). The system transmitted spin history from the projectile for about 2 s when gun-tested at Yuma Proving Ground (YPG). The system was exposed to propellant flash temperatures greater than 2,500° C and setback accelerations greater than 40,000 g's.

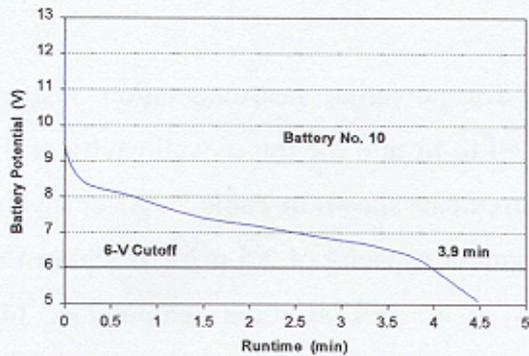


Figure 13. Li/MnO<sub>2</sub> Tracer-Well Battery Discharge at 150 mA.

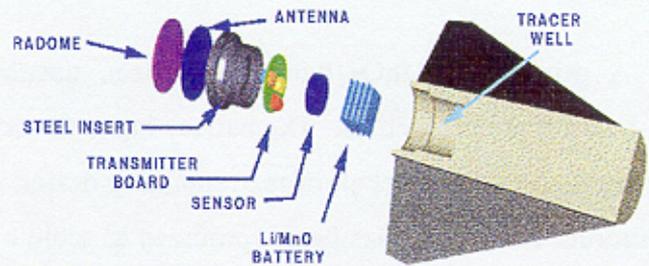


Figure 14. Package Design of an M735 105-mm KE Projectile.



Figure 15. Encapsulated Tracer-Well Assembly and Unencapsulated Tracer-Well Batteries.

## 10. 2.75-in Rocket Battery


The Naval Air Warfare Center at China Lake, CA, required a rechargeable power source for their Advanced Missile Instrumentation Package (AMIP) Program. This instrumentation system consisted of a multichannel pulse code modulation (PCM) telemetry system and an ARL-designed inertial measurement unit (IMU). This instrumentation package, which is about the size of a soda can, fits into a standard 2.75-in rocket. The battery requirements are summarized in Table 3. No commercial batteries could be found to meet both the electrical and mechanical requirements. After estimating the cost of developing a custom battery using standard battery technologies, the HSTSS Program Office was contacted.

**Table 3. Specifications for a 2.75-in Rocket Battery**


Battery Type	Rechargeable Solid Polymer Lithium Ion
Dimension (Length × Width × Height)	31.75 mm × 86.36 mm × 10.16 mm
Minimum Voltage	11.5 V
Maximum Voltage	24 V
Constant Current Drain	700 mA
Minimum Duration	30 s (to Minimum Voltage)
Shock Survivability	500 g's (Maximum)
Spin Rate	50 rps
Operational Temperature	-10° C to +70° C

Two batteries have been designed to meet the AMIP specification. The first design used rechargeable solid polymer lithium-ion technology. This was an aggressive design for this technology because of the high rate of current required. Initial electrical testing of these cells was promising, but, over a short period of time (weeks), the cells would no longer meet the specification. It was discovered that this failure was due to an internal impedance growth problem, which caused the cells to lose capacity over time. Modifications to the processing procedures are currently being addressed to correct this problem.


In order to meet the AMIP Program deadlines, the HSTSS Program funded the development of a Li/MnO<sub>2</sub> version of the battery, shown in Figure 16. Electrical testing of these batteries was performed to verify their performance. The discharge profile for this application included 12 predischarges at 25 mA and then a primary discharge of 700 mA (Figures 17 and 18). Since operation over temperature is also very important for this application, the cells have been tested at -10° C and +70° C and have met the specification [4].

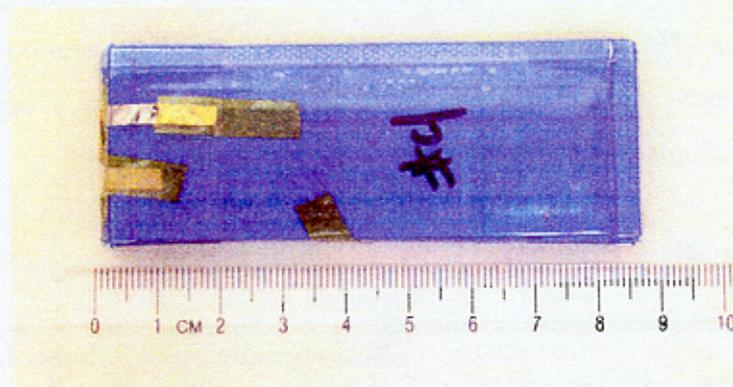

**Figure 16. 2.75-in Rocket Battery.**

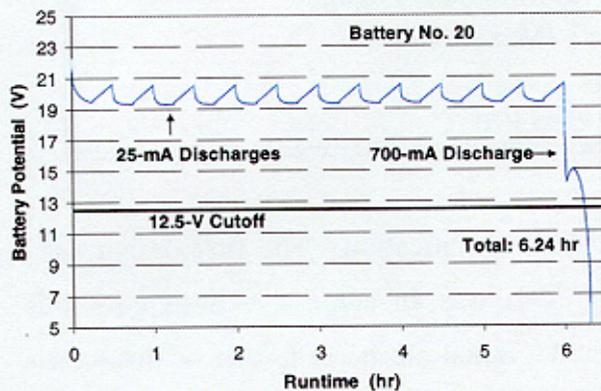

**Figure 17. Li/MnO<sub>2</sub> 2.75-in Rocket Battery With 12 25-mA Discharges and a 700-mA Discharge.**

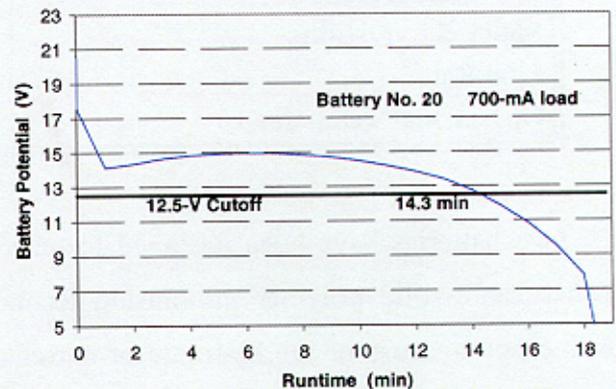

**Figure 18. Exploded View of an Li/MnO<sub>2</sub> 2.75-in Rocket Battery Discharge at 700 mA.**

## 11. Conclusion

Rechargeable, solid polymer lithium-ion batteries are being developed for ballistic telemetry applications. Prototype batteries for artillery nose fuse and rocket applications are currently being built and evaluated. Future work on this technology includes improving capacity and run time, optimizing process parameters, and modifying the electrolyte for low-temperature performance. Solid polymer lithium-ion is still a young technology and is not readily available on the commercial market.

Primary Li/MnO<sub>2</sub> batteries using the Ultralife Thin Cell technology are also being developed for ballistic telemetry applications. Prototype batteries have been built and successfully flight-tested on KE and artillery projectiles. Batteries are also being built for rocket applications. Future work on this technology includes improving shelf life, modifying the electrolyte for improved performance in high-spin applications, and designing internal safety features such as a shut-down separator.

The prototype batteries described in this paper have been designed for use with existing commercial telemetry subsystems. Typical working voltages for these products range from 12 to 24 V. Future HSTSS products are being designed to operate at much lower voltages (3 to 5 V). This will allow for more efficient battery designs that can fully utilize the packaging flexibility of both battery technologies.

INTENTIONALLY LEFT BLANK.

## 12. References

1. Burke, L. W., R. J. Faulstich, and C. E. Newnham. "The Development and Testing of a Polymer Electrolyte Battery for High-g Telemetry Applications." *Power Sources*, vol. 15, pp. 295–313, International Power Sources Committee, Crowborough, UK, 1995.
2. Burke, L. W., E. S. Irwin, R. J. Faulstich, C. E. Newnham, and N. Scholey. "High-g Power Sources for the U.S. Army's HSTSS Programme." *Journal of Power Sources*, vol. 65, pp. 263–270, 1997.
3. Burke, L. W., E. S. Irwin, C. E. Newnham, N. Scholey, L. Malinovsky, B. Coffey, and B. Hoge. "Lithium Batteries for High-g Applications." *Proceedings of the 38th Power Sources Conference*, pp. 139–142, 1998.
4. Ye, Z., and B. Hoge. "Contract Final Report For HSTSS." March 1999.

INTENTIONALLY LEFT BLANK.

<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF</u> <u>COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC DDA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218	1	DIRECTOR US ARMY RESEARCH LAB AMSRL DD 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	HQDA DAMO FDQ D SCHMIDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460	1	DIRECTOR US ARMY RESEARCH LAB AMSRL CS AS (RECORDS MGMT) 2800 POWDER MILL RD ADELPHI MD 20783-1145
1	OSD OUSD(A&T)/ODDDR&E(R) R J TREW THE PENTAGON WASHINGTON DC 20301-7100	3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1145
1	DPTY CG FOR RDA US ARMY MATERIEL CMD AMCRDA 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001		<u>ABERDEEN PROVING GROUND</u>
1	INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN PO BOX 202797 AUSTIN TX 78720-2797	4	DIR USARL AMSRL CI LP (BLDG 305)
1	DARPA B KASPAR 3701 N FAIRFAX DR ARLINGTON VA 22203-1714		
1	NAVAL SURFACE WARFARE CTR CODE B07 J PENNELLA 17320 DAHLGREN RD BLDG 1470 RM 1101 DAHLGREN VA 22448-5100		
1	US MILITARY ACADEMY MATH SCI CTR OF EXCELLENCE DEPT OF MATHEMATICAL SCI MADN MATH THAYER HALL WEST POINT NY 10996-1786		

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
13	CMDR US ARMY ARDEC AMSTA AR AET A M AMORUSO E BROWN C CHUNG A FARINA J GRAU S KAHN K KENDL C LIVECCHIA C NG G MALEJKO W TOLEDO B WONG J THOMASOVICH PICATINNY ARSENAL NJ 07806-5000
1	CMDR US ARMY ARDEC AMSTA AR AET C S LONGO PICATINNY ARSENAL NJ 07806-5000
1	CMDR US ARMY ARDEC AMSTA AR FZ L SPRINGER PICATINNY ARSENAL NJ 07806-5000
3	CMDR US ARMY ARDEC ADAWS M MATTICE D CARLUCCI PICATINNY ARSENAL NJ 07806-5000
1	CMDR US ARMY ARDEC MCATD N GRAY PICATINNY ARSENAL NJ 07806-5000
1	CMDR NAVAL AIR WARFARE CTR WPNS 543000E G BORGEN BLDG 311 POINT MUGU CA 93042-5001

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	CMDR NAVAL AIR WARFARE CTR PM 543E00E D POWELL POINT MUGU CA 93042-5000
1	CMDR NAVAL AIR WARFARE CTR WD E3923 S GATTIS CHINA LAKE CA 93555-6001
1	CMDR NAVAL SURFACE WARFARE CTR INDIAN HEAD DIV D GARVICK 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	CMDR US ARMY YUMA PRVNG GRND ADVANCED TECHLGY OFC STEYP TD ATO A HOOPER YUMA AZ 85365
2	CMDR US ARMY YUMA PRVNG GRND STEYT MT EA C HASTON YUMA AZ 85365-9110
2	CMDR US ARMY YUMA PRVNG GRND STEPY RS EL A HART YUMA AZ 85365-9110
1	CMDR REDSTONE TECHL TEST CTR STERT TE F TD R EPPS REDSTONE ARSENAL AL 35898-8052
2	CMDR STRICOM PM ITTS AMCPM ITTS I R COLANGELO D SCHNEIDER 12350 RESEARCH PARK ORLANDO FL 32826-3276

NO. OF  
COPIES ORGANIZATION

2 STRICOM  
AMSTI LL  
M PHILLIPS  
12350 RESEARCH PARK  
ORLANDO FL 32826-3276

1 DIR US ARMY RESEARCH OFC  
T DOLIGALSKI  
PO BOX 12211  
RESEARCH TRIANGLE PARK NC  
27709

1 NAVAL AIR WARFARE CTR  
TAP/AIRCRAFT INSTRUMENTATION  
DIV  
R FAULSTICH 5.4.2  
UNIT 1  
47765 RANCH RD  
PATUXENT RIVER MD 20670-1469

1 NATIONS INC  
R CARPENTER  
SUITE 110  
12249 SCIENCE DR  
ORLANDO FL 32826-3276

1 BULL SYSTEMS ASSOC  
R BODENSCHATZ  
SUITE 800  
2001 N BEAUREGARD ST  
ALEXANDRIA VA 22311

1 IDA  
J FRASIER  
1801 N BEAUREGARD ST  
ALEXANDRIA VA 22311-1772

2 DARPA MTO  
A PISANO  
B TANG  
3701 N FAIRFAX DR  
ARLINGTON VA 22205-1714

1 SARD  
SARD TR  
W MORRISON  
SUITE 9000  
2511 JEFFERSON DAVIS HWY  
ARLINGTON VA 22202-3911

NO. OF  
COPIES ORGANIZATION

1 MCC  
R MIRACKY  
3500 W BALCONES CTR  
AUSTIN TX 78759-5398

1 ANALOG DEVICES INC  
MS 422  
R MEISENHELDER  
804 WOBURN ST  
WILMINGTON MA 01887-3462

1 JOHNS HOPKINS UNIV  
APPLIED PHYSICS LAB  
H CHARLES  
11100 JOHNS HOPKINS RD  
LAUREL MD 20723-6099

9 DYNAMIC SCIENCE INC  
E BUKOWSKI (3 CPS)  
W CLAY  
E IRWIN  
C MITCHELL  
C MYERS  
N HUNDLEY  
R WERT  
PO BOX 656  
ABERDEEN PROVING GROUND MD  
21005

2 ULTRALIFE BATTERIES INC  
W HOGE  
Z YE  
2000 TECHNOLOGY PKWY  
NEWARK NY 14513

1 ALLIANT TECHSYSTEMS  
MN11 1428  
C CANDLAND  
600 SECOND ST  
HOPKINS MN 55343-8384

NO. OF  
COPIES ORGANIZATION

ABERDEEN PROVING GROUND

2 CMDR US ARMY ATC  
STEAC TC E  
K MCMULLEN  
STEAC TE  
H CUNNINGHAM

21 DIR USARL  
AMSRL WM BA  
F BRANDON  
T BROWN  
L BURKE (3 CPS)  
J CONDON  
W D'AMICO  
B DAVIS  
J FAUST  
T HARKINS  
D HEPNER  
M HOLLIS  
G KATULKA  
V LEITZKE  
P MULLER  
A THOMPSON  
AMSRL WM BC  
P PLOSTINS  
D LYONS  
AMSRL WM BD  
B FORCH  
AMSRL WM BE  
G WREN  
AMSRL WM BF  
J LACETERA

NO. OF  
COPIES ORGANIZATION

2    ULTRALIFE BATTERIES UK LTD  
      COLIN NEWNHAM  
      NEIL SCHOLEY  
      18 NUFFIELD WAY  
      ABINGDON OX14 1TG  
      ENGLAND

INTENTIONALLY LEFT BLANK.

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE May 2000	3. REPORT TYPE AND DATES COVERED Final, Jul 98-Aug 99	
4. TITLE AND SUBTITLE  HSTSS Battery Development for Missile and Ballistic Telemetry Applications		5. FUNDING NUMBERS  1L162618AH80	
6. AUTHOR(S) Lawrence W. Burke, Edward Bukowski,* Colin Newnham,** Neil Scholey,** William Hoge,*** and Zhiyaun Ye***		8. PERFORMING ORGANIZATION REPORT NUMBER ARL-MR-477	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WM-BA Aberdeen Proving Ground, MD 21005-5066		10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES)		11. SUPPLEMENTARY NOTES *Dynamic Science Incorporated, P.O. Box 656, APG, MD 21005; **Ultralife Batteries (UK), Ltd., 18 Nuffield Way, Abingdon OX14 1TG, England; *** Ultralife Batteries, Inc., 2000 Technology Parkway, Newark, NY 14513	
12a. DISTRIBUTION/AVAILABILITY STATEMENT  Approved for public release; distribution is unlimited.		12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  The rapid growth in portable and wireless communication products has brought valuable advancements in battery technology. No longer is a battery restricted to a metal container in cylindrical or prismatic format. Today's batteries (both primary and secondary) can be constructed in thin sheets and sealed in foil/plastic laminate packages. Along with improvements in energy density, temperature performance, and environmentally friendly materials, these batteries offer greater packaging options at a significantly lower development cost. Under the Hardened Subminiature Telemetry and Sensor System (HSTSS) Program, these battery technologies have been further developed for high-g telemetry applications. Both rechargeable solid-state lithium-ion polymer and primary lithium manganese dioxide (Li/MnO2) batteries are being developed in conjunction with Ultralife Batteries, Inc. Prototypes of both chemistries have been successfully tested in a ballistic environment, while providing high constant rates of discharge, which is essential to these types of applications. Electrical performance and environmental data are reported.			
14. SUBJECT TERMS telemetry, batteries, lithium ion, lithium manganese dioxide, high-g		15. NUMBER OF PAGES 26	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED		16. PRICE CODE	
18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

**USER EVALUATION SHEET/CHANGE OF ADDRESS**

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number/Author ARL-MR-477 Date of Report May 2000

2. Date Report Received \_\_\_\_\_

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

CURRENT  
ADDRESS

\_\_\_\_\_  
Organization  
\_\_\_\_\_  
Name E-mail Name  
\_\_\_\_\_  
Street or P.O. Box No.  
\_\_\_\_\_  
City, State, Zip Code

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

OLD  
ADDRESS

\_\_\_\_\_  
Organization  
\_\_\_\_\_  
Name  
\_\_\_\_\_  
Street or P.O. Box No.  
\_\_\_\_\_  
City, State, Zip Code

(Remove this sheet, fold as indicated, tape closed, and mail.)  
**(DO NOT STAPLE)**

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS

**BUSINESS REPLY MAIL**

FIRST CLASS PERMIT NO 0001, APG, MD

POSTAGE WILL BE PAID BY ADDRESSEE

DIRECTOR  
US ARMY RESEARCH LABORATORY  
ATTN AMSRL WM BA  
ABERDEEN PROVING GROUND MD 21005-5066



NO POSTAGE  
NECESSARY  
IF MAILED  
IN THE  
UNITED STATES

