



## **Ballistic Properties of Zylon for Application to Firearm Projectile Protection**

**by E. Pineda, C. Hogue, and W. Goldsmith**

---

**ARL-CR-529**

**July 2003**

prepared by

Department of Mechanical Engineering  
University of California, Berkeley  
Berkeley, CA 94720

in cooperation with

SRI International  
333 Ravenswood Ave.  
Menlo Park, CA 94025

under contract

DAAD17-01-P-0888

## **NOTICES**

### **Disclaimers**

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# **Army Research Laboratory**

Aberdeen Proving Ground, MD 21005-5066

---

---

**ARL-CR-529**

**July 2003**

---

---

## **Ballistic Properties of Zylon for Application to Firearm Projectile Protection**

**E. Pineda, C. Hogue, and W. Goldsmith**

prepared by

Department of Mechanical Engineering  
University of California, Berkeley  
Berkeley, CA 94720

in cooperation with

SRI International  
333 Ravenswood Ave.  
Menlo Park, CA 94025

under contract

DAAD17-01-P-0888

---

## **Abstract**

---

In recent years, a para-phenylene benzobisoxazole fiber, Zylon (registered trademark of the Toyobo Company), has surfaced as a potential candidate for body armor to possibly replace Kevlar (registered trademark of DuPont). Zylon's effectiveness depends on its ballistic properties as well as its mass in comparison with Kevlar. The present extended investigation focuses on determining the ballistic limit and the  $V_{50}$  velocity for 10, 20, and 30 stitched plies of Zylon using standard North Atlantic Treaty Organization 9-mm nonrotating strikers. This report concentrates specifically on the ballistic limit of 10-ply Zylon, as well as the effect that impact location has on perforation. It was also discovered that many other factors affect the ballistic performance, including slip of the fabric in the holder, the preparation of the shell, and the amount of fiber damage present. These aspects will be considered when evaluating Zylon's performance and determining whether or not it is indeed superior to Kevlar for applications in body armor and personnel protection. The first instance of perforation for 10-ply Zylon occurred at an initial velocity of 341.4 m/s, and the highest initial velocity for a ricochet was 566.2 m/s.

---

## Contents

---

<b>List of Figures</b>	<b>v</b>
<b>List of Tables</b>	<b>v</b>
<b>1. Introduction</b>	<b>1</b>
<b>2. Objectives</b>	<b>1</b>
<b>3. Experimental Setup</b>	<b>2</b>
<b>4. Procedure</b>	<b>5</b>
<b>5. Results and Discussion</b>	<b>6</b>
5.1 Sources of Error.....	6
5.2 Load-Deformation Tests.....	7
<b>6. Ballistic Tests</b>	<b>7</b>
<b>7. Conclusions</b>	<b>13</b>
<b>8. References</b>	<b>14</b>
<b>Report Documentation Page</b>	<b>15</b>

INTENTIONALLY LEFT BLANK.

---

## List of Figures

---

Figure 1. The aluminum target holder clamped to the steel backstop. ....	2
Figure 2. The 0.50-cal. powder gun: (a) side view and (b) rear view.....	3
Figure 3. Timing grid holders: (a) 3/4 view from ~2 m and (b) top view, close-up.....	4
Figure 4. Rebound catcher box. ....	4
Figure 5. Zylon target (note: 20-ply sheet shown).....	5
Figure 6. Typical target deformation of a near-perforating shot. ....	7
Figure 7. Load displacement curves. ....	8
Figure 8. Final vs. initial velocity. ....	8
Figure 9. Final vs. initial velocity (striking velocity). ....	11
Figure 10. Recovered projectiles (note: numbers beneath projectiles indicate initial velocity in meters per second). ....	12

---

## List of Tables

---

Table 1. Tabular ballistic data.....	9
--------------------------------------	---

INTENTIONALLY LEFT BLANK.

---

## 1. Introduction

---

Zylon\* is a para-phenylene benzobisoxazole (PBO) fiber made by the Toyobo Company of Osaka, Japan, with promise to replace today's aramids as the super high-performance fiber of the future. It is far superior to Kevlar† and other aramids in both mechanical properties and resistance to such environmental effects as heat, moisture, abrasion, and seawater corrosion. Because of these properties, the U.S. Army took an interest in Zylon as a future bulletproof material. Based on a contract from the Army, the goal of this project is to determine the ballistic performance of Zylon. This is summarized into two basic experimental results—the ballistic limit and the limit velocity.

The earliest reference to “modern” body armor located by a literature search consisted of a 1931 photograph of a bulletproof vest that was not published until 1988 [1]. Other references involving personnel protection have appeared primarily during the last decade [e.g., 2–6] and have been almost exclusively concerned with ballistic fabric or fabric composite shielding. Widespread investigations of projectile penetration and perforation for normal impact have been presented in references [7, 8] and for nonstandard impact conditions, in reference [8]. The ballistic limit can be improved in many ways, both through advances in materials and in the geometry of their application. This study involves simply testing a new material, Zylon, for comparison against similar ballistic fabrics such as Kevlar. New applications for Zylon are being investigated, including a joint project between Boeing, SRI, the Federal Aviation Administration, and the University of California, Berkeley, to explore containment barriers on commercial aircraft jet engines. Their function would be to protect vital fuselage components and systems, as well as passengers, from high velocity fan fragments that can result from catastrophic engine failure.

---

## 2. Objectives

---

The ballistic limit represents the speed of a nonrotating striker of given mass and dimensions at which half of the projectiles will just perforate a specified target at normal incidence [9]. The  $V_{50}$  and limiting velocity is a somewhat more complicated mathematical function and requires a program to compute. These calculations will be made for the samples of 10-, 20-, and 30-ply Zylon targets. In addition to these concrete objectives, other consequential concerns arose after the initial stages of experimentation. First, it was discovered that the boundary conditions of the Zylon target had a great affect on the performance of the fabric. Not only the velocity of the

---

\* Zylon is a registered trademark of the Toyobo Company.

† Kevlar is a registered trademark of DuPont.

projectile, but also the location of the impact (relative to the edges of the target holder) became important. This phenomenon is clearly rooted in the “give” of the material farther from its rigid boundaries. The results of a static force deflection test at various locations on the target will be discussed later. At this point, the effects are only qualitative, but there is hope of developing a model (based on the boundary conditions of a thin membrane with a distributed load) to make this conclusion more quantitative. Also, due to the thickness of the target samples, there was slipping of the material within the holder at high/nonperforating shots. Some of this should be eliminated after some modifications to the target holder (see section 5).

---

### 3. Experimental Setup

---

The experimental setup included a 14- × 14-in aluminum target holder, C-clamped at four corners to a steel “backstop” (Figure 1) that was, in turn, secured to a 680-kg steel table on which the gun was mounted.



Figure 1. The aluminum target holder clamped to the steel backstop.

The targets were struck relatively centrally and normally by standard 9-mm full metal jacket flatback handgun projectiles, made by either Remington or Winchester. The projectiles had a nominal diameter of 0.355 in and a length of 0.625 in. They were made of lead, with a thin copper alloy jacket, and had an average mass of 124 gr each and a sectional density of 0.141.

The 9-mm projectiles were sabotaged for a 0.50-cal. powder gun. The 0.50-cal. powder gun (Figure 2) consisted of a 20-mm-thick high-strength steel barrel with an inside diameter of 0.501 in and a length of 1.6 m, a breech capable of accommodating a 50-mm cartridge and a supporting rail frame which attached the unit to the support.

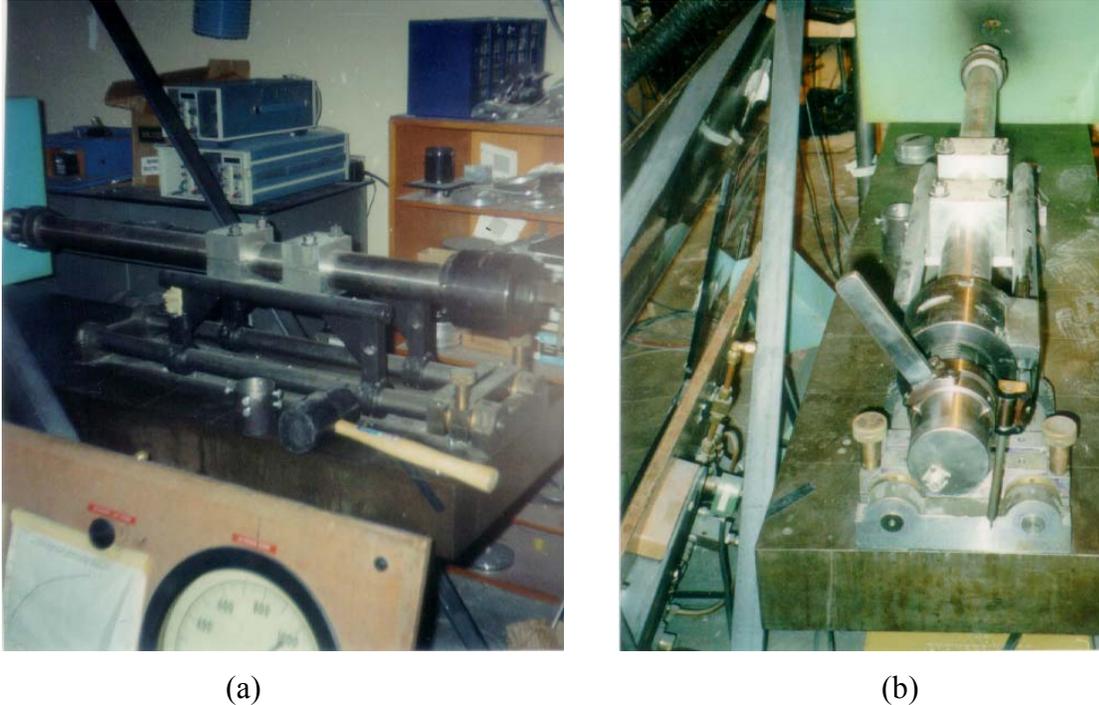


Figure 2. The 0.50-cal. powder gun: (a) side view and (b) rear view.

The initial velocity of the projectiles was measured by the duration required to break the beams of two parallel helium-neon lasers positioned directly in front of the muzzle, separated by 165 mm, with the first of the two lasers located 24 in from the gun muzzle. The target itself was ~44 in from the muzzle. The lasers were focused on two custom photodiodes generating a voltage pulse recorded by a Hewlett-Packard 5316 time-interval counter. The final velocity of the fastest object behind the target was determined by the time between the signals generated by two aluminum foil make screens, each about  $432 \times 254$  mm in size, and separated by 155 mm. The two aluminum foil sheets constituting a make screen were separated by a distance of 6 mm. The two make screens generated both a starting and stopping pulse recorded by a second time interval meter from which the final velocity was determined.

A second “backup” system of consecutive paper targets with a grid of interlocking conducting ink lines (Figure 3) worked in a similar fashion to the foil, also making use of a second Hewlett-Packard 5316 time-interval counter.

A blast shield was placed 10 inches in front of the gun muzzle to prevent undue damage to the rebound catcher box and to keep gasses and firing debris from interacting with data-collecting equipment. The rebound catcher box (Figure 4) was essentially a foam cage with an entrance hole for the projectile and small holes in the sides for the initial velocity lasers to pass through to the detectors. A catcher box using rags was placed behind the gun table to soft recover projectiles and plugs. Several blocks of buff potters clay were placed in front of this catcher box to further slow perforating projectiles.



(a)



(b)

Figure 3. Timing grid holders: (a) 3/4 view from ~2 m and (b) top view, close-up.

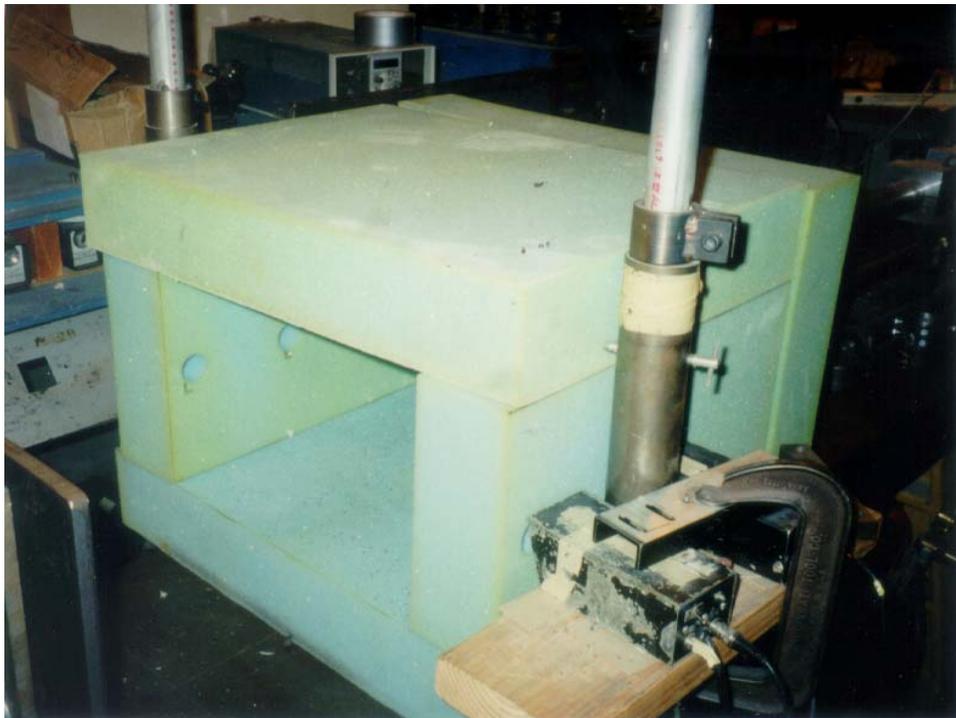


Figure 4. Rebound catcher box.

---

## 4. Procedure

---

The 12- × 12-in Zylon target sample (Figure 5) was secured in an aluminum target holder with essentially a machined “tongue and groove” system to minimize fabric slipping. Uniformity is achieved through the use of an 85 in-lb torque wrench at the numerous screws around the target holder. The targets themselves are 10-, 20-, and 30-ply sheets of Zylon sewn together with chain-link fence-type crisscross stitching. For the thicker samples, the tapped holes will be bored out, and stronger tool-grade steel bolts will be used in lieu of the less reliable lag screws. The desired impact location was aligned to the bore by a laser placed in the breech. The position of the impact was recorded to investigate effects of different tensile preloads in the Zylon target.



Figure 5. Zylon target (note: 20-ply sheet shown).

The lasers and photodiodes were turned on to record the initial velocity of the striker upon beam interruption. Two aluminum foil make switches, each consisting of a set of closely spaced parallel sheets, were connected to a time-interval meter that measured the time differential of the passage between the two positions, representing the final velocity of the projectile behind the target.

Following a test, the projectile was recovered. In a few instances, the projectile shattered, most likely from contact with metallic objects other than the target (e.g., the back of the steel catcher box), and, in other cases, it could not be recovered due to single or multiple ricochet, especially when deviating from its initial trajectory due to impact. The position of the holes in the foils was examined to ascertain the projectile trajectory.

---

## 5. Results and Discussion

---

### 5.1 Sources of Error

There are many factors that contribute to the accuracy of our data; all must be taken into account when observing the data. First and foremost are the boundary conditions of the target holder. The closer to an edge or corner the projectile strikes, the easier it is for the projectile to perforate. With multiple shots per target, it is impossible to have all shots in the center. Another concern when firing multiple shots per target is whether or not the strength of the target as a whole is compromised after the first shot. Figure 6 shows the typical target deformation (originally taut) from a near-perforating target-center shot. If a shot hits too close to a previous impact, the projectile may strike fibers damaged from a previous shot. It is obvious that if this is the case, the data obtained will not be accurate.

The way that the target is secured in the holder also affects the outcome of shots. The target slips slightly from the “grasp” of the target holder upon impact, which increases the target's resistance to perforations. The amount the target slips ranges from 1/2 to 1 in. Previously, the target holder used 16 tapped holes with bolts torqued to a maximum of 85 in-lb to secure the target. Any torque higher than 85 in-lb would snap the bolts. Also, after a few months, the threads of the holes began to wear. This created a resistance to the torque applied in the bolts which made it difficult to assess the actual torque in each bolt. The target holder has been modified to a nut and bolt design, which allows for more torque to be applied to each bolt, and there is no resistance from threads. Soon, higher-grade, larger diameter (3/8 in rather than 1/4 in) bolts will be used, allowing for even more torque.

The way that a shell is loaded can also have a great impact on the projectile's initial velocity. Due to the size of the projectiles, slight variations in the amount of wadding or the way it is tamped down in the shell can greatly affect velocity. It is difficult to obtain desired velocities, and thus difficult to get data for specific areas of interest. This proves to be quite a nuisance when specific velocities are needed to find the  $V_{50}$  or the ballistic limit. It becomes a “shooting-in-the-dark” process, which increases the number of targets needed to obtain specific data.



Figure 6. Typical target deformation of a near-perforating shot.

## 5.2 Load-Deformation Tests

Due to the implication that the location of impact (with respect to the boundary of the target holder) may greatly affect the chance of perforation, load-deformation tests were performed on a 10-ply sheet of Zylon while it was secured in the target holder. Each of the 16 screws was torqued up to 85 in-lb. Figure 7 shows these tests that were performed at three locations—2.5 in, 4.5 in along the diagonal, and in the center.

It was found that the closer to the center of the target one gets, the less force is required to elastically deform the material. Therefore, shots fired closer to the corners have a greater chance of perforating because less energy is absorbed by the target. This fact greatly affects our ballistic results. It was also found that when a target is fired, it slips in the target holder. Due to this implication, we changed the target holder to accommodate a nut and bolt setup with high-grade bolts.

---

## 6. Ballistic Tests

---

Fifty-four shots were fired at various points on 10-ply sheets of Zylon. The complete results for all the shots, obtained from the data in Table 1, are shown in Figure 8. However, since the location of the shots, as well as many other factors, affects the projectile's ability to perforate, Figure 8 is not a completely accurate depiction of the ballistic capabilities of Zylon. However,

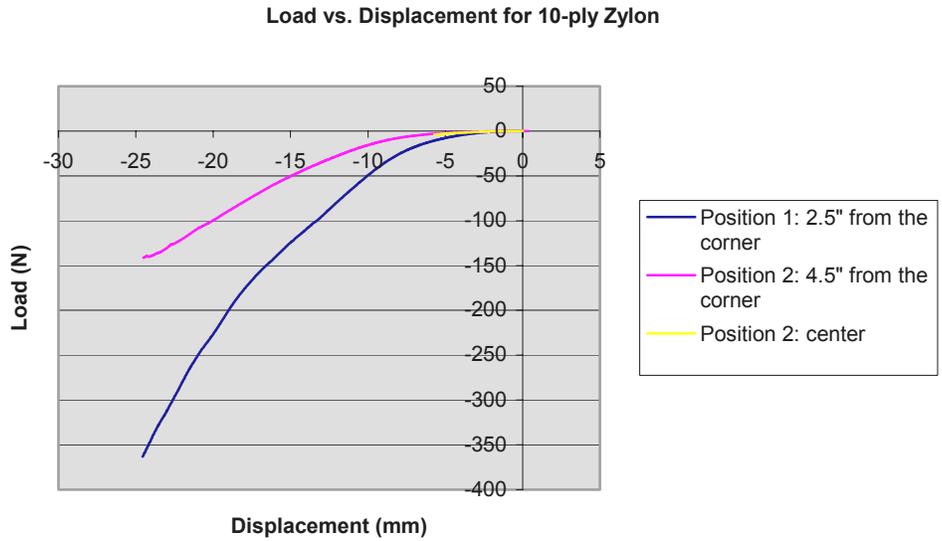


Figure 7. Load displacement curves.

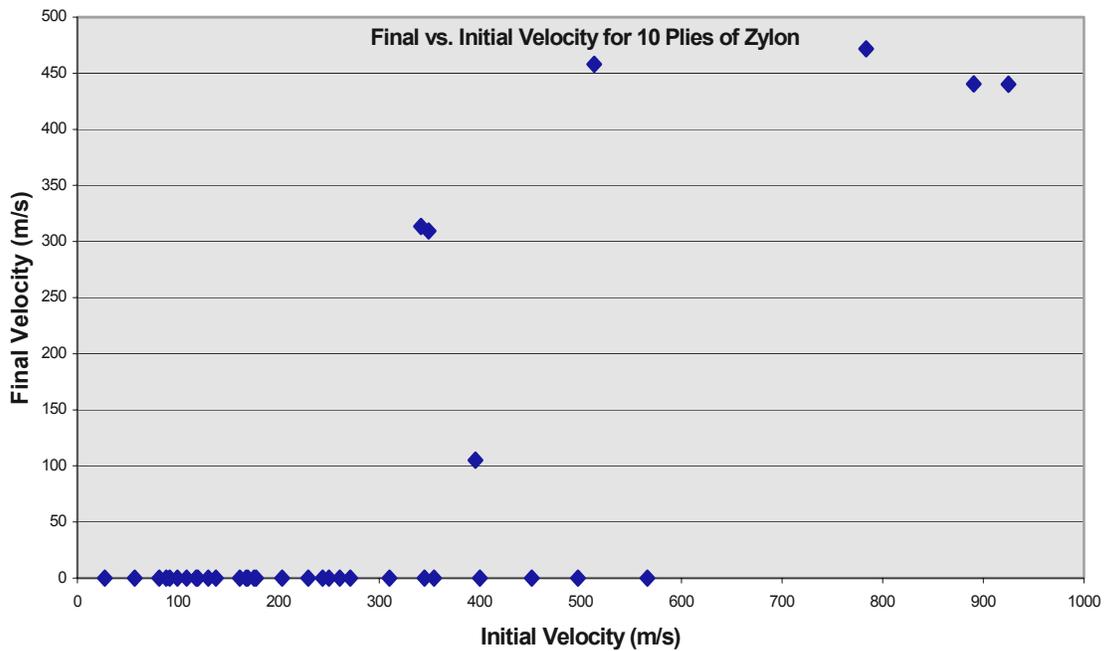


Figure 8. Final vs. initial velocity.

corner shots can be considered a lower bound of sorts and the center shots an upper bound. These discrepancies can be clearly seen using Figure 8. For instance, there is a nonperforating shot with an initial velocity of 566 m/s fired at the center as well as a perforating shot at 349 m/s fired near the corner. Finally, Figure 9 is a three-dimensional plot of initial velocity of projectiles vs. the striking location on the target measured from an origin at an arbitrary corner of the target.

Table 1. Tabular ballistic data.

Shot No.	Ply	Powder Load (g)	Initial Velocity (m/s)	Final Velocity (m/s)	Type of Bullet	Perforation?	X Position (in)	Y Position (in)	Comments
1	10	5.2	error	NA	R	N	3.25	9	
2	10	5.81	348.9	309.5	R	Y	7	8.25	
3	10	6	error	508.86	R	Y	4	4	
4	10	6	890.4	440.5	R	Y	7.5	4.5	
5	10	6	320.5	error	R	Y	6.375	8.125	Shot fired without sabot stripper.
6	10	6	783.5	471.8	R	Y	5.25	3.5	Shot fired without sabot stripper.
7	10	6.5	598.7	error	R	Y	4.5	4.75	Sabot was not stripped.
8	10	6.5	513.4	458.2	R	Y	3.25	3.75	
9	10	7	error	457.8	R	Y	5	3.75	
10	10	7	error	error	R	Y	8.125	4.5	
11	10	7	591.2	error	R	Y	9.75	7.25	
12	10	7.5	395.3	105	R	Y	6.375	7.5	
13	10	7.5	1757.2	error	R	Y	3.5	7.875	
14	10	8	error	236.6	R	Y	3.875	6.25	
15	10	5	682.4	error	R	Y	7.875	6.75	
16	10	0.5	91.63	NA	R	N	8.25	4.75	
17	10	0.75	error	NA	R	N	6	6.125	
18	10	0.75	81.45	NA	R	N	3.25	4.125	
19	10	1	27.3	NA	R	N	6.125	8.375	
20	10	1	88.33	NA	R	N	3	7.5	
21	10	1.25	175.53	NA	R	N	5.625	4.25	
22	10	1.5	19.55	NA	R	N	8	8.75	
23	10	1.75	error	NA	R	N	7.75	6.375	
24	10	1.75	118	NA	R	N	4	3.75	
25	10	6	924.89	440.22	R	Y	7.25	5.75	
26	10	0.5	error	NA	W	N	4.375	4.875	
27	10	0.5	56.99	NA	W	N	7.75	7.25	
28	10	0.75	99.4	NA	W	N	6.875	6.125	
29	10	1	108.4	NA	W	N	4.75	8	
30	10	1.25	167.67	NA	W	N	4.125	4.5	
31	10	2	130	NA	R	N	2.75	8.875	
32	10	2.5	137.5	NA	R	N	7.625	3.75	
33	10	3	error	NA	R	N	5.75	6.125	
34	10	3.5	354.3	NA	R	N	2.5	4.25	
35	10	1.5	error	NA	W	N	5.5	NA	

Table 1. Tabular ballistic data (continued).

Shot No.	Ply	Powder Load (g)	Initial Velocity (m/s)	Final Velocity (m/s)	Type of Bullet	Perforation?	X Position (in)	Y Position (in)	Comments
36	10	1.5	260.6	NA	W	N	2.5	3	Sabot was not stripped.
37	10	2.5	229.26	NA	W	N	4	8.25	
38	10	2	169.3	NA	W	N	4	8.125	
39	10	3	161.29	NA	W	N	8.25	7.5	
40	10	3.5	310	NA	W	N	4.375	5.5	
41	10	4	497.4	NA	R	N	8.375	4.125	Bullet hit target holder before striking target.
42	10	4	243.5	NA	R	N	6.875	4.5	
43	10	4.5	451.44	4.5	R	N	4.875	6.25	
44	10	5	342.89	error	R	Y	3.5	6.375	
45	10	3	344.9	NA	R	N	5.25	4.25	
46	10	3.5	203.5	NA	R	N	3.625	5	Sabot was not stripped.
47	10	4	error	error	R	error	NA	NA	
48	10	3.5	566.2	NA	R	N	5	6.5	
49	10	3.6	399.8	NA	R	N	5.75	6.25	
50	10	3.7	error	error	R	error	NA	NA	
51	10	4.1	250	NA	R	N	5.5	5	Initial velocity obtained from high-speed video camera.
52	10	4.2	341.4	313.6	R	Y	5.5	5.75	
53	10	4	177.4	NA	R	N	6.125	6	
54	10	4	271.1	NA	R	N	5.5	6	

Some interesting information was gained from the recovered projectiles themselves. Figure 10a shows some typical low-velocity, nonperforating projectiles (57–138 m/s) that suffered almost no visible damage upon impact. However, it is also known that each of these projectiles rotated upon impact with the Zylon target and was finally brought to rest completely sideways. This was inferred from the imprint of the bullet left on the Zylon, clearly showing the bullet-like profile of the projectile, rather than a circular one. The extreme case of this rotation can be seen in Figure 10b. Here, higher velocity nonperforating projectiles (161–451 m/s) showed significant deformation in the lateral direction from being “squished” sideways against the Zylon target upon rotation. (Note: The bullets in Figure 10b are shown from behind, parallel to their major axes.) This rotation appears to help the target absorb energy, thus allowing no perforation at 451 m/s, even though lower velocity projectiles showed perforation (such as the 321- and 349-m/s projectile in Figure 10d). Compare these laterally deformed projectiles to those in Figure 10c. Here, the projectiles did not rotate upon impact, and they bear the more intuitive

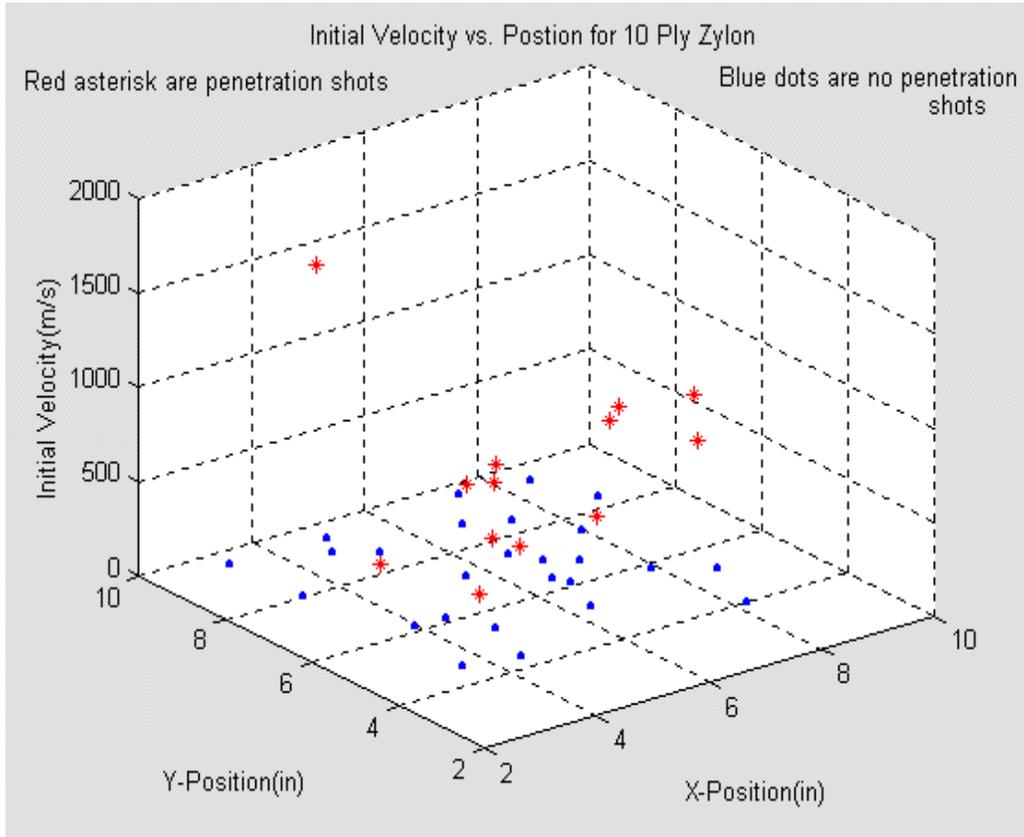


Figure 9. Final vs. initial velocity (striking velocity).

“snub-nosed” shape expected from fully anterior deceleration. Finally, Figure 10d shows some typical perforating shots with velocities ranging from 321 to 890 m/s. It is interesting to note that the higher velocity perforating shots show less damage than those that perforated at lower velocity.

The  $V_{50}$  was estimated using the following:

$$V_{50} = V^*(a_0 + a_1X + a_2X^2 + a_3X^3 + a_4X^4), \quad (1)$$

where  $X = A_d A_p / m_p = (\text{fabric areal density})(\text{projectile base area})/(\text{projectile mass})$ ,

$A_d = 1.56 \text{ kg/m}^2$ ,  $A_p = 254.5 \times 10^{-6} \text{ kg/m}^2$ ,  $m_p = 0.00803 \text{ kg}$ , and  $a_0 = 0.323$ ,  $a_1 = 6.732$ ,  $a_2 = -26.642$ ,  $a_3 = 68.442$ ,  $a_4 = -62.446$ , and  $V^* = 813.2$  [10].


$V_{50}$  was calculated to be 486.8 m/s. Our first instance of perforation was at 341.4 m/s, and our last instance of no perforation was at an initial velocity of 566.2 m/s. Both of these shots were center shots, but the former shot was fired after the nut and bolt fasteners were implemented in the target holder. This allowed for a reduction in slip, thus allowing the target to absorb less of



(a)



(b)

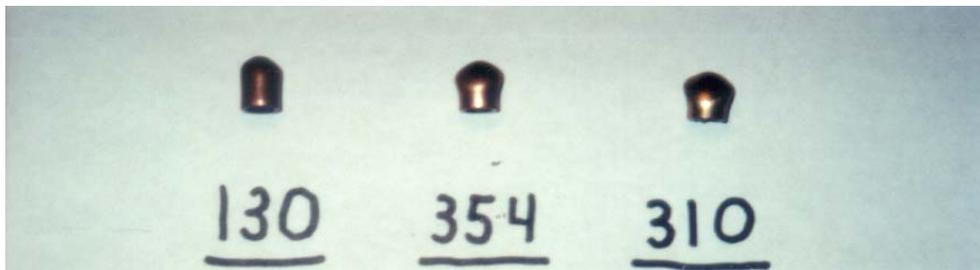

(c)



(d)

Figure 10. Recovered projectiles (note: numbers beneath projectiles indicate initial velocity in meters per second).

the projectile's kinetic energy, resulting in a perforation. These variances in actual limits from the theoretical limit can be attributed to the location of the shots, the accuracy of the initial velocity equipment, and slipping in the target holder. None of these factors can be completely eliminated. Multiple shots per target are necessary due to the number of targets available. The slip can be reduced in our target holder, but it can never be zero. With the data provided in this report, the ballistic limit for various impact locations can be determined. However, the ballistic limit is not the same as the  $V_{50}$  or the limiting velocity. The  $V_{50}$  as well as the limiting velocity will be found on a later date using the programs provided.

The average 9-mm handgun has a muzzle velocity of 388 m/s [11]. Ten plies of Zylon are not enough to stop a shot from the average 9-mm handgun, but a slight increase in the number of plies should prove effective. Ten plies of Kevlar 29 have a  $V_{50}$  of 434 m/s [12]. Although Kevlar 29 has a higher  $V_{50}$  than Zylon, Zylon has a lower areal density. Ten plies of Zylon have an areal density at  $1.56 \text{ kg/m}^2$ , and 10 plies of Kevlar 29 have an areal density of  $2.95 \text{ kg/m}^2$  [12]. Therefore, it may take more plies of Zylon than Kevlar 29 to stop a projectile, but with Zylon's significantly lower areal density, that amount of plies will weigh less than the ballistic equivalent made of Kevlar 29. This shows that Zylon would be more practical than Kevlar 29 for use as body armor in the military and law enforcement where mass is critical.

---

## 7. Conclusions

---

Ten plies of Zylon were not enough to stop a 9-mm bullet fired from an average handgun, nor was the theoretical  $V_{50}$  or the ballistic limit higher than that of Kevlar 29. However, a slight increase in plies should be enough to overcome both of these. Since Zylon has a far less areal density than Kevlar 29, the mass of the number of plies needed to reach the ballistic limit of Kevlar would still be less than that of 10 plies of Kevlar. Twenty plies of Zylon, which will be tested next, should prove effective against projectiles fired at 388 m/s.

Despite the sources of error, a ballistic curve was obtained. The error that comes from the target and the target holder can be considered positive because Zylon in real-world use will not be in laboratory conditions. For 20 plies of Zylon, the slip will be minimized due to modifications made on the target holder. It is essential that the fabric holds up no matter what adversities it faces—multiple shots, slipping, or any other nonideal conditions.

Zylon is the “ballistic fabric” of the future. Zylon's low areal density allows for more maneuverability and proves to be more practical for applications in the armed forces and law enforcement than Kevlar. Further testing will show the number of plies of Zylon needed to achieve the same ballistic limit, as Kevlar 29, will weigh less.

---

## 8. References

---

1. Patton, A. "Images of the Past—'Who Cares About Bullets.'" *American History*, vol. 33, no. 1, 1988.
2. Anderson, K. J. "Ceramic-Metal Composite—Bulletproof Strength." *Mechanical Engineering*, vol. 112, no. 7, pp. 46–51, 1990.
3. Roberts, G. K., and M. E. Bullian. "Protective Ability of the United States Military Personal Armor System, Ground Troops (PAGT): Fragmentation Vest Against Common Small Arms Projectiles." *Military Medicine*, vol. 158, pp. 560–563, 1993.
4. Bazhenov, S. "Dissipation of Energy by Bulletproof Aramid Fabric." *Journal of Materials Science*, vol. 32, pp. 4167–4173, 1997.
5. Scott, B. "Bullet-Resistant Vests: Dressed to the Nine Millimeters." *Scientific Americana*, vol. 176, p. 132, 1997.
6. Ashley, S. "Aramid-Fiber Reinforced Nylon." *Mechanical Engineering*, vol. 119, p. 30, 1997.
7. Corbett, G. G., S. R. Reid, and W. Johnson. "Impact Loading of Plates and Shells by Free-Flying Projectiles: A Review." *International Journal of Impact Engineering*, vol. 18, pp. 141–230, 1996.
8. Goldsmith, W. "Non-Ideal Projectile Impact on Targets." *International Journal of Impact Engineering*, vol. 22, pp. 95–395, 1999.
9. Cipparone, G., B. Bourne, D. Orphal, and W. Goldsmith. "Momentum Exchange Alteration in Projectile/Target Impact." *International Journal of Impact Engineering*, vol. 27, pp. 691–707, 2000.
10. Orphal, D. Personal communication with E. Pineda. February 2002.
11. Koeing, B., S. Hoffman, N. Hirota, and S. Beck. "Signal Convolution of Recorded Free Field Gunshot Sounds." *Journal of Audio Engineering*, vol. 46, pp. 7, 8, and 638, 1998.
12. Cunniff, P. M. "The Performance of Poly(Para-phenylene benzobisoxazole) (PBO) Fabric for Fragmentation Protective Body Armor." *18th International Symposium on Ballistics*, vol. 2, pp. 837–844, 1999.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188		
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE (DD-MM-YYYY) July 2003		2. REPORT TYPE Interim		3. DATES COVERED (From - To) August 2001–April 2002	
4. TITLE AND SUBTITLE Ballistic Properties of Zylon for Application to Firearm Projectile Protection			5a. CONTRACT NUMBER DAAD17-01-P-0888		
			5b. GRANT NUMBER		
			5c. PROGRAM ELEMENT NUMBER		
6. AUTHOR(S) E. Pineda, C. Hogue, and W. Goldsmith			5d. PROJECT NUMBER PERS01		
			5e. TASK NUMBER		
			5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Department of Mechanical Engineering      SRI International University of California, Berkeley      333 Ravenswood Ave. Berkeley, CA 94720      Menlo Park, CA 94025			8. PERFORMING ORGANIZATION REPORT NUMBER		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WM-TD Aberdeen Proving Ground, MD 21005-5066			10. SPONSOR/MONITOR'S ACRONYM(S)		
			11. SPONSOR/MONITOR'S REPORT NUMBER(S) ARL-CR-529		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.					
13. SUPPLEMENTARY NOTES Point of contact for this report is Dr. Nevin Rupert, U.S. Army Research Laboratory, ATTN: AMSRL-WM-TD, Aberdeen Proving Ground, MD 21005-5066.					
14. ABSTRACT In recent years, a para-phenylene benzobisoxazole fiber, Zylon (registered trademark of the Toyobo Company) has surfaced as a potential candidate for body armor to possibly replace Kevlar (registered trademark of DuPont). Zylon's effectiveness depends on its ballistic properties as well as its mass in comparison with Kevlar. The present extended investigation focuses on determining the ballistic limit and the $V_{50}$ velocity for 10, 20, and 30 stitched plies of Zylon using standard North Atlantic Treaty Organization 9-mm nonrotating strikers. This report concentrates specifically on the ballistic limit of 10-ply Zylon, as well as the effect that impact location has on perforation. It was also discovered that many other factors affect the ballistic performance, including slip of the fabric in the holder, the preparation of the shell, and the amount of fiber damage present. These aspects will be considered when evaluating Zylon's performance and determining whether or not it is indeed superior to Kevlar for applications in body armor and personnel protection. The first instance of perforation for 10-ply Zylon occurred at an initial velocity of 341.4 m/s, and the highest initial velocity for a ricochet was 566.2 m/s.					
15. SUBJECT TERMS Zylon, body armor, ballistics, ballistic testing					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT  UL	18. NUMBER OF PAGES  24	19a. NAME OF RESPONSIBLE PERSON Nevin Rupert
a. REPORT UNCLASSIFIED	b. ABSTRACT UNCLASSIFIED	c. THIS PAGE UNCLASSIFIED			19b. TELEPHONE NUMBER (Include area code) (410) 278-9652

INTENTIONALLY LEFT BLANK.

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC OCA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218
1	COMMANDING GENERAL US ARMY MATERIEL CMD AMCRDA TF 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001
1	INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN 3925 W BRAKER LN STE 400 AUSTIN TX 78759-5316
1	US MILITARY ACADEMY MATH SCI CTR EXCELLENCE MADN MATH THAYER HALL WEST POINT NY 10996-1786
1	DIRECTOR US ARMY RESEARCH LAB AMSRL D DR D SMITH 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	DIRECTOR US ARMY RESEARCH LAB AMSRL CS IS R 2800 POWDER MILL RD ADELPHI MD 20783-1197
3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI OK TL 2800 POWDER MILL RD ADELPHI MD 20783-1197
3	DIRECTOR US ARMY RESEARCH LAB AMSRL CS IS T 2800 POWDER MILL RD ADELPHI MD 20783-1197

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
	<u>ABERDEEN PROVING GROUND</u>
2	DIR USARL AMSRL CI LP (BLDG 305)

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
5	UNIVERSITY OF CALIFORNIA 5130 ETCHEVERRY HALL BERKELEY CA 94720
2	SRI INTERNATIONAL CTR FOR FRACTURE PHYSICS D A SHOCKEY 333 RAVENSWOOD AVE MENLO PARK CA 94025
1	BOEING COMMERCIAL AIRPLANES AIRPLANE PERFORMANCE AND PROPULSION DR J E FARSTAD SEATTLE WA 98101