ARMY RESEARCH LABORATORY

Temporal Evolution of the LIBS Spectrum of Aluminum Metal in Different Bath Gases

by Thuvan N. Piehler, Frank C. DeLucia, Jr., Chase A. Munson, Barrie E. Homan, Andrzej W. Miziolek, and Kevin L. McNesby

ARL-TR-3371 **December 2004**

Approved for public release; distribution is unlimited.

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

Army Research Laboratory
Aberdeen Proving Ground, MD 21005-5066

ARL-TR-3371 **December 2004**

Temporal Evolution of the LIBS Spectrum of Aluminum Metal in Different Bath Gases

Thuvan N. Piehler, Frank C. DeLucia, Jr., Chase A. Munson, Barrie E. Homan, Andrzej W. Miziolek, and Kevin L. McNesby
Weapons and Materials Research Directorate, ARL

Approved for public release; distribution is unlimited.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.
PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

1. REPORT DATE *(DD-MM-YYYY)*	2. REPORT TYPE	3. DATES COVERED (From - To)
December 2004	Final	15 August 2003–15 August 2004

4. TITLE AND SUBTITLE
Temporal Evolution of the LIBS Spectrum of Aluminum Metal in Different Bath Gases

5a. CONTRACT NUMBER

5b. GRANT NUMBER

5c. PROGRAM ELEMENT NUMBER

6. AUTHOR(S)
Thuvan N. Piehler, Frank C. DeLucia, Jr., Chase A. Munson, Barrie E. Homan, Andrzej W. Miziolek, and Kevin L. McNesby

5d. PROJECT NUMBER
AH80

5e. TASK NUMBER

5f. WORK UNIT NUMBER

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)
U.S. Army Research Laboratory
ATTN: AMSRD-ARL-WM-BD
Aberdeen Proving Ground, MD 21005-5066

8. PERFORMING ORGANIZATION REPORT NUMBER
ARL-TR-3371

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)
ASEE
1818 N. Street N.W., Ste 600
Washington, DC 20036

10. SPONSOR/MONITOR'S ACRONYM(S)

11. SPONSOR/MONITOR'S REPORT NUMBER(S)

12. DISTRIBUTION/AVAILABILITY STATEMENT
Approved for public release; distribution is unlimited.

13. SUPPLEMENTARY NOTES

14. ABSTRACT
The spectral emission of gas phase aluminum (Al) and Al oxide was measured during and immediately after exposure of a bulk Al sample to a laser-induced spark produced by a focused, pulsed laser beam (Nd:YAG, 10 ns pulse duration, 35 mJ/pulse, $\lambda = 1064$ nm). The spectral emission was measured as a function of time after the onset of the laser pulse, and was also measured in different bath gases (air, N_2, O_2, and He).

15. SUBJECT TERMS
spectroscopy, laser, LIBS, aluminum

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE			Thuvan Piehler
UNCLASSIFIED	UNCLASSIFIED	UNCLASSIFIED	UL	30	19b. TELEPHONE NUMBER (*Include area code*) 410-306-0884

Standard Form 298 (Rev. 8/98)
Prescribed by ANSI Std. Z39.18

Contents

List of Figures **iv**

List of Tables **iv**

1. Introduction **1**

2. Experimental **2**

3. Results and Discussion **3**

3.1 Emission Spectra of an Al Rod in Air 3

3.2 Temporal Evolution of Al and AlO Emission 4

3.3 Temperature Calculations 8

3.4 Electron Density 10

4. Conclusions **12**

5. References **13**

Distribution List **15**

List of Figures

Figure 1. Schematic of the experimental setup used to measure LIBS spectra. 2

Figure 2. A portion of LIBS spectrum of an Al rod in air with a 20-μs gate delay and 2-μs gate (300–420-nm region).....3

Figure 3. A portion of LIBS spectrum of an Al rod in air with a 20-μs gate delay and 2-μs gate (450–550-nm region).....4

Figure 4. A portion of LIBS spectrum of an Al rod in air with a 20-μs gate delay and 2-μs gate (740–760-nm region).....4

Figure 5. LIBS spectrum of an Al rod in air, at various gate delays. The gate pulse width is 2 μs.....5

Figure 6. Temporal emission evolution of Al LIBS in O_2. The gate pulse width is 2 μs. 5

Figure 7. Temporal emission evolution of Al LIBS in He. The gate pulse width is 2 μs. 6

Figure 8. Temporal emission evolution of Al LIBS in N_2. The gate pulse width is 2 μs. 6

Figure 9. Comparison of time evolution of emission intensity for Al (396-nm) LIBS signal in air, He, N_2, and O_2 with a 2-μs gate pulse width. 7

Figure 10. A plot of logarithm of intensity at 396 nm vs. time for the different bath gases used in these experiments. 7

Figure 11. The maximum emission intensity of the AlO band near 484 nm as a function of time for the bath gases air and O_2. 8

Figure 12. The maximum emission intensity of the AlO band near 484 nm as a function of time for the bath gases He and N_2.....8

Figure 13. A Boltzman plot for 308.34-, 309.44-, 394.56-, and 396.26-nm Al I lines in O_2. The gate pulse width is 2 μs. The gate pulse delay is 15 μs. 9

Figure 14. Excitation temperature vs. gate pulse delay with a 2-μs gate width. 10

Figure 15. Electron density of Al vs. gate pulse delay with a 2-μs gate width. 11

Figure 16. Excitation temperature vs. electron density profile in different atmospheres. 12

List of Tables

Table 1. Spectroscopic parameters for Al I and Al II investigated lines. 9

1. Introduction

Aluminum (Al) is a common ingredient of explosives and propellants. In explosives, Al is used to augment air blast, raise reaction temperature, and create incendiary effects (*1*). In rocket propellants, Al is used to increase thermal energy and elevate the flame temperature (*2*). A proposed mechanism for the combustion of Al in O_2 follows(*3*):

$$Al\ (l) \rightarrow Al\ (g) \qquad \Delta H = 317.7\ kJ \tag{1}$$

$$AlO + Al\ (l) \rightarrow Al_2O \qquad \Delta H = -224.0\ kJ \tag{2}$$

$$Al\ (g) + O_2 \rightarrow AlO + O \qquad \Delta H = 6.53\ kJ \tag{3}$$

$$Al\ (g) + O + M \rightarrow AlO + M \qquad \Delta H = -492.1\ kJ \tag{4}$$

$$AlO + O_2 \rightarrow AlO_2 + O \qquad \Delta H = -78.6\ kJ \tag{5}$$

$$AlO + AlO_2 \rightarrow Al_2O_3\ (l) \qquad \Delta H = -1557.2\ kJ \tag{6}$$

$$Al_2O + O_2 \rightarrow Al_2O_3\ (l) \qquad \Delta H = -1562\ kJ \tag{7}$$

For some explosive materials, Al may be used to tailor performance to specific needs. Measurements of relative amounts of Al metal and Al oxide (AlO) during explosions of energetic materials may provide insight into increasing the performance of Al-containing explosives. The experiments described here are a preliminary study of the application of laser-induced breakdown spectroscopy (LIBS) to this problem.

Although best known for high selectivity for metals analysis (*4*), LIBS has also been used to detect energetic materials (*5*), trace elements in liquids (*6*), organic compounds in ambient air (*7*), and some biological materials (*8*). In LIBS, a pulsed laser focused onto a target material converts some of the material into a plasma of ions and electrons, with temperatures that may approach 20,000 K (*9*). As the plasma cools, some of the energy is radiated as light. When measured using a spectrograph, the wavelengths of the emitted light are characteristic to the elemental components of the target, while the intensity of light over a given wavelength range may yield the proportion of that element within the target material (*10*). Additionally, the time evolution of the emission following the laser pulse may be used to identify certain chemical reactions occurring in the plasma as it cools.

In this report, we measure the emission from a laser-induced spark produced by focusing a pulsed Nd:YAG laser onto the surface of an Al rod. The emission is spectrally and temporally resolved, the effect of different bath gases (air, O_2, N_2, and He) on the emission is measured, and temperature and electron density are calculated.

2. Experimental

A schematic of the simple LIBS system used in this work is shown in figure 1. Briefly, a light pulse (~10 ns, 35 mJ per pulse) from an actively Q-switched Nd-YAG laser (Big Sky Laser Technologies Inc., Bozeman, MT) emitting at a wavelength of 1064 nm was focused by a 50-mm convex lens onto the surface of an Al rod. A Si-Si optical fiber (600-μm core diameter) collected the emission from the plasma spark. A lens was placed in front of the fiber so that the plasma spark was sufficiently defocused to eliminate any spatial effects. An echelle spectrometer (Catalina Scientific Corp., Tucson, AZ) fitted with a gated, intensified CCD camera (Andor Technology Com., Model DH 734-18-03) was used to measure the emitted light. The entire experiment, including background measurement, laser control, data acquisition, and data processing, was controlled by a laptop computer (Dell).

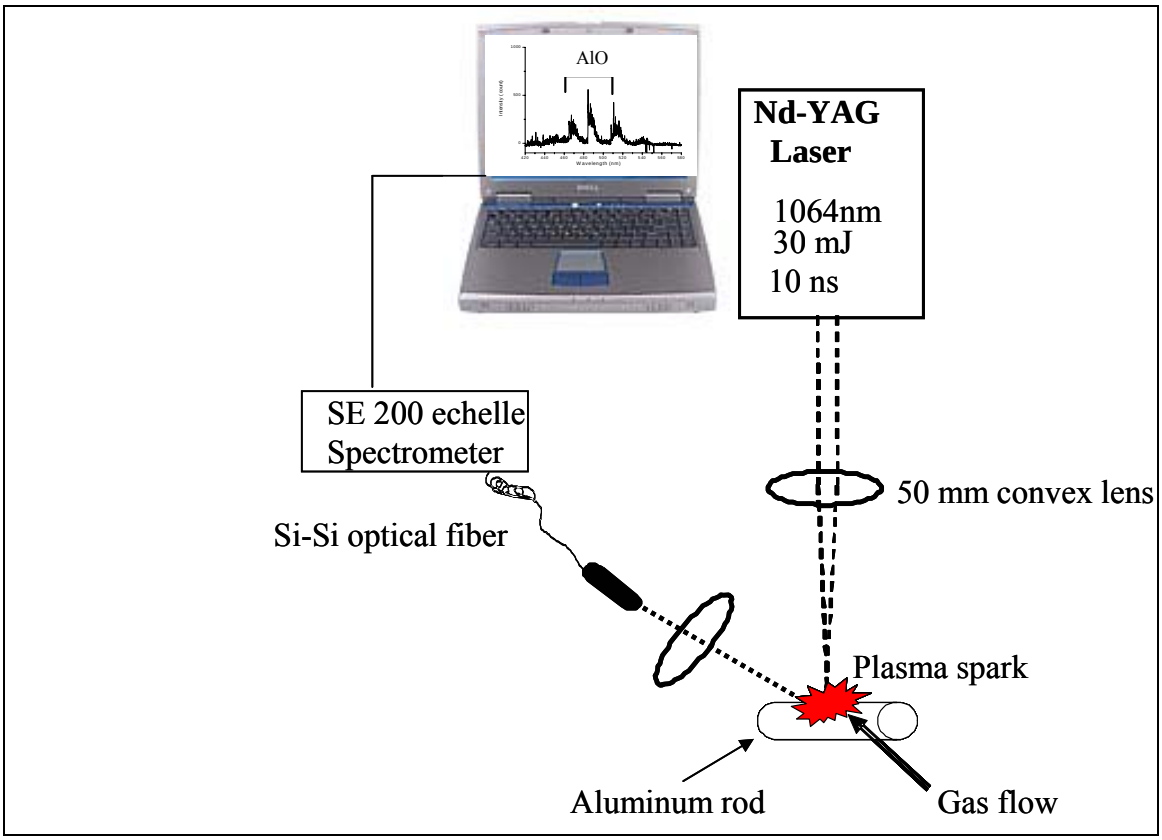

Figure 1. Schematic of the experimental setup used to measure LIBS spectra.

Prior to the measurement of each LIBS spectrum, a background spectrum was measured and subsequently subtracted from the sample spectral data. In an attempt to minimize errors due to shot to shot variations in the laser output power (~5%), each spectrum used in the data analysis is the average of 50 "single shot" spectra. For each LIBS spectrum measured, the Al rod was

repositioned so only a new sample was exposed to the laser-induced spark. To enable comparison with previous LIBS studies of Al (*11*), a detector gate width of 2 μs was used for these experiments. Detector gate delays (relative to the Q-switch of the Nd:YAG laser) ranged from 0 to 30 μs. The composition of Al rods used in this study was Al 91.4%, Cu 5.67%, Fe 1.28%, Li 1.11%, and minor constituents (Mg, Mn, Ti, and Zn percentage <0.5% by weight). Bath gases (N_2, O_2, and He) were obtained from Matheson and were used without any further purification. Typical flow rates were ~2 L/min. The gas flow was delivered via 4-mm I.D. Tygon tubing. The exit port of the tubing was ~5 mm from the location of the plasma volume.

3. Results and Discussion

3.1 Emission Spectra of an Al Rod in Air

The most intense regions of the Al rod LIBS spectrum (bath gas = air [ambient], gate width = 2 μs, gate delay = 20 μs) are shown in figures 2, 3, and 4. The first spectral window (figure 2) from 300 to 420 nm includes emission from gas phase aluminum (Al I) at wavelengths of 308.34, 309.44, 394.56, and 396.26 nm. The second spectral window (figure 3; 420–580 nm) includes emission from the gas phase molecular species AlO, with the most intense emission near 484.58 nm. The third spectral window (figure 4; 740–760 nm) includes emission from gas phase aluminum (Al II) at a wavelength of 747.14 nm. For Al combustion in air, previous investigators have suggested that above the melting point of Al_2O_3 (2315 K) (*12*), the Al species with highest partial pressures are Al and AlO.

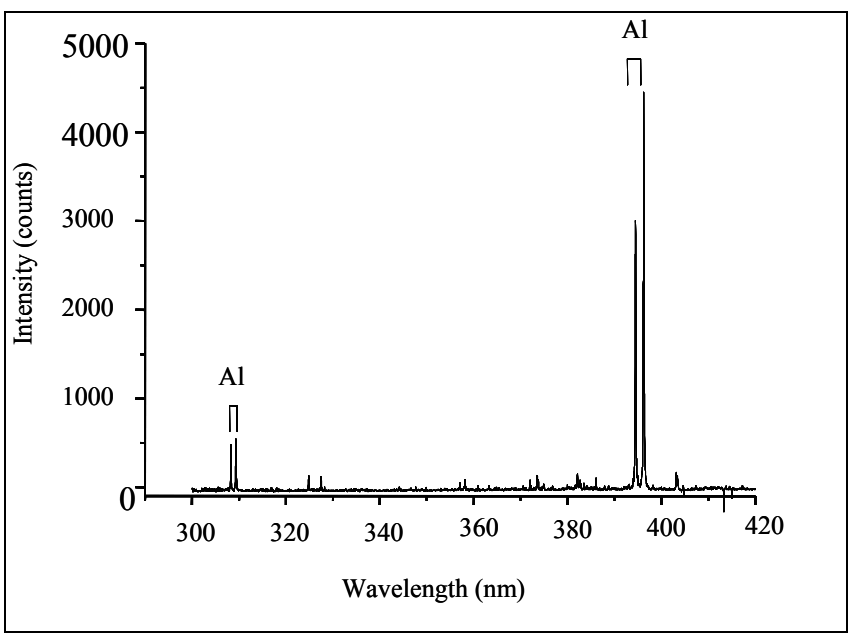

Figure 2. A portion of LIBS spectrum of an Al rod in air with a 20-μs gate delay and 2-μs gate (300–420-nm region).

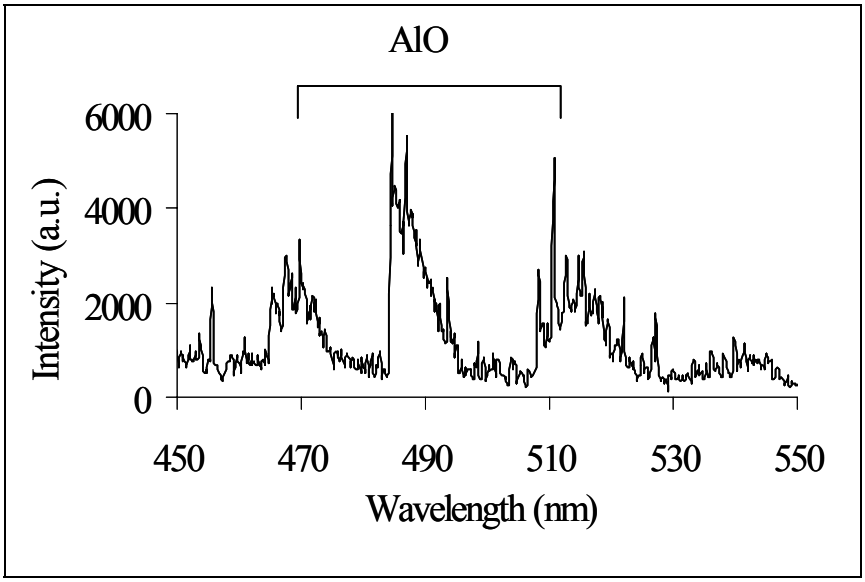

Figure 3. A portion of LIBS spectrum of an Al rod in air with a 20-μs gate delay and 2-μs gate (450–550-nm region).

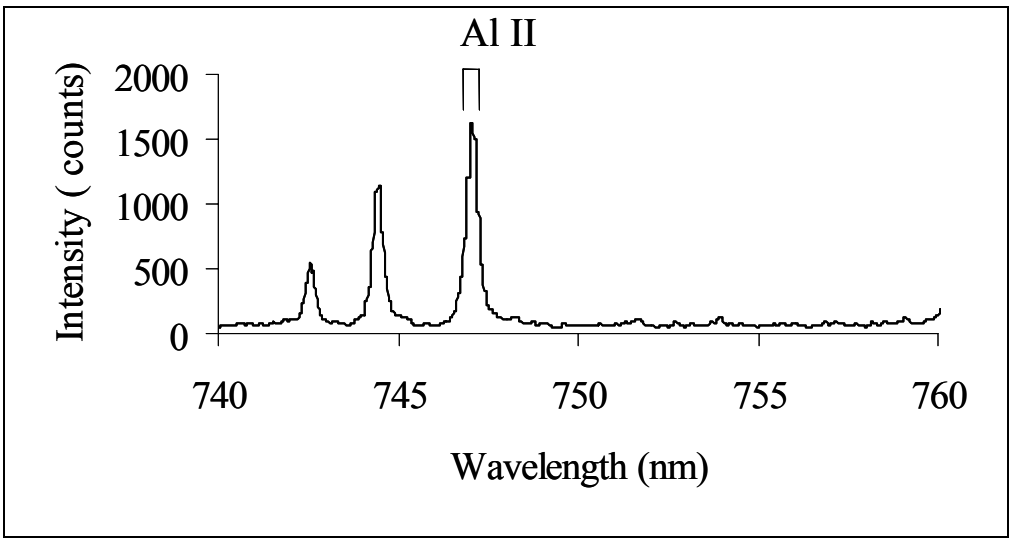

Figure 4. A portion of LIBS spectrum of an Al rod in air with a 20-μs gate delay and 2-μs gate (740–760-nm region).

3.2 Temporal Evolution of Al and AlO Emission

Figure 5 shows the LIBS spectrum of an Al rod in air at various gate delays (gate width = 2 μs). As seen in figure 5, the Al I line (396.2 nm) reaches its maximum intensity in air ~5 μs after the laser pulse. The band from AlO emission (484.4 nm) reaches its maximum intensity ~20 μs after the laser shot. This is qualitatively consistent with the combustion mechanism for Al in oxygen, outlined in reactions 1–7 earlier.

LIBS spectra of the Al rod (measured from 350 to 580 nm) at various gate delays (gate width = 2 μs) for the bath gases O_2, He, and N_2 are shown in figures 6, 7, and 8, respectively. For comparison, the peak intensities of the Al I line in each figure have been normalized. It is worth noting that the emission near 484 nm (from AlO) in figure 7 (He bath gas) and figure 8 (N_2 bath gas) is vanishingly small compared to the emission near 484 nm in figure 5 (air bath gas) and figure 6 (O_2 bath gas).

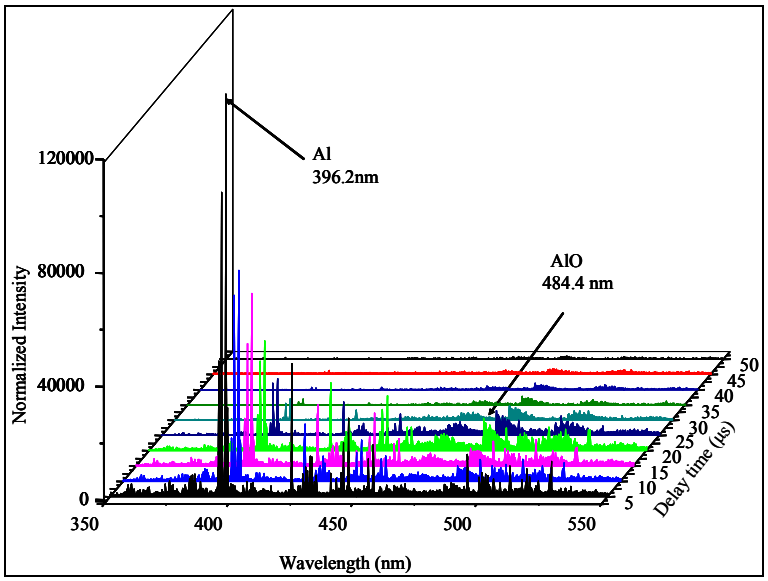

Figure 5. LIBS spectrum of an Al rod in air, at various gate delays. The gate pulse width is 2 μs.

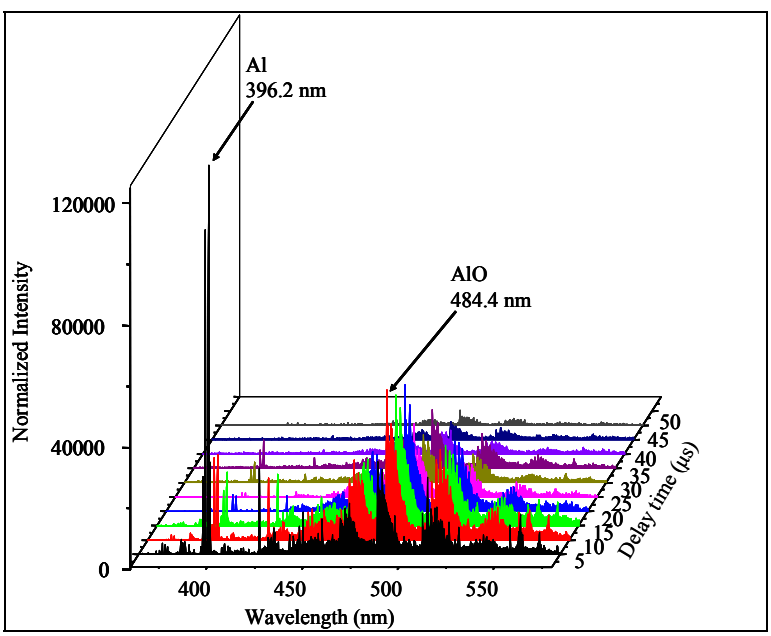

Figure 6. Temporal emission evolution of Al LIBS in O_2. The gate pulse width is 2 μs.

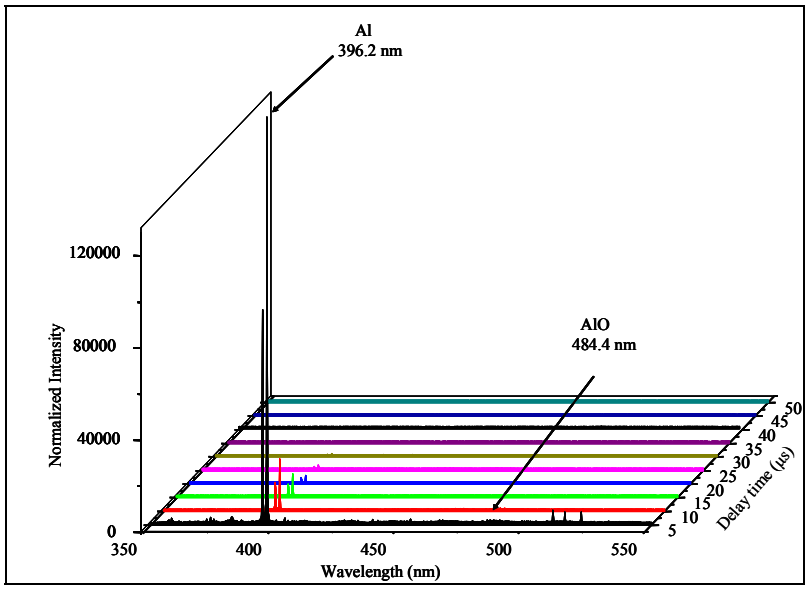

Figure 7. Temporal emission evolution of Al LIBS in He. The gate pulse width is 2 µs.

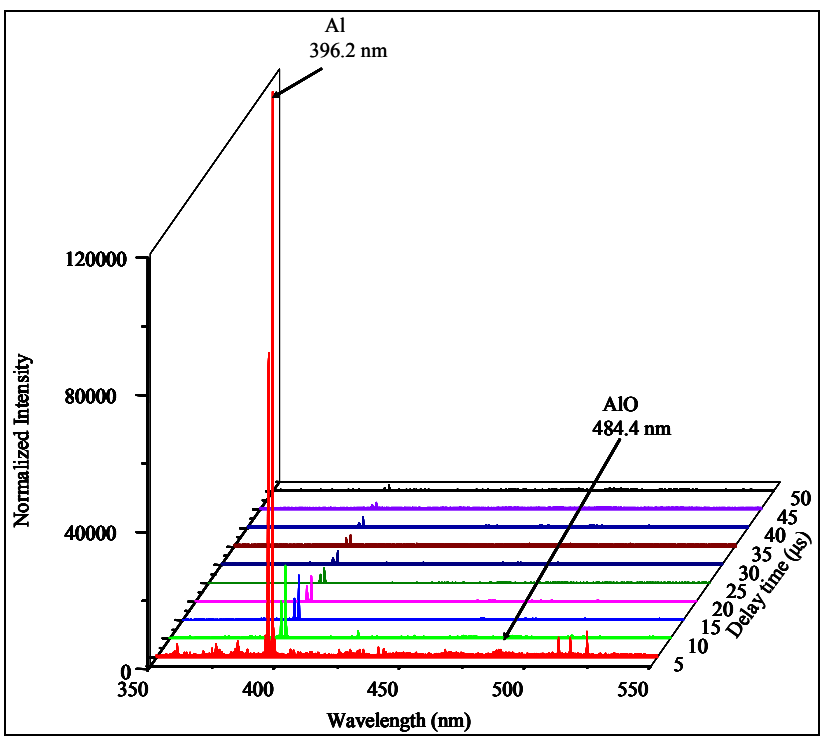

Figure 8. Temporal emission evolution of Al LIBS in N_2. The gate pulse width is 2 µs.

Figure 9 shows that the decrease in Al emission (396 nm) with time appears exponential. Figure 10 shows a pseudo-first-order plot of logarithm of intensity at 396 nm vs. time. From this plot, the deactivation of Al (fastest to slowest) as a function of bath gas is O_2~He>air>N_2. Figures 11 and 12 (expanded by a factor of 10,000) show the maximum emission intensity of the AlO band

near 484 nm as a function of time for reactive (air and O_2) and nonreactive (He and N_2) bath gases, respectively. Figure 11 shows that the maximum emission from AlO occurs 10 µs after the laser pulse in the pure O_2 atmosphere, while the intensity in air reached a maximum 20 µs after the laser pulse. Therefore, we believe the main source of AlO emission in bath gases of O_2 and air is AlO formed by the reaction of Al (g) with ambient O_2, analogous to reactions 3 and 4 for the combustion of Al in O_2. This is also supported by the increase in AlO emission as the bath gas is changed from air (figure 5) to O_2 (figure 6).

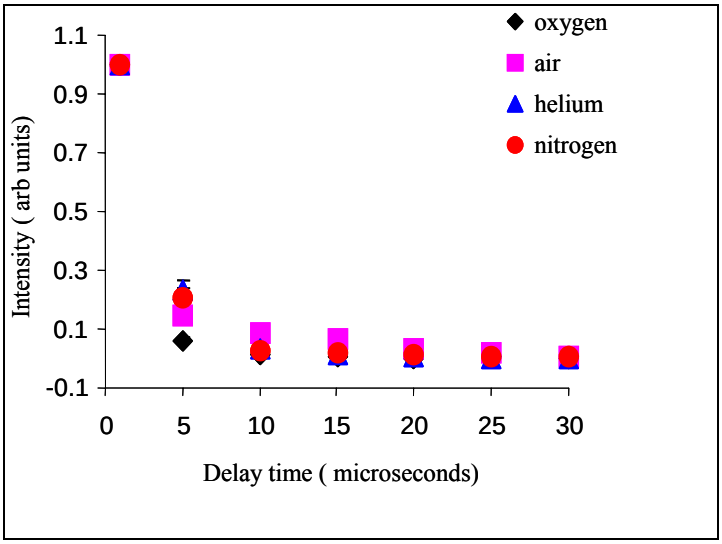

Figure 9. Comparison of time evolution of emission intensity for Al (396-nm) LIBS signal in air, He, N_2, and O_2 with a 2-µs gate pulse width.

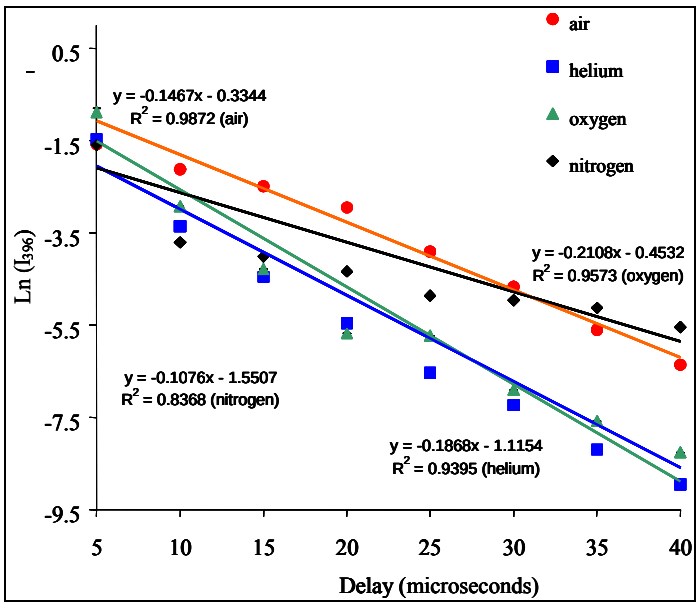

Figure 10. A plot of logarithm of intensity at 396 nm vs. time for the different bath gases used in these experiments.

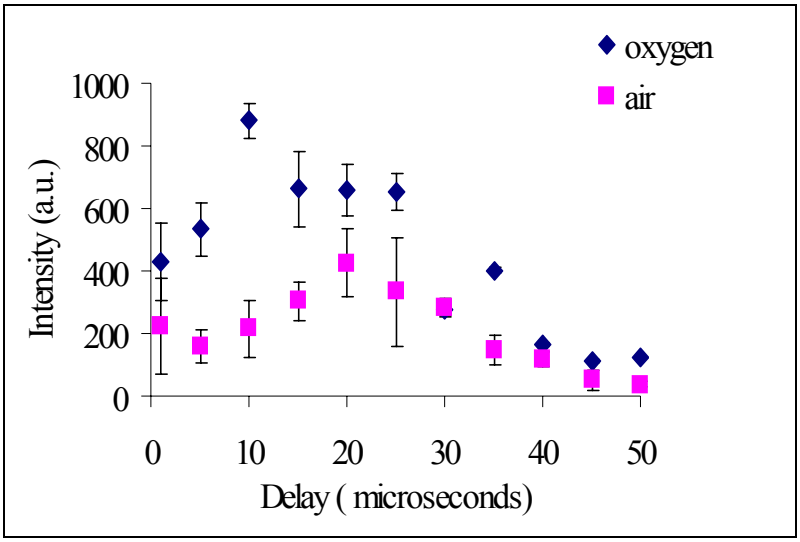

Figure 11. The maximum emission intensity of the AlO band near 484 nm as a function of time for the bath gases air and O_2.

Figure 12 shows that, in the absence of ambient O_2, the temporal behavior of the AlO emission is similar to that of the Al emission; i.e., the temporal behavior of the AlO emission in the unreactive bath gases is similar to emission from material (Al) native to the Al rod. Therefore, we believe the source of the AlO emission in the absence of ambient O_2 is the Al_2O_3 layer on the Al metal.

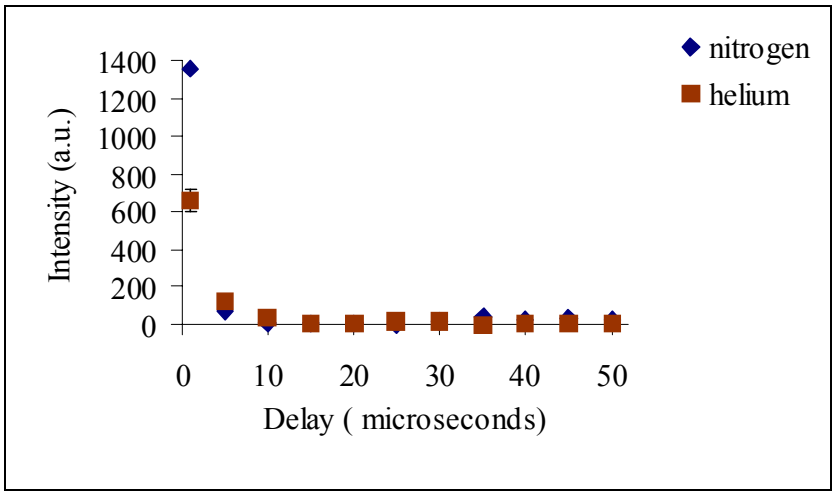

Figure 12. The maximum emission intensity of the AlO band near 484 nm as a function of time for the bath gases He and N_2.

3.3 Temperature Calculations

For the temperature calculations reported, we assume that for the gate width used (2 μs), the time rate of change of the plasma temperature is small, and that light emission collected and analyzed is emitted from a gas region that is approximately homogeneous in temperature and composition.

This assumption of "local thermodynamic equilibrium" is necessary when calculating temperatures using a Boltzmann distribution. The intensities of Al I spectral lines at wavelengths of 308.34, 309.44, 394.56, and 396.26 nm were used to calculate temperatures at different gate pulse delays according to the following equation:

$$\mathrm{Ln}\,(I/\,(g_i\,A_{ki}))= -\,(E_k\,/\,kT) + \mathrm{Ln}\,(C_\alpha F/\,U_\alpha(T))\,, \qquad (8)$$

where I is the peak line intensity of atomic species α with concentration C_α, E_k is the upper energy level, T is the plasma temperature, $U_\alpha(T)$ is the partition function of the species α, k is the Boltzmann constant, F is a constant depending on experimental conditions, A_{ki} is the transition probability, and g_i is the statistical weight for the upper level. Spectroscopic data (table 1) were obtained from the National Institute of Standards and Technology database (*13*). A plot of Ln $(I\,/\,(g_i\,A_{ki}))$ as a function of E_k will have a slope equal to –1/kT. A typical Boltzman plot using equation 8 is shown in figure 13.

Table 1. Spectroscopic parameters for Al I and Al II investigated lines.

	Wavelength (nm)	**A_{kj} ($10^8\ s^{-1}$)**	**E_k (eV)**	**g_i**	**ω (nm)**
Al I	308.34	0.63	4.021485	2	—
	309.44	0.74	4.021650	4	—
	394.56	0.49	3.142721	2	—
	396.26	0.98	3.142721	2	—
Al II	466.30	0.53	13.25646	3	6.85×10^{-3}
	747.14	0.94	15.30840	7	1.26×10^{-2}

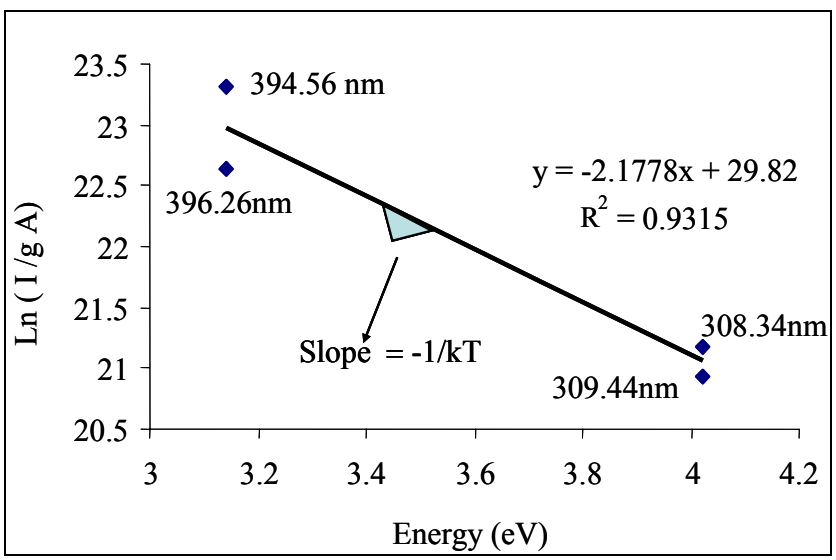

Figure 13. A Boltzman plot for 308.34-, 309.44-, 394.56-, and 396.26-nm Al I lines in O_2. The gate pulse width is 2 μs. The gate pulse delay is 15 μs.

Temperatures calculated using equation 8 and spectral line intensities from LIBS spectra measured in different bath gases are shown in figure 14. These calculated temperatures are in good agreement with previously reported calculated temperatures for similar systems (*14–16*). In general, the calculated temperature exhibits an approximately exponential decay over the emission lifetime.

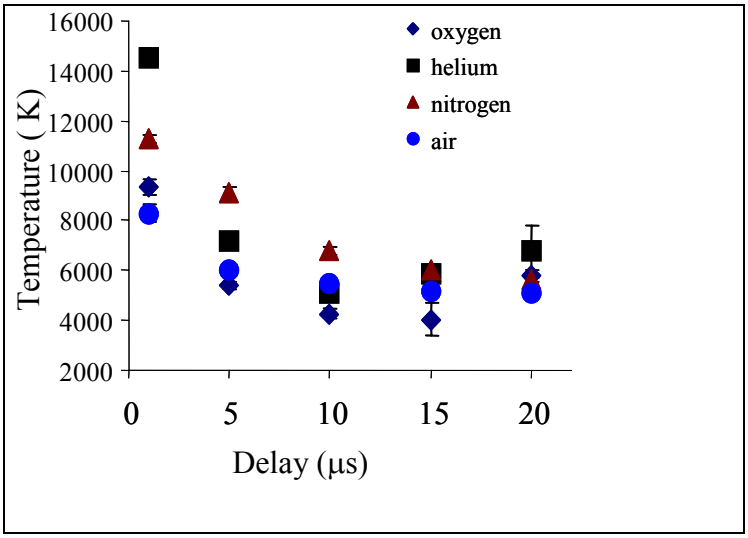

Figure 14. Excitation temperature vs. gate pulse delay with a 2-μs gate width.

3.4 Electron Density

The electron density (N_e) was determined using the Stark broadening effect (*17*) and assuming the plasma to be optically thin (negligible self absorption) for the Al II emission line at 747.14 nm. Stark broadening parameters are available for the lines at 747.14 and 466.3 nm (*18*). The Al II line at 466.3 nm was not used because this line is partially obscured by the AlO band near 484 nm. The relation between the line width (full width at half maximum [FWHM]) of the Stark broadened line and the electron density is given by equation 9:

$$\Delta\lambda_{1/2} = 2\omega\,(N_e / 10^{16}) + 3.5\,A\,(N_e / 10^{16})^{1/4}\;\;(1 - BN_D^{\;-1/3})\,\omega\,(N_e / 10^{16}), \qquad (9)$$

where $\Delta\lambda_{1/2}$ is the line width (FWHM), ω is the Stark broadening parameter, A is the ion broadening parameter, N_D is the number of particles in the Debye sphere, and B is a coefficient equal to 1.2 for ions and 0.75 for neutral lines. The values of ω were taken from Coloa et al. (*18*).

The measured line width was corrected to first order by subtracting the contribution of the instrumental line broadening. The instrument line broadening was found to be 0.1 nm, as determined by measuring the emission lines from a calibrated mercury lamp. The first term on the right side of equation 9 is the contribution of electron broadening. The second term on the

right side of equation 9 is the quasistatic ion broadening contribution, which can to be neglected in this analysis (*19*). Equation 9 then reduces to

$$\Delta\lambda_{1/2} = 2\omega\ (N_e / 10^{16}). \tag{10}$$

In order to make a determination as to whether the local thermodynamic equilibrium conditions were satisfied for the selected spectral lines, the critical value of electron density distribution (N_e) was evaluated by following the procedure described by Aragon et al. (*20*). The critical limit of electron density distribution was determined from equation 11:

$$N_e \geq 1.6 \times 10^{12}\ T^{1/2}\ (E_k - E_i)^3\ . \tag{11}$$

For the experiments reported here, the critical electron densities varied from 3×10^{15} to 9.5×10^{15} cm^{-3} for the temperature range from 4000 to 14,500 K. The lowest calculated electron density value exceeded these critical values by a factor of 20 for the range of temperatures calculated using the Boltzmann equation (equation 8). As seen in figure 15, there is a general trend toward lower electron densities at later decay times (also see figure 16) as the plasma cools.

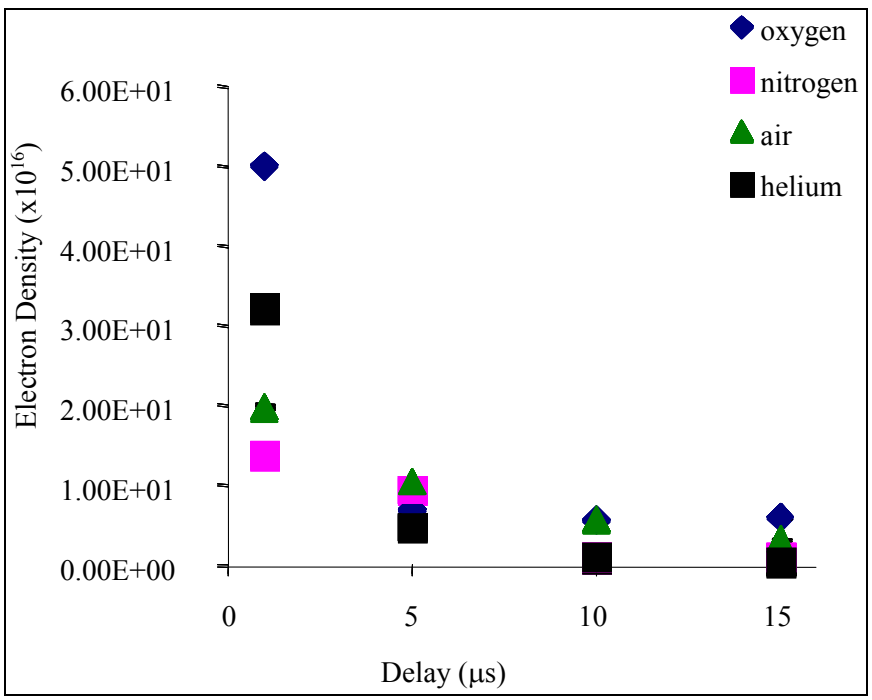

Figure 15. Electron density of Al vs. gate pulse delay with a 2-µs gate width.

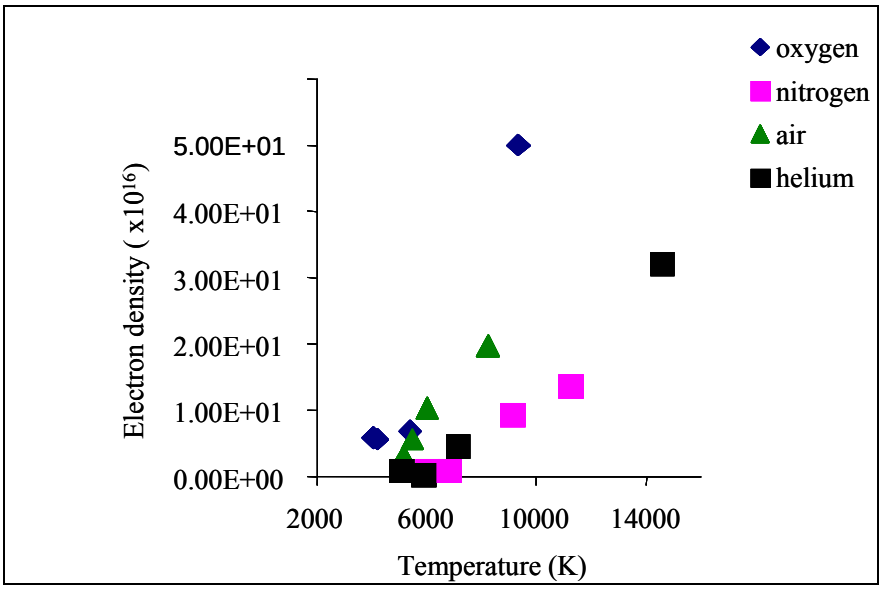

Figure 16. Excitation temperature vs. electron density profile in different atmospheres.

4. Conclusions

Measurements of the emission of AlO following exposure of an Al metal surface to a laser-induced spark have been carried out for bath gases of air, O_2, N_2, and He. Results of these experiments indicate that virtually all of the AlO emission is from AlO formed by the reaction of Al vapor with O_2 from the bath gas (if present). Emission from AlO initially present as an Al_2O_3 oxide layer on the metal sample was vanishingly small for emission spectra measured in bath gases of N_2 and He, when compared to the AlO emission measured in air and in O_2 bath gases. However, it is possible to distinguish the AlO emission from the Al_2O_3 oxide layer from AlO formed by reaction with ambient O_2 by examining the temporal behavior of the emission. The temporal behavior of Al and AlO emission following Al metal exposure to a laser-induced spark (in air and O_2) is consistent with known chemical mechanisms for Al combustion in O_2. Finally, calculations of temperature assuming a Boltzmann distribution of Al emission lines gives results in good agreement with calculations by previous investigators.

5. References

1. Brousseau, P.; Dorsett, H.; Cliff, M. Detonation Properties of Explosives Containing Nanometric Aluminum Powder in Microdetonics. *The Twelfth International Detonation Symposium*, San Diego, CA, 2002.

2. Mueller, D. C.; Turns, S. R. A Theoretical Evaluation of Secondary Atomization Effects on Engine Performance for Aluminum Gel Propellants. *J. Propulsion and Power* **1996**, *12*, 591–597.

3. Yuasa, S.; Zhu, Y.; Sogo, S. Ignition and Combustion of Aluminum in Oxygen/Nitrogen Mixture Streams. *Combustion and Flame* **1997**, *108*, 387–396.

4. Capitelli, F.; Coloa, F.; Provenzano, M. R.; Fantoni, R.; Brunetti, G.; Senesi, N. Determination of Heavy Metals in Soils by Laser-Induced Breakdown Spectroscopy. *Geoderma* **2002,** *106*, 45–62.

5. DeLucia, F. C., Jr.; Harmon, R. S.; McNesby, K. L.; Winkel, R. J., Jr.; Miziolek, A. W. Laser-Induced Breakdown Spectroscopy Analysis of Energetic Materials. *Appl. Opt. 42* **2003,** *30*, 6148.

6. Yueh, F. Y.; Sharma, R. C.; Singh, J. P.; Zhang, H.; Spencer, W. A. Evaluation of the Potential of Laser-Induced Breakdown Spectroscopy for Detection of Trace Element in Liquid. *J. Air Waste Manag. Assoc.* **2002**, *52* (11), 1307–15.

7. Portnov, A.; Rosenwaks, S.; Bar, I. Emission Following Laser-Induced Breakdown Spectroscopy of Organic Compounds in Ambient Air. *Appl. Opt*. **2003**, *42* (15), 2835–42.

8. Samuel, A. C.; DeLucia, F. C., Jr.; McNesby, K. L.; Miziolek, A. W. Laser-induced Breakdown Spectroscopy of Bacterial Spores, Molds, Pollens, and Protein: Initial Studies of Discrimination Potential. *Appl. Opt.* **2003**, *42* (30), 6205.

9. Simeonsson, J. B.; Miziolek, A. W. Time-Resolved Emission Studies of ArF Laser Produced Microplasmas. *Appl. Opt.* **1993**, *32* (6), 939–947.

10. Wainner, R. T.; Harmon, R. S.; Miziolek, A. W.; McNesby, K. L.; French, P. D. Analysis of Environmental Lead Contamination: Comparison of LIBS Field and Laboratory Instruments. *Spectrochemica Acta Part B* **2001**, *56* (6), 777–793.

11. Awadhesh, K. R.; Hansheng, Z.; Fang Yu, Y.; Singh, J. P.; Weisburg, A. Parametric Study of a Fiber-Optic Laser-Induced Breakdown Spectroscopy Probe for Analysis of Aluminum Alloys. *Spectrochimica Acta Part B* **2001**, *56* (12), 2371–2383.

12. Dokhan, A.; Price, E. W.; Seitzman, J. M.; Sigman, R. K. Combustion Mechanisms of Bimodal and Ultra Fine Aluminum in Ammonium Perchlorate Solid Propellant. *AIAA* **2002**, 4173.

13. National Institute of Standards and Technology Atomic Spectra Database Lines Form. http://physics.nist.gov/cgi-bin/AtData/lines_form (accessed 1 October 2004)

14. Le Drogoff, B.; Margot, J.; Chaker, M.; Sabsabi, M.; Barthelemy, O.; Johnston, T. W.; Laville, S.; Vidal, F.; Von Kaenel, Y. Temporal Characterization of Femtosecond Laser Pulses Induced Plasma for Spectrochemical Analysis of Aluminum Alloys. *Spectrochimica Acta Part B* **2001**, *56*, 987–1002.

15. Liu, H. C.; Mao, X. L.; Yoo, J. H.; Russo, R. E. Early Phase Laser Induced Plasma Diagnostic and Mass Removal During Single Pulse Laser Ablation of Silicon. *Spectrochimica Acta Part B* **1999**, *54*, 1607.

16. Amoruso, S. Modeling of UV-Pulsed Laser Ablation of Silicon. *Appl. Phys. A* **1999**, *69*, 323.

17. Saramdaev, E. V.; Salakhov, M. K. H. Regularities in the Stark Widths and Shifts of Spectral Lines of Singly-Ionized Aluminum. *J. Quant. Spectrsc. Radiat. Transfer* **1996**, *56* (3), 399–407.

18. Coloa, F.; Lazic, V.; Fantoni, F.; Pershin, S. A Comparison of Single and Double Pulse Laser-Induced Breakdown Spectroscopy of Aluminum Samples. *Spectrochimica Acta Part B* **2002**, *57*, 1167–1179.

19. Abdellatif, G.; Imam, H. A Study of the Laser Plasma Parameters at Different Laser Wavelengths. *Spectrochimica Acta Part B* **2002**, *57*, 1155–1165.

20. Aragon, C.; Bengoechea, J.; Aguilera, J. A. Influence of the Optical Depth on Spectral Line Emission From Laser-Induced Plasmas. *Spectrochimica Acta Part B* **2001**, *56*, 619.

NO. OF COPIES	ORGANIZATION
1 (PDF ONLY)	DEFENSE TECHNICAL INFORMATION CTR DTIC OCA 8725 JOHN J KINGMAN RD STE 0944 FORT BELVOIR VA 22060-6218
1	US ARMY RSRCH DEV & ENGRG CMD SYSTEMS OF SYSTEMS INTEGRATION AMSRD SS T 6000 6TH ST STE 100 FORT BELVOIR VA 22060-5608
1	INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN 3925 W BRAKER LN STE 400 AUSTIN TX 78759-5316
1	US MILITARY ACADEMY MATH SCI CTR EXCELLENCE MADN MATH THAYER HALL WEST POINT NY 10996-1786
1	DIRECTOR US ARMY RESEARCH LAB IMNE AD IM DR 2800 POWDER MILL RD ADELPHI MD 20783-1197
3	DIRECTOR US ARMY RESEARCH LAB AMSRD ARL CI OK TL 2800 POWDER MILL RD ADELPHI MD 20783-1197
3	DIRECTOR US ARMY RESEARCH LAB AMSRD ARL CS IS T 2800 POWDER MILL RD ADELPHI MD 20783-1197

NO. OF COPIES	ORGANIZATION
	ABERDEEN PROVING GROUND
1	DIR USARL AMSRD ARL CI OK TP (BLDG 4600)

NO. OF COPIES	ORGANIZATION
3	AIR FORCE RSCH LAB EDWARDS (AFRL) AFRL EDWARDS/USC ERC/AFRL K CRISTE 10 E SATURN BLVD EDWARDS AFB CA 93524
1	AIR FORCE RSCH LAB AFRL/PRSP BLDG 8451 G DRAKE 10 E SATURN BLVD EDWARDS AFB CA 93524
1	AIR FORCE RSCH LAB EGLIN (AFRL) AFRL/MNME W COOPER 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MNME M FAJARDO 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MNAV S FEDERLE 101 W EGLIN BLVD STE 342 EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MN S KORN 101 W EGLIN BLVD STE 105 EGLIN AFB FL 32542-6810
1	AIR FORCE RSCH LAB AFRL/MNME M KRAMER 2306 PERIMETER RD EGLIN AFB FL 32542-6810
1	AIR FORCE RSCH LAB AFRL/MNAC J KUJALA 101 W EGLIN BLVD STE 334 EGLIN AFB FL 32542-6810

NO. OF COPIES	ORGANIZATION
1	AIR FORCE RSCH LAB AFRL/MNME W R MAINES 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MNME T MCKELVEY 2306 PERIMETER RD EGLIN AFB FL 32542-5910
1	AIR FORCE RSCH LAB AFRL/MNME D W RICHARDS 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MNME C RUMCHIK 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MNME L STEWART 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE RSCH LAB AFRL/MNME K WALKER 2306 PERIMETER RD EGLIN AFB FL 32542
1	AIR FORCE AFOSR M BERMAN AFOSR 4015 WILSON BLVD RM 713 ARLINGTON VA 22203-1954
1	US ARMY ARDEC/WECAC AMSTA AR WEE/B3022 D DOWNS PICATINNY ARSENAL NJ 07806-5000
1	US ARMY TACOM ARDEC P HAN BLDG 3022 PICATINNY ARSENAL NJ 07806-5000

NO. OF COPIES	ORGANIZATION
1	US ARMY TACOM ARDEC AMSTA AR WEE A L HARRIS PICATINNY ARSENAL NJ 07806
1	US ARMY TACOM ARDEC AMSTA AR WEA BLDG 355 D KAPOOR PICATINNY ARSENAL NJ 07806
1	US ARMY TACOM ARDEC AMSTA AR WE BLDG 1 J LANNON PICATINNY ARSENAL NJ 07806-5000
1	US ARMY TACOM ARDEC AMSTA AR WEE/B3022 S NICOLICH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY TACOM ARDEC R PAWLICKI DOTC BLDG 3022 RM 222 PICATINNY ARSENAL NJ 07806-5000
1	US ARMY TACOM ARDEC V STEPANOV BLDG 3028 PICATINNY ARSENAL NJ 07806
1	US ARMY TACOM ARDEC R SURAPANENI BLDG 3022 PICATINNY ARSENAL NJ 07806-5000
1	CDR US ARMY TACOM ARDEC AMSTA AR WEE A T VLADIMIROFF PICATINNY ARSENAL NJ 07806
1	CDR US ARMY AMRDEC US AVIATION AND MISSILE CMD AMSAM RD PS PT R HATCHER REDSTONE ARSENAL AL 35989
1	CDR US ARMY AMRDEC US AVIATION AND MISSILE CMD AMSAM RD PS WF S HILL REDSTONE ARSENAL AL 35898-5247

NO. OF COPIES	ORGANIZATION
1	CDR US ARMY AMRDEC US AVIATION AND MISSILE CMD AMSAM RD PS WF A STULTS REDSTONE ARSENAL AL 5989-5247
1	CDR US ARMY AMRDEC US AVIATION AND MISSILE CMD AMSAM RD PS PT BLDG 7120 D THOMPSON REDSTONE ARSENAL AL 35989
1	US ARMY RSCH OFFICE D MANN PO BOX 12211 RSCH TRIANGLE PARK NC 27709-2211
1	NATL GROUND INTELLIGENCE CTR IANG GS MT/MS 306 C BEITER 2055 BOULDER RD CHARLOTTESVILLE VA 22911-8318
1	NATL GROUND INTELLIGENCE CTR IANG GS MT/MS 306 R YOBS 2055 BOULDER RD CHARLOTTESVILLE VA 22911-8318
1	CDR US ARMY SOLDIER SYSTEMS CTR AMSSB RIP B (N) M MAFFEO NATICK MA 01760-5019
1	CDR US ARMY SOLDIER SYSTEMS CTR AMSSB RIP B (N) J WARD NATICK MA 01760-5019
1	US ARMY SPECIAL OPERATIONS CMD CAG COMBAT APPLICATIONS GROUP L BOIVIN PO BOX 70660 FT BRAGG NC 28307

NO. OF COPIES	ORGANIZATION
1	US ARMY SPECIAL OPERATIONS CMD CAG COMBAT APPLICATIONS GROUP G GEORGEVITCH PO BOX 71859 FT BRAGG NC 28307-5000
1	US ARMY SPECIAL OPERATIONS CMD CAG COMBAT APPLICATIONS GROUP D JETER PO BOX 70660 FT BRAGG NC 28307
1	US MARINE CORPS CTR FOR EMERGING THREATS AND OPPORTUNITIES C CURCIO 3087 ROAN AVE BLDG 3087C QUANTICO VA 22134
1	US MARINE CORPS MARINE CORPS SYSTEMS CMD CESS PM NBC DEFENSE MEDICAL MCSC MED T EAGLES 20333 BARNETT AVE STE 315 QUANTICO VA 22134-5010
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV J BALDWIN 1 ADMINISTRATION CIRCLE CODE 477200D CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV T BOGGS CODE 4T4300D CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV CODE 4T4310D M CHAN CHINA LAKE CA 93555-6100

NO. OF COPIES	ORGANIZATION
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV CODE 4T4200D R CHAPMAN CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV CODE 478400D P DIXON 1 ADMINISTRATION CIRCLE CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV T FOLEY 1 ADMINISTRATION CIRCLE CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV K HIGA 1 ADMINISTRATION CIRCLE CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV CODE 477200D B LORMAND 1 ADMINISTRATION CIRCLE CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV CODE 477200D M MASON 1 ADMINISTRATION CIRCLE CHINA LAKE CA 93555-6100
1	NAVAL AIR WARFARE CTR NAVAIR WEAPONS DIV CODE 4T4320D T PARR CHINA LAKE CA 93555-6100
1	NAVAL ORDNANCE SAFETY AND SECURITY ACTIVITY D PORADA 23 STRAUSS AVE INDIAN HEAD MD 20640

NO. OF COPIES	ORGANIZATION
1	NAVAL ORDNANCE SAFETY AND SECURITY ACTIVITY K TOMASELLO FARAGUT HALL BLDG D323 23 STRAUSS AVE INDIAN HEAD MD 20640-1541
1	US NAVAL RSCH LAB CODE 6189 R MOWREY 4555 OVERLOOK AVE SW WASHINGTON DC 20375-5342
1	US NAVAL RSCH LAB CHEMISTRY DIV CODE 6125 J RUSSELL 4555 OVERLOOK AVE SW WASHINGTON DC 20375-5342
1	CDR NAVAL SEA SYSTEMS CMD INDIAN HEAD CODE 910A W KOPPES 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	CDR NAVAL SURFACE WARFARE CTR CODE 4023 BLDG3347 S D'ARCHE 300 HWY 361 CRANE IN 47522-5001
1	NAVAL SURFACE WARFARE CTR CODE G22 BLDG 221 R GARRETT 17320 DAHLGREN RD DAHLGREN VA 22448-5100
1	NAVAL SURFACE WARFARE CTR CODE G24 S HOCK 17320 DAHLGREN RD DAHLGREN VA 22448-5100
1	NAVAL SURFACE WARFARE CTR CODE G24 B KNOTT 17320 DAHLGREN RD DAHLGREN VA 22448-5100

NO. OF COPIES	ORGANIZATION
1	NAVAL SURFACE WARFARE CTR E LACY 17320 DAHLGREN RD DAHLGREN VA 22448-5100
1	NAVAL SURFACE WARFARE CTR CODE G22 S WAGGENER 17320 DAHLGREN RD DAHLGREN VA 22448-5100
1	NAVAL SURFACE WARFARE CTR CODE 910 W BLDG 600 V BELLITTO 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR BLDG 600 J CAREY 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 440C P CARPENTER 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 910F J CHANG 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR D CICHRA 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR EXPLOSIVES TEST & DEVELOPMENT CODE 370 D COOK 101 STRAUSS AVE BLDG 695 INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR R CRAMER 101 STRAUSS AVE INDIAN HEAD MD 20640

NO. OF COPIES	ORGANIZATION
1	NAVAL SURFACE WARFARE CTR CODE 90D R DOHERTY 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR M DUNN 101 STRAUSS AVE BLDG 695 INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR CODE ST A DUONG 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR BLDG 600 F FOROHAR 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR CODE 920J R GUIRGUIS 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR RSCH & TECHNOLOGY DEPT CODE 9100 BLDG 600 J HARPER 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR R JONES 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR ENERGETIC MATERIALS RSCH CODE 920L BLDG 600 V JOSHI 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR RSCH AND TECH DEPT CODE 910R R JOUET 101 STRAUSS AVE INDIAN HEAD MD 20640-5035

NO. OF COPIES	ORGANIZATION
1	NAVAL SURFACE WARFARE CTR BLDG 490 ROOM 220 C KNOTT 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR BLDG 600 J MANNION 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR BLDG D 323 CODE 4210M R MCCALL 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 90 P MILLER 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 920D BLDG 600 S MILLER 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 920 G PANGILINAN 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 920U BLDG 600 L PARKER 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE 920P BLDG 600 S PEIRIS 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR D ROSENBERG 101 STRAUSS AVE INDIAN HEAD MD 20640

NO. OF COPIES	ORGANIZATION
1	NAVAL SURFACE WARFARE CTR CODE 370JG BLDG 695 J ROGERSON 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR J SALAN 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR CODE CSE BLDG 600 A STERN 101 STRAUSS AVE INDIAN HEAD MD 20640-5035
1	NAVAL SURFACE WARFARE CTR CODE 4210D C WALSH 101 STRAUSS AVE INDIAN HEAD MD 20640
1	NAVAL SURFACE WARFARE CTR INDIAN HEAD CODE 910X BLDG 600 A WARREN 101 STRAUSS AVE INDIAN HEAD MD 20640
1	OFFICE OF NAVAL RSCH C BEDFORD 800 N QUINCY ST ARLINGTON VA 22217
1	NAVAL AIR SYSTEMS CMD PATUXENT (NAVAIR) HQ AIR 4 7 48150 SHAW RD BLDG 2109 RM 122 A GEHRIS PATUXENT RIVER MD 20670
1	OFFICE OF SECRETARY OF DEFENSE ODUSD/S&T 1777 N KENT ST STE 9030 D TAM ARLINGTON VA 22209

NO. OF COPIES	ORGANIZATION
1	PENTAGON LW&M LAND WARFARE & MUNITIONS D BAUM OUSD(AT&L)/DS/LW&M RM 3B1060 3090 DEFENSE PENTAGON WASHINGTON DC 20301-3090
1	OUSD(AT&L)/DS/LAND WARFARE & MUNITIONS S ROJAS RM 3B1060 3090 DEFENSE PENTAGON WASHINGTON DC 20301-3090
1	ARGONNE NATL LAB K CARNEY PO BOX 2528 IDAHO FALLS ID 83404
1	ARGONNE NATL LAB CHEMISTRY DIVISION J HESSLER 9700 SOUTH CASS AVE ARGONNE IL 60439-4831
1	LAWRENCE LIVERMORE NATL LAB PO BOX 808 L 092 A GASH LIVERMORE CA 94551
1	LAWRENCE LIVERMORE NATL LAB MS L 30 A KUHL PO BOX 808 LIVERMORE CA 94550
1	LAWRENCE LIVERMORE NATL LAB L 282 J MOLITORIS PO BOX 808 LIVERMORE CA 94551
1	LOS ALAMOS NATL LAB MS P918 DX DO W DANEN LOS ALAMOS NM 87545

NO. OF COPIES	ORGANIZATION
1	LOS ALAMOS NATL LAB MS E549 K HUBBARD LOS ALAMOS NM 87545
1	LOS ALAMOS NATL LAB MS C920 S SON LOS ALAMOS NM 87545
1	LOS ALAMOS NATL LAB GROUP DX 2 MS C920 B TAPPAN LOS ALAMOS NM 87545
1	SANDIA NATL LABORATORIES MS 0836 M BAER ALBUQUERQUE NM 87185-0836
1	SANDIA NATL LABORATORIES MS 0836 E HERTEL ALBUQUERQUE NM 87185-0836
1	SANDIA NATL LABORATORIES MS 1172 T HITCHCOCK PO BOX 5800 ALBUQUERQUE NM 87185-1172
1	SANDIA NATL LABORATORIES PO BOX 5800 MS 1452 B INGRAM ALBUQUERQUE NM 87185-1452
1	SANDIA NATL LABORATORIES PO BOX 5800 MS 1454 M KANESHIGE ALBUQUERQUE NM 87185-1454
1	SANDIA NATL LABORATORIES PO BOX 5800 MS 1452 B MELOF ALBUQUERQUE NM 87185-1452
1	SANDIA NATL LABORATORIES PO BOX 5800 MS 1454 A RENLUND ALBUQUERQUE NM 87185-1424

NO. OF COPIES	ORGANIZATION
1	DEFENSE THREAT REDUCTION AGENCY TDSH J KOLTS STOP 6201 8725 JOHN J KINGMAN RD FORT BELVOIR VA 22060
1	DCI CTR FOR WEAPONS INTELLIGENCE NONPROLIFERATION AND ARMS CONTROL WINPAC M AGUILO WASHINGTON DC 20505
1	J BACKOFEN 2668 PETERSBOROUGH ST HERNDON VA 20171-2443
1	C LLOYD 47110 SOUTHAMPTON STERLING VA 20165
1	DCI CTR FOR WEAPONS INTELLIGENCE NONPROLIFERATION AND ARMS CONTROL WINPAC J WALTON WASHINGTON DC 20505
1	DEFENSE INTELLIGENCE AGENCY BLDG 6000 DWO 4 K CRELLING BOLLING AIR FORCE BASE WASHINGTON DC 20340-5100
1	AEROJET E LIU PO BOX 13222 SACRAMENTO CA 95813
1	ALLIANT TECHSYSTEMS INC C ZISETTE PO BOX 1 RADFORD VA 24141
1	APPLIED RSCH ASSOCIATES C NEEDHAM SUITE A 220 4300 SAN MATEO BLVD NE ALBUQUERQUE NM 87110

NO. OF COPIES	ORGANIZATION
1	ARGONIDE CORP F TEPPER 291 POWER CT SANFORD FL 32771
1	ATK THIOKOL PROPULSION PO BOX 707 MS 244 J AKESTER BRIGHAM CITY UT 84302-0707
1	ATK THIOKOL PROPULSION PO BOX 707 MS 244 P BRAITHWAITE BRIGHAM CITY UT 84302
1	ATK THIOKOL PROPULSION PO BOX 707 MS 230 S GLAITTLI BRIGHAM CITY UT 84302-0707
1	ATK THIOKOL PROPULSION PO BOX 707 MS 244 K LEE BRIGHAM CITY UT 84302-0707
1	ATK THIOKOL PROPULSION PO BOX 707 MS 244 G LUND BRIGHAM CITY UTAH 84302
1	ATK THIOKOL PROPULSION PO BOX 707 MS 230 S LUSK BRIGHAM CITY UT 84302-0707
1	BATTELLE MEMORIAL INSTITUTE T BURKY 505 KING AVE COLUMBUS OH 43201
1	BOOZ ALLEN HAMILTON G ZUCCARELLO 3811 N FAIRFAX DR STE 600 ARLINGTON VA 22203
1	CACI INC M EGGLESTON 14151 PARK MEADOW DR CHANTILLY VA 20151
1	DE TECHNOLOGIES INC C FORSYTH 3620 HORIZON DR KING OF PRUSSIA PA 19406

NO. OF COPIES	ORGANIZATION
1	ENERGETIC MATERIALS APPLICATIONS L JOSEPHSON 300 DAWN CT RIDGECREST CA 93555
1	ENSIGN BICKFORD AEROSPACE & DEFENSE A GARVEY 640 HOPMEADOW ST BLDG 46 SIMSBURY CT 06070
1	EXOTHERM CORPORATION A LASCHIVER 1035 LINE ST CAMDEN NJ 08103
1	GENERAL SCIENCES INC P ZAVITSANOS 205 SCHOOLHOUSE RD SOUDERTON PA 18964
1	GEO CTRS INC BLDG 3028 D PARITOSH PICATINNY ARSENAL NJ 07806-5000
1	HICKS & ASSOCIATES INC SUITE 1300 C KITCHENS JR 1710 SAIC DR MCLEAN VA 22102
1	NANOTECHNOLOGIES INC D HAMILL 1908 KRAMER LN AUSTIN TX 78758
1	NORTHROP GRUMMAN CORP/DTRA J COCCHIARO 6940 S KINGS HIGHWAY STE 210 ALEXANDRIA VA 22310
1	NORTHROP GRUMMAN IT M SEIZEW PO BOX 471 SAN PEDRO CA 90733-0471
1	PRATT & WHITNEY N TRIVEDI 600 METCALF RD SAN JOSE CA 95138

NO. OF COPIES	ORGANIZATION
1	ST MARKS POWDER A GENERAL DYNAMICS CO J DRUMMOND PO BOX 222 ST MARKS FL 32355
1	SAIC W WAESCHE 4319 BANBURY DR GAINESVILLE VA 20155
1	SRI INTERNATL J BOTTARO RM PS 318 333 RAVENSWOOD AVE MENLO PARK CA 94025
1	TALLEY DEFENSE SYSTEMS G KNOWLTON 40512 N HIGLEY RD MESA AZ 85205

ABERDEEN PROVING GROUND

26	DIR USARL AMSRD ARL WM B A HORST AMSRD ARL WM BD W ANDERSON R BEYER A BRANT S BUNTE E BYRD L CHANG J COLBURN P CONROY B FORCH B HOMAN P KASTE A KOTLAR C LEVERITT K MCNESBY M MCQUAID A MIZIOLEK M NUSCA R PESCE-RODRIGUEZ B RICE R SAUSA AMSRD ARL WM TB P BAKER D KOOKER B KRZEWINSKI R LOTTERO B ROOS